

NCHRP

Project 9-44

**Developing a Plan for Validating an
Endurance Limit for HMA Pavements**

HMA Endurance Limit Validation Study

Research Plan

LIMITED USE DOCUMENT

The information contained in this Document is regarded as fully privileged. Dissemination of information included herein must be approved by the NCHRP.

**Final
November 21, 2008**

**Advanced Asphalt Technologies, LLC
108 Powers Court, Suite 100
Sterling, Virginia 20166**

**ADVANCED ASPHALT TECHNOLOGIES
ENGINEERING SERVICES FOR THE ASPHALT INDUSTRY**



ACKNOWLEDGMENT OF SPONSORSHIP

This work was sponsored by the American Association of State Highway and Transportation Officials, in cooperation with the Federal Highway Administration, and was conducted in the National Cooperative Highway Research Program, which is administered by the Transportation Research Board of the National Research Council.

DISCLAIMER

This is an uncorrected draft as submitted by the research agency. The opinions and conclusions expressed or implied in the report are those of the research agency. They are not necessarily those of the Transportation Research Board, the National Research Council, the Federal Highway Administration, the American Association of State Highway and Transportation Officials, or the individual states participating in the National Cooperative Highway Research Program.

Table of Contents

Table of Contents	i
Table of Contents	ii
List of Figures	iv
List of Tables	v
List of Tables	v
Acknowledgements	vi
Acknowledgements	vi
Abstract	vii
Introduction	1
Purpose	1
Statement of the Problem	1
Objectives and Hypothesis	4
Scope of the Plan	5
Summary of the Research Plan	7
Task by Task Description of the Research Plan	12
Task A. Management and Reporting	12
Subtask A.1 Project Management	12
Subtask A.2 Progress Reporting	15
Subtask A.3 Interim Reports and Presentations	15
Subtask A.4 Final Report and Presentation	16
Task A Milestones	16
Task A Labor Estimate	16
Task A Sources	18
Task B. Formulate Design Procedure	18
Preliminary Design Procedure	18
Subtask B.1 Review Selected Literature	34
Subtask B.2 Finalize Preliminary Approach	36
Subtask B.3 Incorporate Findings from Laboratory Studies	36
Subtask B.4 Modify Approach Based on Analysis of Accelerated Pavement Tests	37
Subtask B.5 Prepare Final Design Procedure	38
Task B Milestones	38
Task B Labor Estimate	39
Task B Sources	39
Task C. Database Management	41
Subtask C.1 Develop a Plan to Use the NCHRP 9-30 Database	41
Subtask C.2 Develop Needed Tables	43
Subtask C.3 Input and Manage Data	43
Task C Milestones	43

Task C Labor Estimate.....	43
Task C Sources	44
Task D. Laboratory Studies	44
Subtask D.1 Experiment 1: Mixture Compositional Factors Affecting Healing in HMA..	46
Subtask D.2 Experiment 2: Effect of Applied Strain on Healing	55
Subtask D.3 Experiment 3: Effect of Temperature and Rest Period Duration on Healing	56
Subtask D.4 Experiment 4: Development of Testing and Analysis Procedures to Determine Allowable Strain Levels.....	63
Subtask D.5 Experiment 5: Estimation of Allowable Strain Levels from Mixture Composition.....	72
Task D Milestones	75
Task D Labor Estimate	76
Task D Sources	77
Task E. Analysis of Pavement Sections.....	79
Subtask E.1 Review Data Sources and Select Sections for Analysis	80
Subtask E.2 Obtain Materials and Data for Accelerated Pavement Tests and Test Roads .	90
Subtask E.3 Perform Lab Testing and Analyze Accelerated Pavement Tests and Test Roads	92
Subtask E.4 Obtain Materials and Data for In-Service Pavement Sections	92
Subtask E.5 Perform Lab Testing and Analyze In-Service Pavement Sections	93
Task E Milestones.....	97
Task E Labor Estimate.....	98
Task E Sources.....	98
Schedule of Tasks	101
Budget	104
References.....	107
Appendix A: Recommended LTPP Test Sections.....	113

List of Figures

Figure 1. Typical S-N Diagram From Laboratory Fatigue Tests.....	2
Figure 2. Results of Flexural Fatigue Tests by Carpenter et al., Including Extrapolated Results at Low Strain Levels	3
Figure 3. Project Flow Chart.....	7
Figure 4. Overall Project Schedule.	Error! Bookmark not defined.
Figure 5. Recommended Research Management Structure.....	14
Figure 6. Effect of Rest Periods on Plateau Value	22
Figure 7. Effect of Rest Period on Fatigue Life.....	23
Figure 8. Plateau Value for Continuous Loading as a Function of Applied Strain Level.	25
Figure 9. Application of Time-Temperature Superposition to Rest Periods.	28
Figure 10. Comparison of Applied and Allowable Strains.....	32
Figure 11. Example of Minimum Asphalt Thicknesses to Resist Bottom Initiated Fatigue Cracking With Observed Performance of Four UK Pavement Sections.	33
Figure 12. Schematic of Pulsed, Strain Controlled Fatigue Loading.	53
Figure 13. Expected Results When Healing is Significant.	54
Figure 14. Schematic of Time-Temperature Superposition Applied to Rest Periods.....	62
Figure 15. Typical Plot of Ratio of Dissipated Energy Change Versus Loading Cycles	64
Figure 16. Typical Damage Ratio Curves From a Cyclic Direct Tension Fatigue Test.....	67
Figure 17. Typical Damage Relationship From Continuum Damage Analysis.	70
Figure 18. Comparison of Area Fatigue Cracking (Area Alligator Cracking Based on a Percent of Wheel Path Area) and HMA Layer Thickness	86
Figure 19. Comparison of the Area Fatigue Cracking for and Maximum Tensile Strain Computed at the Bottom of the HMA Layer	86
Figure 20. Comparison of the Maximum Tensile Strain at the Bottom of the HMA Layer and HMA Thickness	88
Figure 21. Schematic of Field Section Data Analysis.	95
Figure 22. Project Schedule With Critical Path Shown in Black. Error! Bookmark not defined.	
Figure 23. Project Budget.	105
Figure 24. Estimated Monthly and Cumulative Expenditures.....	106

List of Tables

Table 1. Summary of Man-hour and Cost Estimates.....	8
Table 2. Major Task 1 Milestones.....	17
Table 3. Estimated Labor Hours for Task 1.....	17
Table 4. Summary of Existing Pavement Analysis Approaches Considered.....	20
Table 5. Effect of Rest Period on Fatigue Life.....	23
Table 6. Approximate Rest Periods for Various Design Traffic Levels.....	24
Table 7. Allowable Strains for Various Design Traffic Levels.....	27
Table 8. Computation of Allowable Strain Strains.....	30
Table 9. Applied Strains for Design Example.....	31
Table 10. Major Task 2 Milestones.....	38
Table 11. Estimated Labor Hours for Task 2.....	39
Table 12. Major Task C Milestones.....	43
Table 13. Estimated Labor Hours for Task C.....	44
Table 14. Summary of Proposed Laboratory Experiments.....	45
Table 15. Design for a Two Level, Seven Factor Plackett-Burman Experiment.....	47
Table 16. Summary of Proposed Experiment 1.....	52
Table 17. Strain Level Experiment.....	56
Table 18. Experimental Design for Experiment 3.....	57
Table 19. Temperature and Frequency Combinations for Dynamic Modulus Tests.....	58
Table 20. Major Task 4 Milestones.....	76
Table 21. Estimated Labor Hours for Task 4.....	76
Table 22. HMA Thicknesses in NCAT Structural Sections.....	82
Table 23. Summary of MNRoad Mainline HMA Pavement Sections.....	83
Table 24. FHWA Pavement Testing Facility Superpave Fatigue Experiment.....	83
Table 25. Preliminary Matrix for Field Calibration of the Allowable Strain Limit Design Procedure.....	89
Table 26. LTPP Sections Recommended for Consideration.....	90
Table 27. Summary of Required Inputs for Allowable Strain Limit Design.....	91
Table 28. Preliminary Testing Plan for Cores From the LTPP Sections.....	94
Table 29. Major Task 5 Milestones.....	97
Table 30. Estimated Labor Hours for Task 5.....	98
Table 31. Project Milestone Summary.....	103
Table 32. Labor Costs Used in Budget Preparation.....	104
Table 33. Travel Cost Estimate.....	104
Table 34. Estimate of Report Printing Costs.....	104

Acknowledgements

The work reported herein was performed under NCHRP Project 9-44 by Advanced Asphalt Technologies, LLC, and Applied Research Associates, Inc. Ramon Bonaquist, Chief Operating Officer for Advanced Asphalt Technologies, LLC, served as Principal Investigator for the project and was the primary author of this research plan. Mr. Harold Von Quintus, Principal Engineer for Applied Research Associates, Inc. co-authored this research plan.

Special thanks are extended to the participants of the HMA Endurance Limit Workshop listed below. These professionals unselfishly presented ideas to the research team that helped shape the planned research.

Name	Affiliation
Dr. David Anderson	Consultant
Dr. Samuel Carpenter	University of Illinois
Dr. Donald Christensen	Advanced Asphalt Technologies, LLC
Dr. Herve Di Benedetto	Ecole Nat. des TPE
Mr. Bruce Dietrich	Florida Department of Transportation
Mr. Kenneth Fults	KWF Pavement Consulting
Mr. Roger Green	Ohio Department of Transportation
Dr. Kevin Hall	University of Arkansas
Dr. Edward Harrigan	National Cooperative Highway Research Program
Dr. Richard Kim	North Carolina State University
Dr. Dallas Little	Texas A&M University
Dr. Leslie Ann McCarthy	Federal Highway Administration
Dr. Andre Molenaar	Delft University
Professor Carl Monismith	University of California Berkeley
Dr. David Newcomb	National Asphalt Pavement Association
Dr. Michael Nunn	Lane One Limited
Dr. Brian Prowell	Advanced Material Services, LLC
Dr. Rey Roque	University of Florida
Ms. Amy Schutzbach	Illinois Department of Transportation
Dr. Jacob Uzan	Technion University
Dr. Linbing Wang	Virginia Polytechnic and State University
Dr. Matthew Witczak	Arizona State University

Abstract

This document presents a plan for research to rationally incorporate the concept of an endurance limit for hot mix asphalt (HMA) into a mechanistic-empirical algorithm for bottom initiated fatigue cracking in flexible pavements, and to validate the resulting procedure using performance data from full-scale pavement sections.

The planned research is based on the hypothesis that the endurance limit for HMA is the result of a balance of damage caused by loading and healing or damage recovery that occurs during rest periods. Under this hypothesis the primary objective in designing a flexible pavement to resist bottom initiated fatigue cracking will be to make sure that the damage induced by loading remains small enough so that healing occurs and there is no accumulation of damage over the life of the pavement. This is a significant departure from current cumulative or incremental damage models, which assume that no healing occurs and that each load cycle uses up a portion of the finite fatigue life of the HMA.

This research plan includes a preliminary design procedure that is based on layered elastic analysis and compatible with the Mechanistic-Empirical Pavement Design Guide (MEPDG). It uses allowable strains to identify satisfactory conditions for full healing. The allowable strains are a function of the properties of the HMA, the pavement temperature, and the duration of rest periods between traffic loads. Five laboratory experiments that are needed to fully develop the procedure are described. Studies using data from completed accelerated pavement tests and test roads are proposed to verify critical aspects of the design procedure. Finally, an experiment to calibrate the design procedure using selected test sections from the Long Term Pavement Performance Program is presented.

The recommended research study has been titled the HMA Endurance Limit Validation Study. It addresses an important concept in the design of perpetual pavements that is gaining increasing acceptance worldwide. It is envisioned that application of an endurance limit in flexible pavement design will lead to more effective pavement sections with significant benefit and cost savings to the public.

Introduction

Purpose

This document presents a plan for research to rationally incorporate the concept of an endurance limit for hot mix asphalt (HMA) into a mechanistic-empirical algorithm for bottom initiated fatigue cracking in flexible pavements, and to validate the resulting procedure using performance data from full-scale pavement sections. For HMA pavements, the endurance limit has been defined as *a level of strain below which there is no cumulative damage over an indefinite number of load cycles (1)*.

This research plan is the primary product of National Cooperative Highway Research Program (NCHRP) Project 9-44, *Developing a Plan for Validating an Endurance Limit for HMA Pavements*. The recommended research study has been titled the HMA Endurance Limit Validation Study. It addresses an important concept in the design of perpetual pavements that is gaining increasing acceptance worldwide. It is envisioned that application of an endurance limit in flexible pavement design will lead to more effective pavement sections with significant benefit and cost savings to the public.

Statement of the Problem

In engineering, fatigue refers to the progressive and localized damage that occurs when a material is subjected to repeated loading below its ultimate strength. It is an important consideration in the design of many civil engineering structures including pavements.

The fatigue behavior of materials is evaluated using laboratory fatigue tests, where a sample is loaded repeatedly using a known stress or strain and the number of load applications are counted until the sample fails. By performing tests at different stress or strain levels a Wöhler curve or S-N diagram can be developed. These diagrams are simply plots of the applied stress or strain and the corresponding number of cycles to failure. Figure 1 shows two typical S-N diagrams generated from laboratory test data. In curve (a), the fatigue life increases at a gradually increasing rate with decreasing stress amplitude. In curve (b), on the other hand, the fatigue life gradually increases until a limit is reached (50 MPa in this case) where the fatigue

life becomes indefinite. This is called the endurance limit for the material. The endurance limit is a critical concept in the design of structures that must resist large numbers of repeated loads. If stresses or strains are kept below the endurance limit, the structure will be able to withstand an infinite number of load applications.

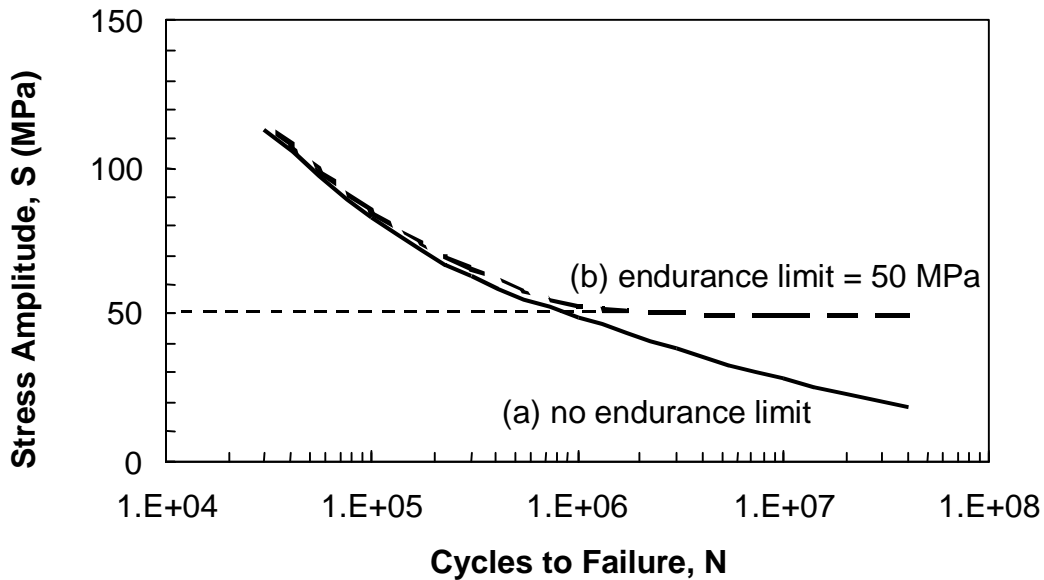


Figure 1. Typical S-N Diagram From Laboratory Fatigue Tests: (a) No Endurance Limit; (b) 50 MPa Endurance Limit.

Many materials do not have the well-defined endurance limit shown schematically in Figure 1. HMA is one of these materials. Although early HMA fatigue research conducted by Monismith and his colleagues suggested that HMA exhibited an endurance limit at approximately 70 μ strain (2), only limited HMA fatigue research was conducted at low strain levels until recently when the Asphalt Pavement Alliance began promoting the concept of perpetual pavement design (3). A perpetual pavement is an asphalt pavement that provides a very long life without structural failure and only requires periodic replacement of the surface. A key element of perpetual pavement design is to eliminate fatigue cracking that initiates at the bottom of the HMA base due to repeated flexure under traffic loading and to confine distresses to the surface of the pavement, which can easily be renewed by milling and resurfacing.

In response to increasing interest in perpetual pavements, a substantial amount of laboratory fatigue testing has recently been performed in the United States in an effort to demonstrate that HMA does exhibit an endurance limit. Most of this work has been performed at the University of Illinois (4,5) and the National Center for Asphalt Technology (NCAT) (6). These studies provide clear evidence that the fatigue behavior of HMA is much different in low strain level tests compared to normal strain level tests. Figure 2 shows a consolidated plot of the University of Illinois fatigue data including low and normal strain level test data. Below approximately 100 μ strain, the fatigue life is significantly longer than estimated from extrapolation of normal strain level test data. Healing of microdamage has been proposed as the primary reason for the increased fatigue life at low strain levels (1, 7, 8). For cyclic tests at low strain levels, it appears that the damage that is caused by loading is offset by healing that occurs during unloading resulting in essentially infinite fatigue life. Current mechanistic-empirical fatigue criteria for HMA, including the field calibrated criterion in the Mechanistic Empirical Pavement Design Guide (MEPDG), are based on results from normal strain level tests and do not include the low strain level effects shown in Figure 2.

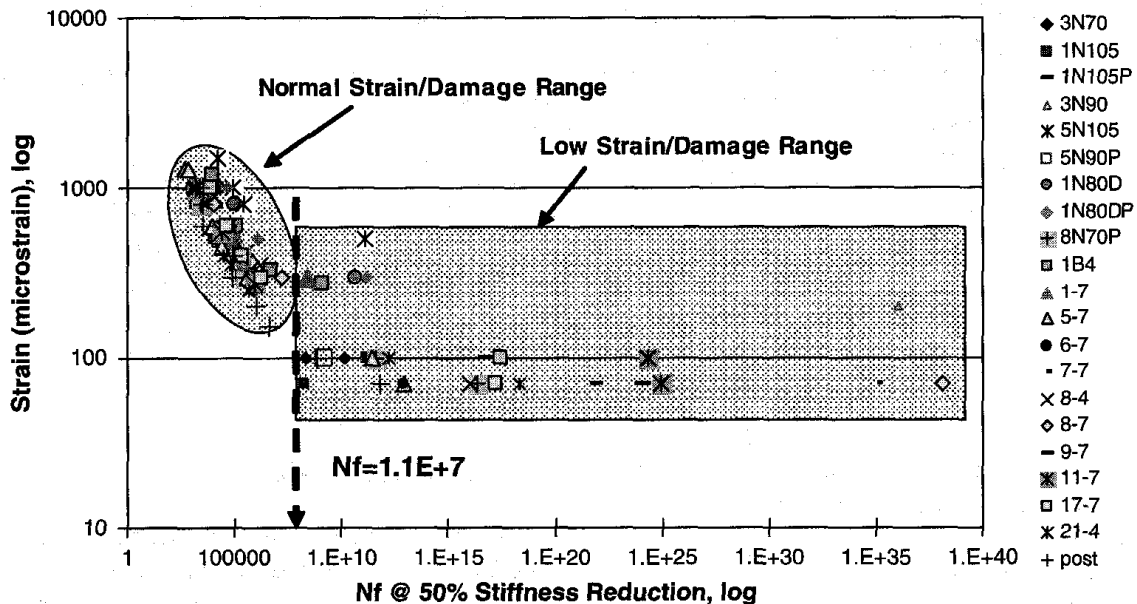


Figure 2. Results of Flexural Fatigue Tests by Carpenter et al., Including Extrapolated Results at Low Strain Levels (4).

Detailed investigation of four heavily trafficked pavements in the United Kingdom support the perpetual pavement concept and the likelihood of an endurance limit for HMA. This comprehensive study found no evidence of fatigue damage at the bottom of properly constructed thick flexible pavements with total HMA thickness ranging from 230 to 350 mm (9). Cracks in these pavements were found to have initiated at the surface and deflections monitored over a number of years generally showed steady or decreasing deflection with increasing cumulative traffic, indicating that fatigue damage to the bottom of the HMA was not occurring. Similar conclusions concerning the absence of cracking at the bottom of thick HMA pavements have been reported by others (10, 11, 12).

In summary, there is mounting evidence that an endurance limit for HMA does exist. It has been observed in laboratory studies of fatigue at low strain levels, and several documented case studies indicate that bottom initiated fatigue cracking is almost non-existent in properly constructed, thick HMA pavements. A concentrated research effort, however, is needed to validate the endurance limit concept, and to devise effective methods for incorporating it in mechanistic-empirical pavement design methods.

Objectives and Hypothesis

The objectives of the HMA Endurance Limit Validation Study are:

1. To incorporate the concept of an endurance limit for HMA into a mechanistic-empirical algorithm for bottom initiated fatigue cracking in flexible pavements.
2. To validate the methodology using performance data from full-scale pavement sections.

These objectives could potentially be satisfied using a number of research approaches. The specific approach presented in this plan is based on the following hypothesis, which was developed from a review of recent literature concerning the fatigue response of HMA, and recommendations made during the HMA Endurance Limit Workshop conducted early in NCHRP Project 9-44 (1):

HMA does exhibit an endurance limit. This endurance limit, however, does not reflect an absence of load induced damage in the HMA. It is the result of a balance of damage caused by loading and healing or damage recovery that occurs during rest periods. The endurance limit for HMA is, therefore, not a single value, but will change depending on the loading and environmental conditions applied to the HMA. To properly consider this form of an endurance limit in flexible pavement design requires consideration of the effects of loading, environment and material properties on both damage accumulation and healing.

Under this hypothesis the primary objective in designing a flexible pavement to resist bottom initiated fatigue cracking will be to make sure that the damage induced by loading remains small enough so that healing occurs and there is no accumulation of damage over the life of the pavement. This is a significant departure from current cumulative or incremental damage models which assume that no healing occurs and that each load cycle uses up a portion of the finite fatigue life of the HMA. The hypothesis presented above implies that any flexible pavement structure can be designed to indefinitely resist bottom initiated fatigue cracking. Thicker pavements will be required for heavier loads, shorter rest periods (higher traffic volume), and poorer foundation conditions. To successfully formulate this type of design procedure will require research to quantify the effects of temperature, aging, and materials properties on damage accumulation and damage recovery in HMA. Once formulated, the procedure can be validated using performance data from full-scale pavement sections.

Scope of the Plan

This research plan is a comprehensive document describing the research that must be completed to successfully incorporate the concept of an endurance limit for HMA into a fatigue algorithm for bottom initiated fatigue cracking and to validate the resulting procedure using full-scale pavement sections. It includes four parts in addition to this Introduction. The first is a summary that briefly describes the proposed research and presents overall cost estimates and time requirements. The second is a description of the required research tasks. This section includes detailed information for each task and subtask, including (1) a description of the work to be performed, (2) preliminary experimental designs when appropriate, (3) a list of milestones related to the task, (4) labor hour estimates, and (5) a listing of pertinent data and reference material that will be needed to accomplish the task. The third is a detailed schedule for the

project. The schedule addresses the sequence of the research tasks and the interactions between tasks. Finally, the fourth presents the proposed budget for the project. The budget includes detailed estimates of labor and other costs associated with each task and subtask.

Summary of the Research Plan

The HMA Endurance Limit Validation Study consist of five major tasks: (A) Management and Reporting, (B) Formulate Design Procedure, (C) Database Management, (D) Laboratory Studies, and (E) Analysis of Pavement Sections. Figure 3 presents an overall flow chart for the project with major interactions between tasks identified. Table 1 lists the subtasks for each of the five major tasks and presents estimated labor hours and costs. The HMA Endurance Limit Validation Study is estimated to require approximately 12,923 man-hours of effort at a cost of approximately \$1.5 million. Figure 4 presents the overall schedule for the project, which is estimated to require 48 months to complete.

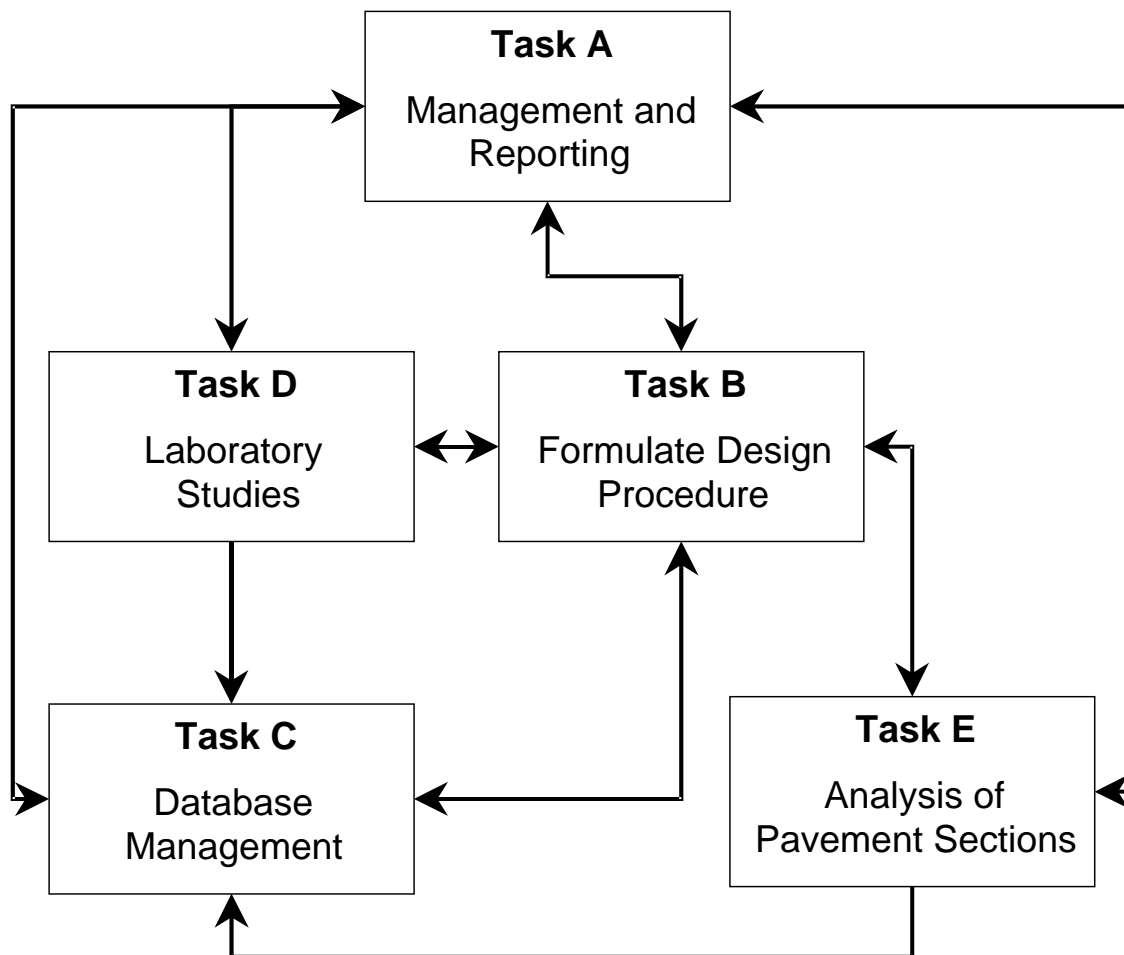


Figure 3. Project Flow Chart.

Table 1. Summary of Man-hour and Cost Estimates.

Task/ Subtask	Description	Estimated Labor Hours				Estimated Cost
		Senior Eng./ Stat	Eng./ Prog.	Tech.	Admin.	
A.0	Management and Reporting					
A.1	Project Management	424	0	0	40	\$66,000
A.2	Progress Reporting	210	0	0	20	\$32,700
A.2	Interim Reports and Presentations	780	0	0	80	\$129,780
A.3	Final Report and Presentation	420	0	0	40	\$68,400
Task A Total		1834	0	0	180	\$296,880
B.0	Formulate Design Procedure					
B.1	Review Selected Literature	240	160	0	0	\$52,000
B.2	Finalize Preliminary Approach	80	160	0	0	\$28,000
B.3	Incorporate Findings from Laboratory Studies	80	160	0	0	\$28,000
B.4	Modify Approach Based on Analysis of Accelerated Pavement Tests	80	80	0	0	\$20,000
B.5	Prepare Final Design Procedure	120	80	0	0	\$26,000
Task B Total		600	640	0	0	\$154,000
C.0	Database Management					
C.1	Develop Plan to Use NCHRP 9-30 Database	120	0	0	0	\$18,000
C.2	Develop Needed Tables	80	240	0	0	\$36,000
C.3	Input and Manage Data	40	396	0	0	\$45,600
Task C Total		240	636	0	0	\$99,600
D.0	Laboratory Studies					
D.1	Experiment 1: Mixture Compositional Factors Affecting Healing	42	0	388	0	\$39,280
D.2	Experiment 2: Effect of Applied Strain on Healing	32	0	214	0	\$22,990
D.3	Experiment 3: Effect of Temperature and Rest Period Duration on Healing	69	0	242	0	\$30,920
D.4	Experiment 4: Testing and Analysis Procedures for Allowable Strain Levels	168	0	392	0	\$58,520
D.5	Experiment 5: Estimation of Allowable Strain Levels from Mixture Composition	456	0	1890	0	\$229,050
Task D Total		767	0	3126	0	\$380,760
E.0	Analysis of Pavement Sections					
E.1	Review Data Sources and Select Sections for Analysis	52	320	0	0	\$39,800
E.2	Obtain Materials and Data for Accelerated Pavement Tests	48	280	0	0	\$35,200
E.3	Perform Testing and Analyze Accelerated Pavement Tests	164	512	32	0	\$78,520
E.4	Obtain Materials and Data for In-Service Pavement Sections	120	1280	0	0	\$195,600
E.5	Perform Testing and Analyze In-Service Pavement Sections	300	512	1280	0	\$205,000
Task E Total		684	2904	1312	0	\$554,120
Project Total		4,125	4,180	4,438	180	1,485,360

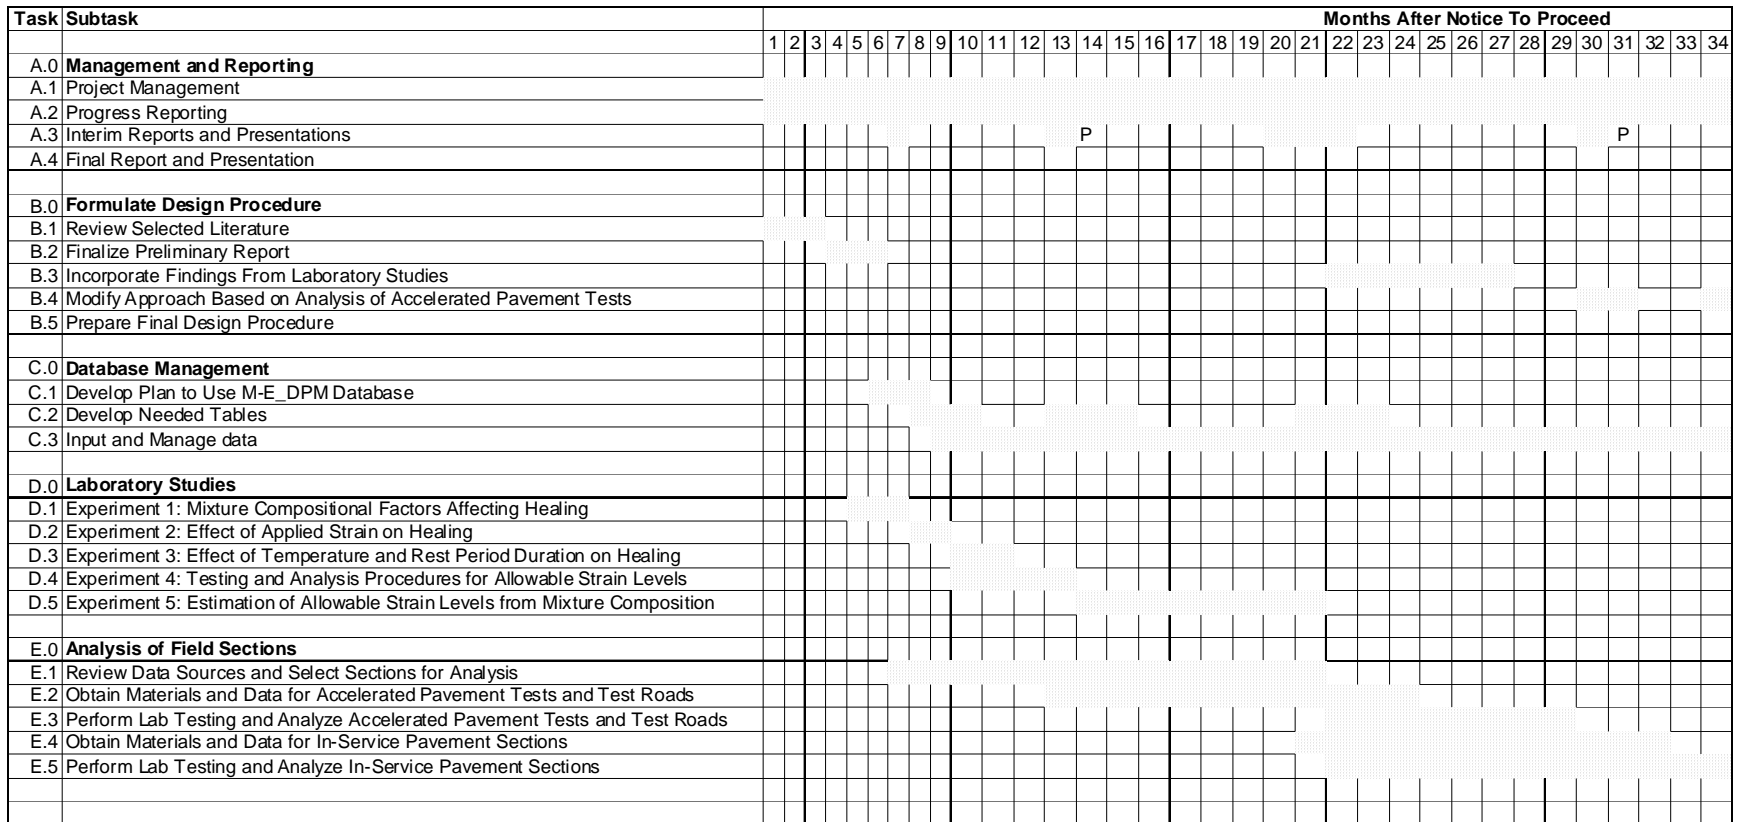


Figure 4. Overall Project Schedule.

Figure 4. Overall Project Schedule

Task A, Management and Reporting, includes all activities normally associated with management and reporting for NCHRP Projects. Major management tasks include scheduling, coordinating, and directing various technical work activities as well as project financial management. Reporting activities include monthly and quarterly progress reports, the preparation of several interim reports and presentations, and the preparation of the final report. Interim reports are required at approximately 6 month intervals and coincide with the completion of five critical milestones:

- (1) Formulation of the preliminary design procedure and selection of the laboratory analysis approach,
- (2) Selection of pavement sections for analysis,
- (3) Completion of the laboratory studies,
- (4) Modification of the preliminary design procedure to reflect the findings from the laboratory studies and the analysis of accelerated pavement tests, and
- (5) Analysis of the calibration sections and preparation of the final design procedure.

The final report will document the entire study and will be prepared from the interim reports.

Task B, Formulate Design Procedure, is a critical project task that will be active throughout the project. This task includes finalizing the preliminary approach that is presented in this research plan, modifying the preliminary approach based on the results of the laboratory studies and selected accelerated pavement tests, and preparation of the final design procedure after analysis of the calibration pavement sections. It is important to emphasize that the preliminary approach prepared early in this task will shape the laboratory studies and guide the selection of pavement sections, both accelerated pavement tests and in-service pavement sections.

Task C, Database Management, is a support task that will be active throughout the project. A database will be developed in this task to store and analyze data from the laboratory studies and the analysis of the pavement sections. It is envisioned that the database will be an adaptation of the one developed in NCHRP Project 9-30.

Task D, Laboratory Studies, includes the planning and execution of five laboratory studies that are needed to complete the design procedure that will be formulated in Task 2. The laboratory studies concentrate on quantifying what affects the healing properties of HMA. The laboratory studies will be sufficient in breadth to develop models relating mixture and binder properties to the key engineering properties required for the analysis.

Task E, Analysis of Pavement Sections, includes several activities associated with the selection and analysis of full-scale pavements. The preliminary design procedure formulated in Task 2 will be tested using data from completed accelerated pavement tests, such as the fatigue studies from the Federal Highway Administration's (FHWA's) Pavement Testing Facility or the structural sections included in the National Center for Asphalt Technology (NCAT) test track. Calibration of the design procedure will be accomplished through an analysis of in-service pavements where it has been documented that bottom-up fatigue cracking has occurred or has not occurred. These analyses will serve to calibrate the design procedure and validate the HMA endurance limit concept. The predictive models developed in Task D will be used in the analysis of the full-scale pavement sections. This will allow consideration of pavement sections where original materials are not available since the required data can be obtained from cores taken from the pavement section.

Task by Task Description of the Research Plan

This section of the research plan presents detailed descriptions of each of the tasks and subtasks included in the HMA Endurance Limit Validation Study. Each task description includes a detailed description of the work to be performed including: (1) preliminary experimental designs when appropriate, (2) a list of milestones related to the task, (3) labor hour estimates, and (4) a listing of pertinent data and reference material that will be needed to accomplish the task.

Task A. Management and Reporting

Task A includes all activities normally associated with management and reporting for NCHRP projects. Task A has been divided into four subtasks:

- A.1 Project Management,
- A.2 Progress Reporting,
- A.3 Interim Reports and Presentations, and
- A.4 Final Report and Presentation.

Each of these subtasks are described in detail below.

Subtask A.1 Project Management

Effective project management will be critical to the successful completion of the HMA Endurance Limit Study. The study requires that the Principal Investigator have in-depth knowledge of the following technical areas:

- Mechanistic-empirical pavement design and analysis,
- Experimental design,
- Model development,
- Laboratory characterization of HMA,
- Accelerated pavement testing, and
- Pavement evaluation.

Since the design procedure incorporating an endurance limit for bottom initiated fatigue cracking will determine the details of the laboratory and field studies, the Principal Investigator should directly lead Task B, Formulate Design Procedure. To efficiently manage several tasks that will be conducted concurrently, the team structure shown in Figure 5 is recommended. In this structure, the Principal Investigator is supported by three teams: Laboratory, Pavement, and Data Support, each with a separate team leader. Additionally, it is strongly recommended that a Statistician be included in the project team to assist the Principal Investigator and team leaders with detailed experimental design, model formulation, and model calibration. The Principal Investigator will be responsible for the overall technical content of the project, while the team leaders will be responsible for the details of the work in their area of expertise. In addition to the scenario shown in Figure 5 where the management team consists of the Principal Investigator and three team leaders, other structures are possible depending on the skills and commitment levels of the senior members of the research team. For example, the Principal Investigator may also serve as one of the team leaders and one individual may serve as the leader of the remaining two teams. It is recommended, however, that a single individual not fill more than two leadership roles.

This research plan as modified during the proposal process will serve as the principal project management tool. Shortly after contract award, the research management team should meet and the Principal Investigator should make initial task assignments to the project team. The research management team should then meet semi-monthly to discuss the progress of the work and resolve any problems that may develop. These meetings should be scheduled to provide timely information for the monthly and quarterly progress reports discussed in the next section.

Another important aspect of project management is coordination with other on-going research efforts. Several studies addressing cracking in flexible pavements are on-going including: (1) NCHRP 1-41, *Models for Predicting Reflection Cracking of Hot-Mix Asphalt Overlays*, (2) NCHRP 1-42A, *Models for Predicting Top-Down Cracking of Hot-Mix Asphalt Layers*, and (3) the fatigue studies being conducted in the Asphalt Research Consortium. Although different approaches are being used in each of these studies, it is important that the research team monitor and share information with these studies.

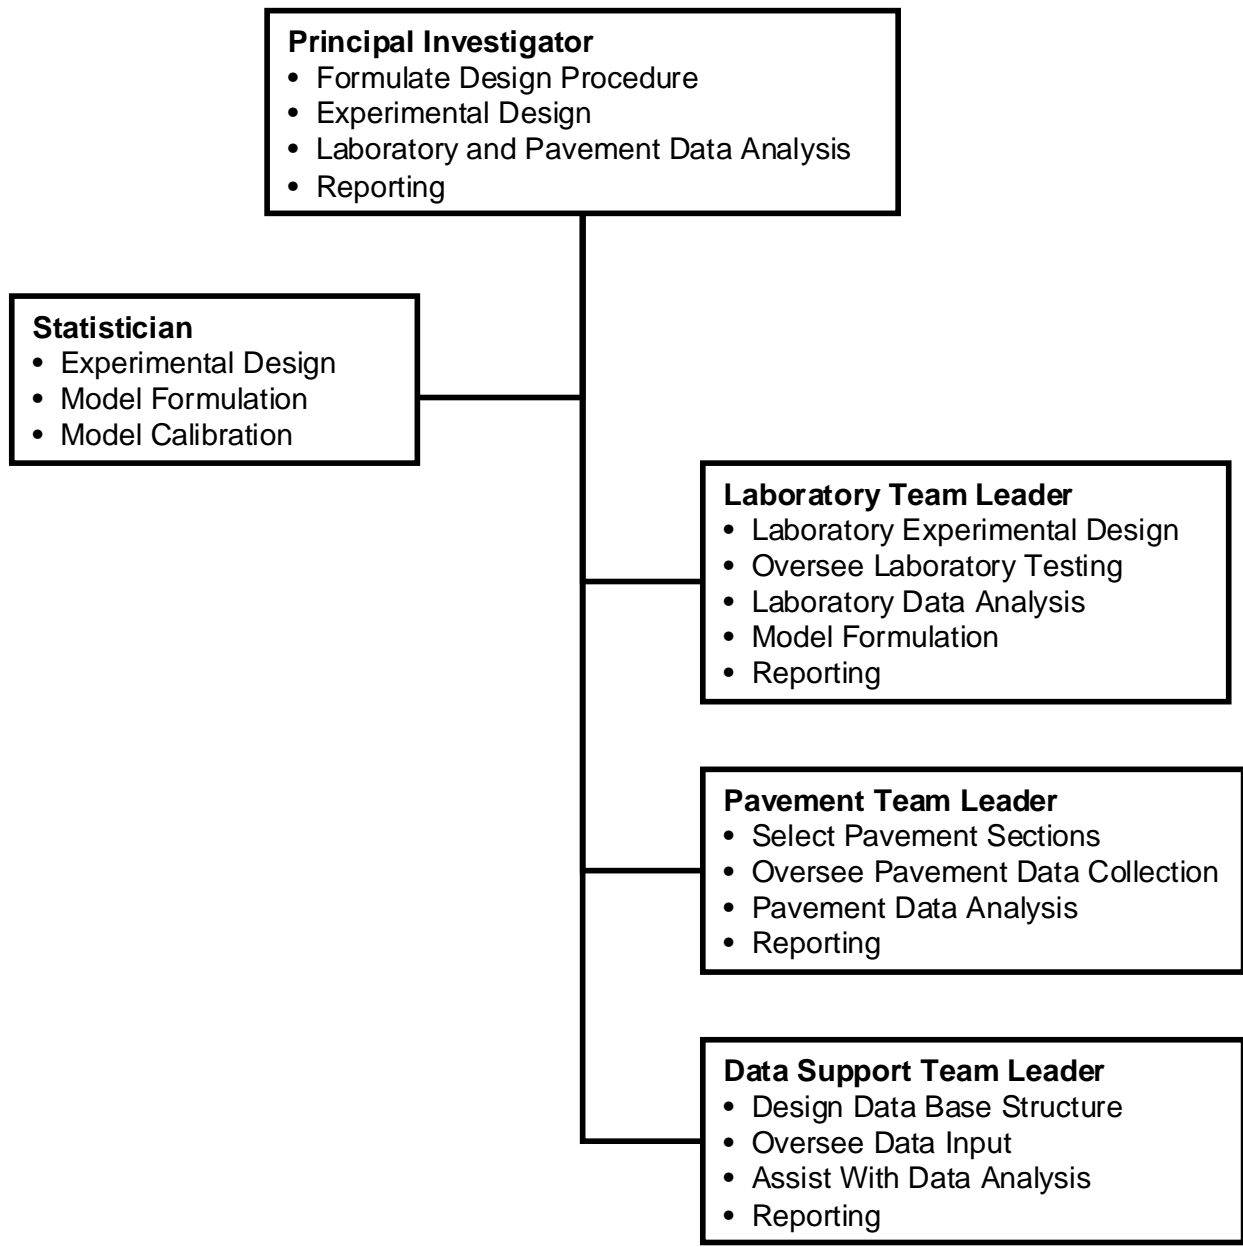


Figure 4. Recommended Research Management Structure.

Subtask A.2 Progress Reporting

NCHRP has specific requirements for progress reporting (13). The required reporting includes brief monthly progress reports and detailed quarterly progress reports. The monthly progress reports briefly summarize the work that has been completed, planned work, problems encountered, and expenditures for the project. The detailed quarterly progress reports describe completed work, planned work, and problems encountered in sufficient detail for review by the project panel during the course of the project. The quarterly progress reports are the means by which the project panel provides direction to the research team. Timely progress reporting and communication with the project panel are essential tools for effective project management.

Subtask A.3 Interim Reports and Presentations

The HMA Endurance Limit Validation Study includes a series of interim reports that coincide with the completion of five critical milestones:

- (1) Formulation of the preliminary design procedure and selection of the laboratory analysis approach,
- (2) Selection of pavement sections for analysis,
- (3) Completion of the laboratory studies,
- (4) Modification of the preliminary design procedure to reflect the findings from the laboratory studies and the analysis of accelerated pavement tests, and
- (5) Analysis of the calibration sections and preparation of the final design procedure.

Each interim report should be prepared in accordance with NCHRP requirements (14) and specifically address the work completed in the relevant tasks. These interim reports will provide more detailed information than normally contained in the progress reports. The final report will be compiled from the interim reports.

Presentations to the project panel are included after the second and fourth interim reports. The purpose of these presentations is to encourage a dialog between the project panel and the

Principal Investigator on the progress and direction of the work. One full day should be planned for each of these presentations sessions. Each session should include:

- (1) A presentation from the Principal Investigator focusing on the completed interim reports, planned work, and any changes to the direction of the research.
- (2) A discussion period where the project panel discusses critical aspects of the completed and planned work with the Principal Investigator and other key members of the research team.
- (3) Recommendations concerning the direction of the research.

Subtask A.4 Final Report and Presentation

The final report will document the entire project and will be compiled from the five interim reports. This report will be prepared in accordance with NCHRP requirements (14) and revised as required for publication. Upon completion of the review of the draft of the final report, the Principal Investigator will meet with the project panel to discuss the outcome of the project and to jointly develop recommendations concerning implementation and additional research activities.

Task A Milestones

Table 2 summarizes the major milestones for Task A. This milestone schedule assumes that this research plan as modified during the proposal process will serve as the work plan for the project. In addition to the major milestones listed in Table 2, meetings of the research management team will occur semi-monthly throughout the project, and monthly progress reports will be submitted as required by NCHRP.

Task A Labor Estimate

Table 3 presents the estimated labor required for Task 1. Table 3 presents estimated labor hours for each of the positions in the research management structure presented in Figure 5. Project management and reporting is estimated to require a total of 2014 man-hours of effort. This is approximately 16 percent of the total effort required for the project.

Table 2. Major Task A Milestones.

Milestone	Description	Months After Contract Award
A.1	Initial Work Assignments	0.5
A.2	First Quarterly Progress Report	3
A.3	Second Quarterly Progress Report	6
A.4	First Interim Report (Preliminary Design Procedure and Laboratory Analysis Approach)	7
A.5	Third Quarterly Progress Report	9
A.6	Fourth Quarterly Progress Report	12
A.7	Second Interim Report (Selection of Pavement Sections for Analysis)	13
A.8	First Panel Presentation (Interim Reports 1 and 2)	14
A.9	Fifth Quarterly Progress Report	15
A.10	Sixth Quarterly Progress Report	18
A.11	Seventh Quarterly Progress Report	21
A.12	Third Interim Report (Analysis of Laboratory Studies)	22
A.13	Eighth Quarterly Progress Report	24
A.14	Ninth Quarterly Progress Report	27
A.15	Tenth Quarterly Progress Report	30
A.16	Fourth Interim Report (Design Procedure Incorporating Findings From Laboratory Studies and Analysis of Accelerated Pavement Tests)	30
A.17	Second Panel Presentation (Interim Reports 3 and 4)	31
A.18	Eleventh Quarterly Progress Report	33
A.19	Twelfth Quarterly Progress Report	36
A.20	Thirteenth Quarterly Progress Report	39
A.21	Fifth Interim Report (Analysis of Validation Sections and Final Design Procedure)	42
A.22	Fourteenth Quarterly Progress Report	42
A.23	Submit Draft of Final Report	45
A.24	Fifteenth Quarterly Progress Report	45
A.25	Third Panel Presentation (Draft Final Report and Recommendations for Implementation and Additional Research)	46
A.26	Revised Final Report	48

Table 3. Estimated Labor Hours for Task A.

Subtask	Principal Investigator	Statistician	Laboratory Team Leader	Pavement Team Leader	Data Support Team Leader	Administrative Assistant
A.1 Project Management	112	0	104	104	104	40
A.2 Progress Reporting	120	0	30	30	30	20
A.3 Interim Reports and Presentations	432	0	116	116	116	80
A.4 Final Report and Presentation	216	0	68	68	68	40
Total	880	0	318	318	318	180

Task A Sources

Procedural Manual for Agencies Conducting Research in the National Cooperative Highway Research Program, Transportation Research Board, August, 2006.

Preparing Your CRP Final Report, Transportation Research Board, September, 2006

Task B. Formulate Design Procedure

In Task B, the procedure for designing pavements to resist bottom initiated fatigue cracking that considers the effects of an endurance limit for HMA will be developed. Task B will build on the preliminary procedure described in this research plan in four distinct steps:

1. Finalize preliminary procedure,
2. Incorporate findings from laboratory studies,
3. Modify approach based on analysis of accelerated pavement tests, and
4. Prepare final design procedure.

In step 1, the research team will become familiar with the preliminary procedure described in this research plan, and develop improvements based on their review of the relevant literature and research in progress. Then in steps 2, 3, and 4 information obtained from Tasks D and E of the project will be used to further improve the procedure. The final product will be a procedure for designing flexible pavements to resist bottom initiated fatigue cracking that accounts for the effects of an HMA endurance limit. This procedure will be compatible with current mechanistic-empirical flexible pavement design methods such as the MEPDG.

Preliminary Design Procedure

Background

A major part of the work completed during NCHRP 9-44 was the development of a preliminary procedure for designing pavements to resist bottom initiated fatigue cracking that considers the effects of an endurance limit. This preliminary procedure is based on the research hypothesis that the endurance limit for HMA is the result of a balance of damage caused by

loading and healing or damage recovery that occurs during rest periods. Under this hypothesis the primary objective in designing a flexible pavement to resist bottom initiated fatigue cracking will be to make sure that the damage induced by loading remains small enough so that healing occurs and there is no accumulation of damage over the life of the pavement. This is a significant departure from current cumulative or incremental damage models, which assume that no healing occurs and that each load cycle uses up a portion of the finite fatigue life of the HMA.

A number of approaches for designing pavements to resist bottom initiated fatigue cracking were reviewed during NCHRP Project 9-44. Table 4 briefly summarizes the approaches that were considered. These range from relatively simple modifications of traditional mechanistic-empirical fatigue algorithms to sophisticated finite element models based on damage mechanics and fracture mechanics. The major deficiency of the more practical approaches is that they do not account for the beneficial effects of healing. In the HMA Endurance Limit Workshop, healing was identified as a significant factor affecting the endurance limit in HMA (1). The sophisticated approaches can account for healing, but are not practical at this time for use in routine pavement design.

Effect of Rest Periods

An alternative approach was conceived during NCHRP Project 9-44 based on recent endurance limit research published by Carpenter and Shen (7). In this work, Carpenter and Shen clearly demonstrated the beneficial effects of rest periods on the fatigue life of HMA. Strain controlled flexural fatigue tests were conducted at 20 °C using a 10 Hz haversine load pulse with a rest period between each pulse to simulate the time between traffic loads. The rest periods ranged from 0 sec (continuous loading) to 9 seconds. Two 19 mm mixtures, one with a neat PG 64-22 binder and one with a polymer modified PG 70-22 binder, were tested. The gradation, binder content and air void content of the two mixtures was the same.

Table 4. Summary of Existing Pavement Analysis Approaches Considered.

Approach	Key Elements	Selected References	Advantages	Disadvantages
Strain Limit	Assume fatigue life is infinite at damage levels below the endurance limit. Use Miner's law for strain levels above the endurance limit.	Timm and Young (15) Witczak (16) Thompson and Carpenter (17)	Easy to implement in existing M-E design. Compatible with layered elastic analysis used in MEPDG.	Does not consider the beneficial effect of rest periods. Relies on Miners law for strains above the endurance limit. Above endurance limit fatigue life of HMA is predefined.
Crack Initiation	Limit strain level to that causing crack initiation in laboratory fatigue tests.	Sidess and Uzan (18)	Easy to implement in existing M-E design. Compatible with layered elastic analysis used in MEPDG. Rational basis for design.	Does not consider the beneficial effect of rest periods. Relies on Miners law. Cycles to crack initiation are predefined.
Strain Limit-Crack Initiation	Assume fatigue life is infinite at damage levels below the endurance limit. Use Miner's law for strain levels above the endurance limit. The endurance limit is estimated from the indirect tensile strength test and is dependent on the modulus of the mixture.	Von Quintus (19, 20)	Relatively easy to implement in existing M-E based methods. Compatible with layered elastic analysis used in the MEPDG. Value is dependent on the temperature (modulus), and volumetric properties of the mixture.	Does not consider the beneficial effect of rest periods. Relies on Miner's law for strains above the endurance limit. Key property used to estimate endurance limit is highly variable.
Recursive Miner's Law	Modify fatigue life of HMA to account for the strength loss of a pavement structure as a function of traffic loading.	Tsai, et. al., (21)	Easy to implement in existing M-E design. Compatible with layered elastic analysis used in MEPDG. Accounts for changes in fatigue life of HMA with traffic.	Assumes that HMA fatigue life deteriorates with traffic loading. Does not consider the beneficial effect of rest periods.
Visco-Elastic Continuum Damage	Model the evolution of damage in a viscoelastic continuum.	Mun, et. al., (22)	Can be used to predict crack initiation. Directly accounts for damage accumulation and healing.	Computationally intensive. Not compatible with layered elastic analysis used in MEPDG.
Fracture Mechanics	Model responses at the crack tip and the propagation of cracks.	Roque, et. al. (23)	Predict crack growth.	Requires crack initiation model. Computationally intensive. Not compatible with layered elastic analysis used in MEPDG.

The resulting data were analyzed using the ratio of dissipated energy change (RDEC) approach developed at the University of Illinois (5). In this approach, the ratio of dissipated energy change reaches a plateau value (PV) where a constant percentage of the input energy is being converted to damage. The University of Illinois research found a unique relationship between the plateau value and the traditional definition of failure in flexural fatigue tests, 50 percent stiffness reduction, that holds for a range of mixtures and loading conditions (5).

$$PV = 0.4429 \times (N_f)^{-1.1102} \quad (1)$$

where:

PV = plateau value

N_f = number of cycles to 50 percent stiffness reduction

Lower plateau values correspond to longer fatigue lives. Based on the ratio of dissipated energy change approach, an HMA mixture will exhibit endurance limit behavior when the plateau value is 6.74×10^{-9} or less, which based on Equation 1 corresponds to a traditional fatigue life of 1.1×10^7 cycles or greater.

The effect of rest periods on the plateau value is shown in Figure 6 for the two mixtures that were tested. Equations 2 and 3 present the relationship between plateau value and the length of the rest period that were developed for the neat PG 64-22 and the modified PG 70-22 mixtures, respectively for a strain level of 500 μ strain (7).


$$\text{For neat PG 64-22} \quad PV = 1.018 \times 10^{-5} (RP + 1)^{-0.9069} \quad (2)$$

$$\text{For modified PG 70-22} \quad PV = 4.353 \times 10^{-6} (RP + 1)^{-1.352} \quad (3)$$


where:

PV = plateau value

RP = duration of intermittent rest period, sec

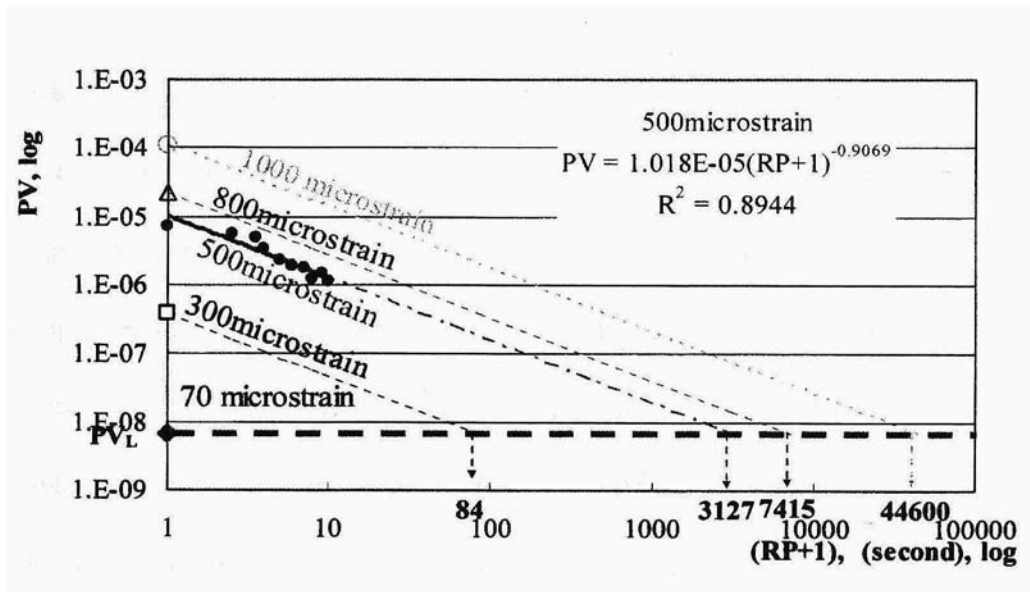

a. Neat PG 64-22

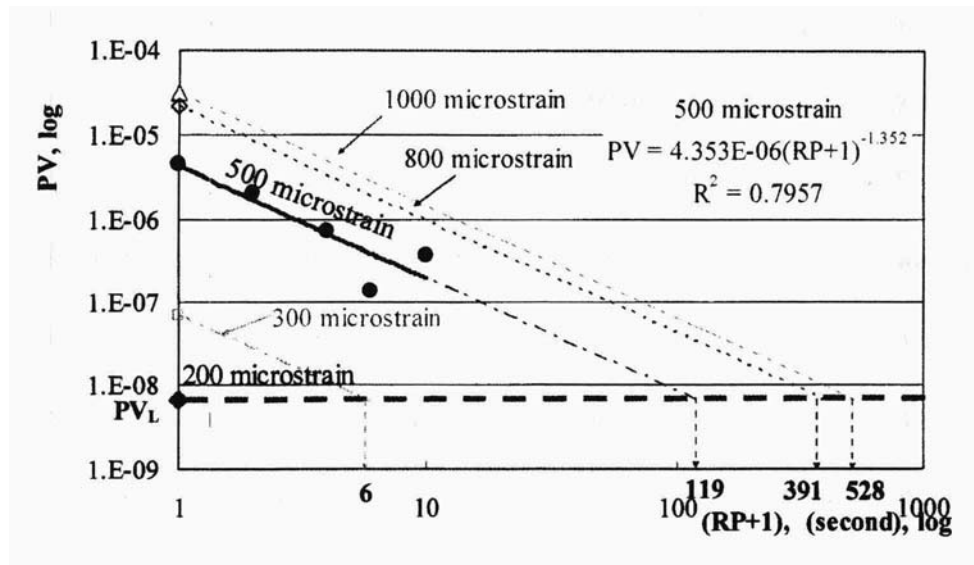

b. Polymer PG 70-22

Figure 5. Effect of Rest Periods on Plateau Value (5).

The decreasing plateau values for tests with rest periods result in increasing fatigue lives. This can be quantified by substituting plateau values from Equations 2 or 3 into Equation 1. The results are summarized in Table 5. Figure 7 shows the beneficial effect of the rest periods on the fatigue lives for the two mixtures. There is a substantial improvement in the fatigue life of both mixtures. The values for the neat PG 64-22 mixture are of similar magnitude to improvements previously reported by Bonnaure, et. al. (24). The effect of rest periods on the modified PG 70-22 mixture is much more pronounced.

Table 5. Effect of Rest Period on Fatigue Life.

Rest Period, sec	Neat PG 64-22			Modified PG 70-22		
	PV	N _f	Ratio	PV	N _f	Ratio
0	1.02E-05	1.51E+04	1.00	4.35E-06	3.24E+04	1.00
1	5.43E-06	2.65E+04	1.76	1.71E-06	7.53E+04	2.33
2	3.76E-06	3.70E+04	2.45	9.86E-07	1.23E+05	3.81
3	2.90E-06	4.68E+04	3.10	6.68E-07	1.75E+05	5.41
4	2.37E-06	5.61E+04	3.72	4.94E-07	2.30E+05	7.10
5	2.00E-06	6.51E+04	4.32	3.86E-07	2.87E+05	8.86
6	1.74E-06	7.39E+04	4.90	3.13E-07	3.46E+05	10.69
7	1.54E-06	8.24E+04	5.47	2.62E-07	4.08E+05	12.58
8	1.39E-06	9.07E+04	6.02	2.23E-07	4.70E+05	14.52
9	1.26E-06	9.89E+04	6.56	1.94E-07	5.35E+05	16.51
10	1.16E-06	1.07E+05	7.09	1.70E-07	6.01E+05	18.54

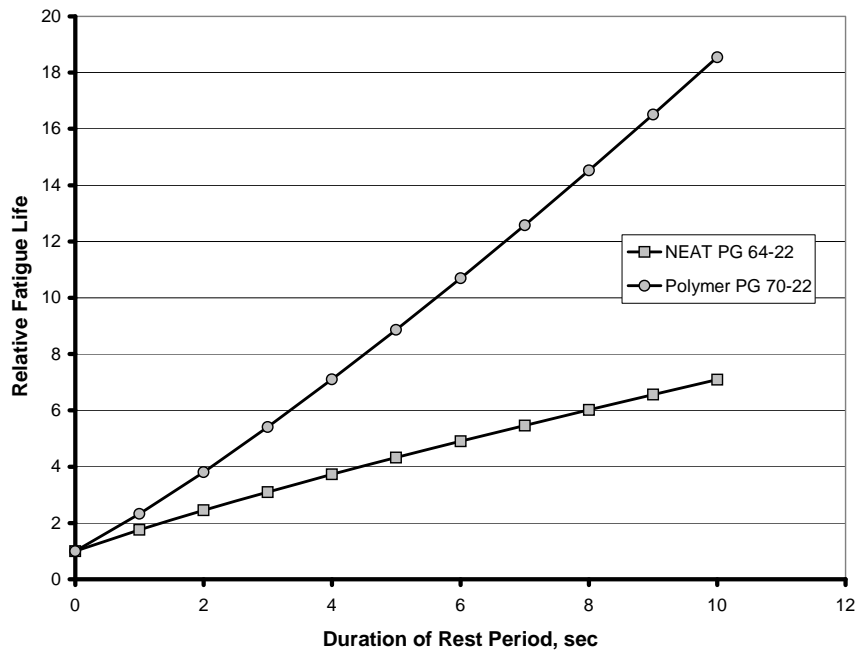


Figure 6. Effect of Rest Period on Fatigue Life.

An estimate of approximate rest periods can be obtained from the 20 year design traffic level typically used in mixture design. Table 6 summarizes rest periods for various design traffic levels. The rest period for a 20 year design traffic level of 100 million ESAL is approximately 6 sec., which results in a factor of 5 improvement in the fatigue life of the mixture with the neat PG 64-22 binder and a factor of 10 improvement for the polymer modified PG 70-22 mixture.

Table 6. Approximate Rest Periods for Various Design Traffic Levels.

20 Year Design ESAL	ESAL/Day	ESAL/sec	Rest Period, sec
1.00E+05	13.7	0.0002	6307.2
3.00E+05	41.1	0.0005	2102.4
1.00E+06	137.0	0.0016	630.7
3.00E+06	411.0	0.0048	210.2
1.00E+07	1369.9	0.0159	63.1
3.00E+07	4109.6	0.0476	21.0
1.00E+08	13698.6	0.1585	6.3
3.00E+08	41095.9	0.4756	2.1

Allowable Strains

Continuous loading tests at different strain levels were also conducted by Carpenter and Shen on the two mixtures and the plateau values are shown in Figure 6 for a rest period of zero (RP+1=1) (7). From these data relationships between the plateau value for continuous loading and the applied strain level can be developed as shown in Figure 8. These relationships are given in Equations 4 and 5 for the neat PG 64-22 mixture and the polymer modified PG 70-22 mixture.

$$\text{For neat PG 64-22} \quad PV_0 = 9.142 \times 10^{-16} (\varepsilon)^{3.617} \quad (4)$$

$$\text{For modified PG 70-22} \quad PV_0 = 5.347 \times 10^{-21} (\varepsilon)^{5.331} \quad (5)$$

where:

PV_0 = plateau value for continuous loading

ε = tensile strain, μ strain

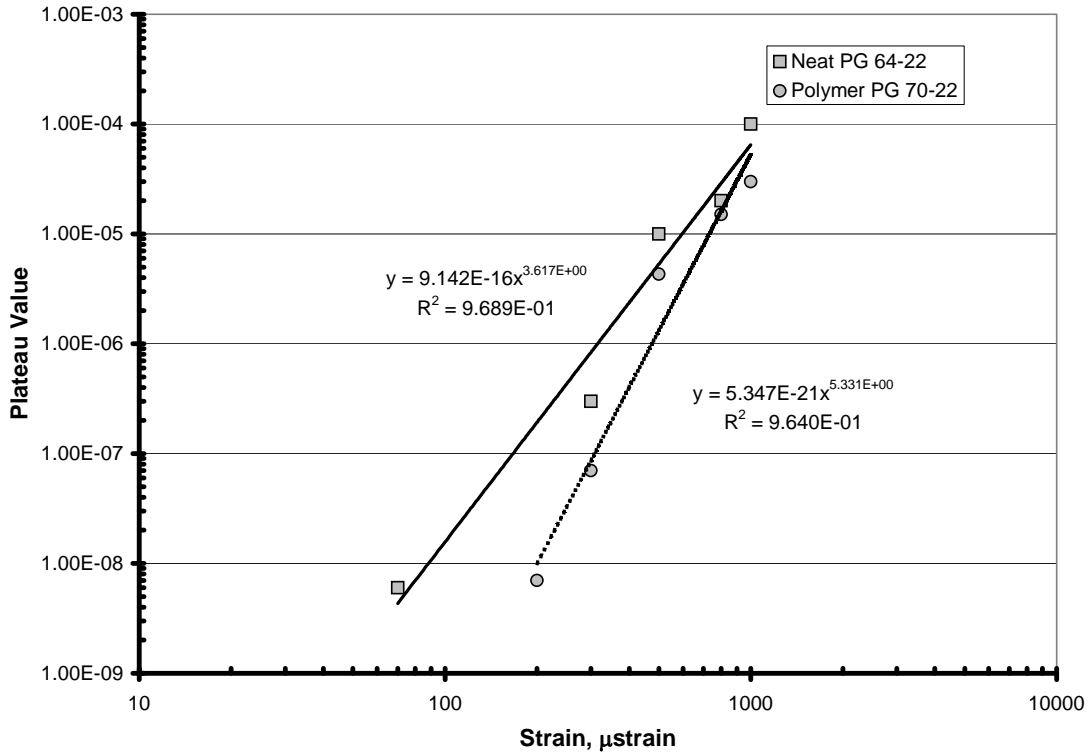


Figure 7. Plateau Value for Continuous Loading as a Function of Applied Strain Level.

Based on previous work by Bonnaure (24), it is reasonable to assume that the effect of the rest periods is the same at each strain level. Substituting Equations 4 and 5 for the constants 1.018×10^{-5} and 4.353×10^{-6} in Equations 2 and 3 respectively, yield the following relationships between the plateau value, applied strain and rest period for the two mixtures.

$$\text{For neat PG 64-22} \quad PV = 9.142 \times 10^{-16} (\varepsilon)^{3.617} (RP + 1)^{-0.9069} \quad (6)$$

$$\text{For modified PG 70-22} \quad PV = 5.347 \times 10^{-21} (\varepsilon)^{5.331} (RP + 1)^{-1.352} \quad (7)$$

where:

PV = plateau value

ε = tensile strain, μstrain

RP = duration of intermittent rest period, sec

Equations 6 and 7 can then be substituted into Equation 1 and solved for the allowable strain level to produce a selected mixture fatigue life.

$$\text{For neat PG 64-22} \quad \varepsilon_a = 11483.32 \left[\frac{(1 + RP)^{0.2507}}{(N_f)^{0.3069}} \right] \quad (8)$$

$$\text{For modified PG 70 -22} \quad \varepsilon_a = 5448.74 \left[\frac{(1 + RP)^{0.2536}}{(N_f)^{0.2082}} \right] \quad (9)$$

where:

ε_a = allowable tensile strain, μ strain

RP = duration of intermittent rest period, sec

N_f = number of cycles to failure

Recalling that endurance limit behavior occurs when the number of cycles to failure exceeds 1.1×10^7 , then setting the number of cycles to failure in Equations 8 and 9 to a value above 1.1×10^7 will ensure that full healing occurs at the selected rest period. Conservatively using 2.0×10^7 as the number of cycles to failure yields Equations 10 and 11, which give allowable strain levels as a function of rest period to ensure that full healing occurs.

$$\text{For neat PG 64-22} \quad \varepsilon_{af} = 66.0(1 + RP)^{0.2507} \quad (10)$$

$$\text{For modified PG 70-22} \quad \varepsilon_{af} = 164.5(1 + RP)^{0.2536} \quad (11)$$

where:

ε_{af} = allowable tensile strain for full healing, μ strain

RP = duration of intermittent rest period, sec

If the strains in a pavement at 20 °C are kept below the values given by Equations 10 and 11, then complete healing will occur during intermittent rest periods, and the pavement will exhibit endurance limit behavior. Table 7 summarizes these strain levels for various 20 year design traffic levels.

Table 7. Allowable Strains for Various Design Traffic Levels.

20 Year Design ESAL	Rest Period, sec	Allowable Strains, μ strain	
		Neat PG 64-22	Modified PG 70-22
1.00E+05	6307.2	592	1513
3.00E+05	2102.4	449	1145
1.00E+06	630.7	332	844
3.00E+06	210.2	253	639
1.00E+07	63.1	187	472
3.00E+07	21.0	143	360
1.00E+08	6.3	109	272
3.00E+08	2.1	88	219

Multiple Temperatures

The allowable strains presented in the previous section were developed from test data obtained at 20 °C. To be useful in a pavement design procedure, the allowable strains for a wide range of temperatures must be available. In this procedure the major concern is the effect of temperature on the healing properties of the mixture. Previous research by Bonnaure, et al. (24) concluded that the beneficial effect of rest periods increased with increasing temperature. Since healing can be envisioned as a type of flow phenomenon where the binder flows together to repair microcracks, it has been hypothesized that the effect of healing at multiple temperatures can be accounted for using time-temperature superposition. By applying time-temperature superposition, rest periods at different temperatures can be reduced to an equivalent rest period at 20 °C. The reduced rest period for temperatures above 20 °C will be longer than the actual rest period, while those for temperatures below 20 °C will be shorter than the actual rest period. Research conducted in NCHRP Project 9-19 showed that linear, viscoelastic time-temperature shift factors obtained from dynamic modulus tests could be applied when a high level of nonlinear damage is present (25). Equation 12 presents the application of time-temperature superposition to the duration of the rest period.

$$\log(RP_R) = \log(RP) - \log(A_T) \quad (12)$$

where:

RP_R = duration of the rest period at the reference temperature, sec

RP = actual duration of the rest period, sec

A_T = linear viscoelastic time temperature shift factor obtained from dynamic modulus testing.

Figure 9 illustrates the use of time-temperature superposition for rest periods at temperatures of 40, 20, and 4 °C using 20° C as the reference temperature. In developing Figure 9, typical time-temperature shift factors were used ($\log(A_T)$ for 4 °C = 2.0 and $\log(A_T)$ for 40 °C = -2.2).

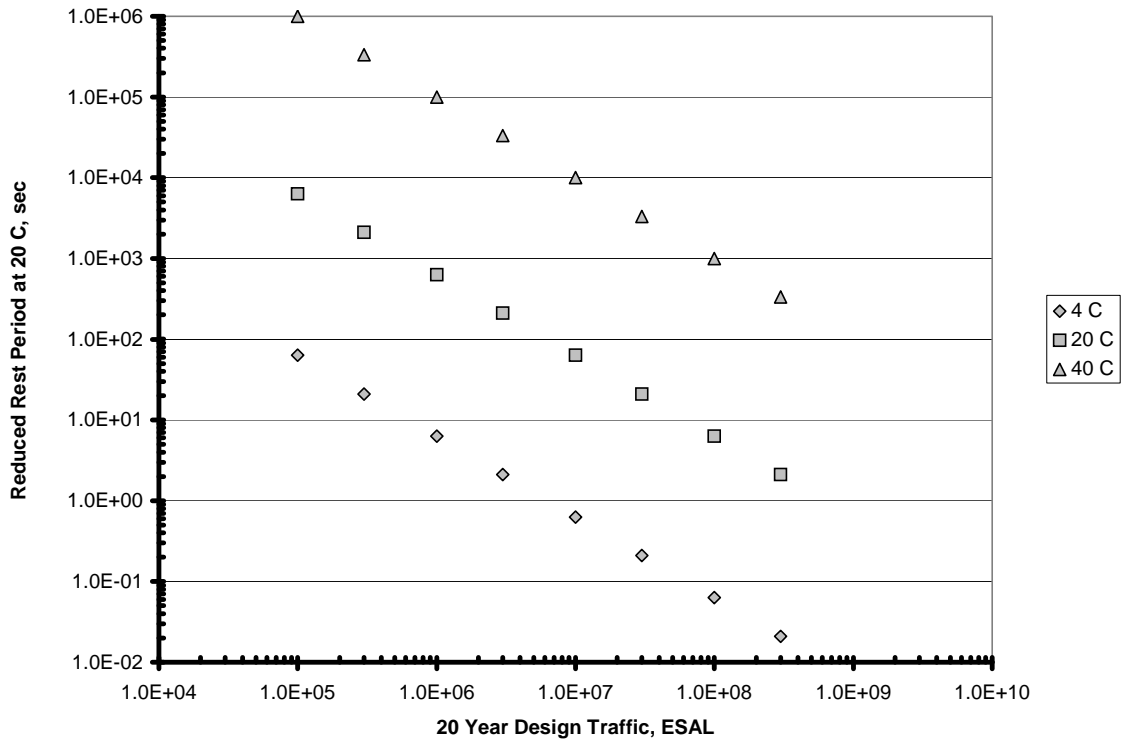


Figure 8. Application of Time-Temperature Superposition to Rest Periods.

Design Example

This section illustrates how the proposed methodology would be used in a mechanistic-empirical design system such as the MEPDG. To limit the number of computations, a monthly analysis is illustrated using typical pavement temperatures estimated from mean monthly air temperature data from Reagan National Airport in Washington, DC. The pavement being analyzed is 9 in of HMA constructed on a 6 in aggregate subbase base layer and a silty clay subgrade. The 20 year design traffic level is 1×10^8 ESALs, and the design traffic speed is 45 mph. The purpose of the analysis is to determine if the pavement section is sufficiently thick to

resist bottom initiated fatigue cracking assuming the fatigue properties of the neat PG 64-22 mixture discussed in the preceding section.

Material Properties

For this analysis the modulus of the subgrade is assumed to be 4,500 psi and constant throughout the year. The modulus of the aggregate subbase is assumed to be 25,000 psi and is also assumed constant throughout the year. Dynamic modulus testing of a typical 19 mm mixture with PG 64-22 binder using the Simple Performance Test System yielded the master curve and shift factors given in Equations 13 and 14 for a reference temperature of 20 °C. The allowable strains for full healing are given in Equation 15.

$$\log|E^*| = 0.234 + \left[\frac{3.259}{\left(1 + e^{-1.213 - 0.499 \log(f_r)}\right)} \right] \quad (13)$$

$$\log f_r = \log f + 10448.2 \left(\frac{1}{T} - \frac{1}{293.2} \right) \quad (14)$$

$$\varepsilon_{af} = 66.0(1 + RP_r)^{0.2507} \quad (15)$$

where:

$|E^*|$ = dynamic modulus, ksi

f = loading frequency, Hz

f_r = reduced frequency, Hz

T = temperature, °K

ε_{af} = allowable tensile strain of full healing, μ strain

RP_r = reduced rest period at 20 °C, sec

Allowable Strains

Allowable strains at the bottom of the asphalt layer are determined from Equation 15 using reduced rest periods that depend on the traffic volume and the monthly pavement temperature.

Mean monthly pavement temperatures can be estimated from the mean monthly air temperature using Equation 16 (26).

$$M_p = M_a \left(1 + \frac{1}{z+4} \right) - \frac{34}{z+4} + 6 \quad (16)$$

where:

M_p = mean monthly pavement temperature at depth z , °F

M_a = mean monthly air temperature, °F

z = depth, in

For a 20 year design traffic of 1×10^8 ESAL, the rest period is 6.3 sec. The reduced rest period for each month is determined from Equation 12 using the shift factors from the dynamic modulus master curve and the mean monthly pavement temperature. Table 8 summarizes the computation of the allowable strains. Because the reduced rest period is much shorter during cold months compared to warm months, the allowable strain levels for full healing are significantly lower.

Table 8. Computation of Allowable Strain Strains.

Month	Mean Monthly Pavement Temp, C	Log (A_T)	Rest Period, sec	Reduced Rest Period, sec	Allowable Strain Level, μ strain
Jan	5.5	1.851	6.3	0.09	67
Feb	7.3	1.611	6.3	0.15	68
Mar	12.2	0.971	6.3	0.67	75
Apr	18.0	0.242	6.3	3.61	97
May	23.7	-0.445	6.3	17.56	137
Jun	29.0	-1.065	6.3	73.20	194
Jul	32.0	-1.397	6.3	157.26	235
Aug	30.9	-1.276	6.3	118.95	219
Sep	26.8	-0.803	6.3	40.04	167
Oct	19.7	0.036	6.3	5.79	107
Nov	13.8	0.773	6.3	1.06	79
Dec	8.4	1.469	6.3	0.21	69

Applied Strains

The strains applied by the traffic loading are computed for the design axle load using layered elastic analysis. In this example an 18 kip single axle load was used for computing applied strains. For this example the modulus of the subgrade and subbase are constant at 4.5 and 25 ksi, respectively. The modulus of the asphalt depends on the pavement temperature and the speed of traffic. Recent research by Al-Qadi, et. al, using in-situ instrumentation at the Virginia Smart Road (27) indicates that loading rates computed by the transformed section analysis in the MEPDG and other approaches such as that recommended by Barksdale (28) overestimate the frequency of the load pulse. Based on data presented by Al-Qadi, a loading rate of 16 Hz appears reasonable for a depth of 9 in under 45 mph traffic. Table 10 summarizes the applied strains for each month computed using the KENLAYER software (26). The applied strains are compared to the allowable strains in Figure 10. Since the applied strains in Table 9 are less than the allowable strains, the proposed section is acceptable with respect to bottom initiated fatigue cracking. An interesting observation in Figure 10 is that this analysis shows that the critical condition for bottom initiated fatigue cracking occurs at intermediate to low pavement temperatures, which is in contrast with traditional cumulative or incremental damage analyses, which show that the majority of the fatigue damage occurs at high pavement temperatures.

Table 9. Applied Strains for Design Example.

Month	Mean Monthly Pavement Temp, C	Log (A _T)	Load Frequency, Hz	Reduced Frequency, Hz	AC Modulus, ksi	Subbase Modulus, ksi	Subgrade Modulus, ksi	Applied Strain, μ strain
Jan	5.6	1.841	16	1108.93	1969.7	25	4.5	51
Feb	7.5	1.584	16	614.01	1858.0	25	4.5	54
Mar	12.8	0.900	16	127.08	1535.8	25	4.5	62
Apr	19.0	0.122	16	21.21	1148.4	25	4.5	77
May	25.1	-0.608	16	3.95	801.7	25	4.5	100
Jun	30.8	-1.265	16	0.87	535.6	25	4.5	133
Jul	33.9	-1.616	16	0.39	418.2	25	4.5	157
Aug	32.8	-1.488	16	0.52	458.9	25	4.5	148
Sep	28.4	-0.987	16	1.65	641.1	25	4.5	117
Oct	20.8	-0.096	16	12.83	1041.1	25	4.5	83
Nov	14.4	0.688	16	78.05	1431.1	25	4.5	65
Dec	8.7	1.432	16	432.33	1789.1	25	4.5	55

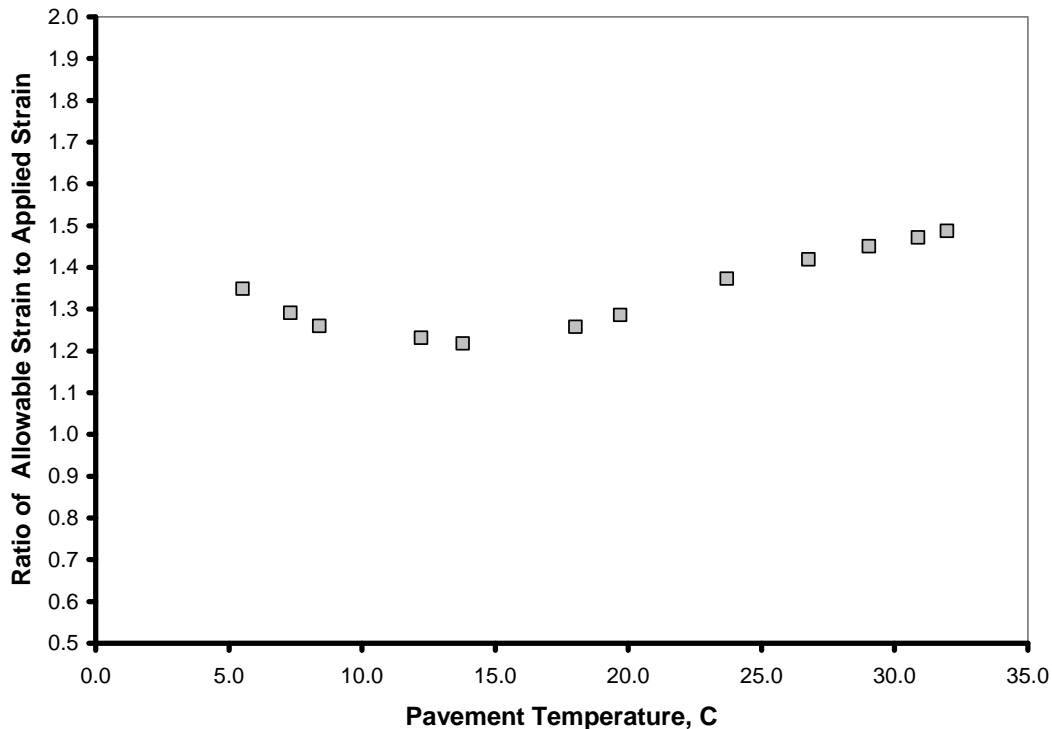


Figure 9. Comparison of Applied and Allowable Strains.

Traffic Level

The analysis presented above can be performed to determine minimum asphalt thicknesses to resist bottom initiated fatigue cracking for the given subgrade and subbase conditions as a function of traffic level. The results are shown in Figure 11 for a 22 kip single axle load. A 22 kip axle load was used to allow comparison with observed data from the analysis of in-service pavements that was conducted in the United Kingdom (9). Figure 11 also shows the thickness and accumulated traffic for the four pavements that were analyzed in detail and it was documented that bottom initiated fatigue cracking had not occurred. This comparison shows the engineering reasonableness of the proposed approach. It is reasonable to expect that when the proposed approach is improved to consider the effects of aging and design reliability, the minimum asphalt thicknesses will increase. It is important to note that at the low traffic levels, deformation of the subgrade may govern the analysis rather than bottom initiated fatigue cracking. Research in the United Kingdom indicates that for asphalt thicknesses less than about 7 in subgrade deformation governs the performance of the pavement (9). This limit is shown as the dashed line in Figure 11.

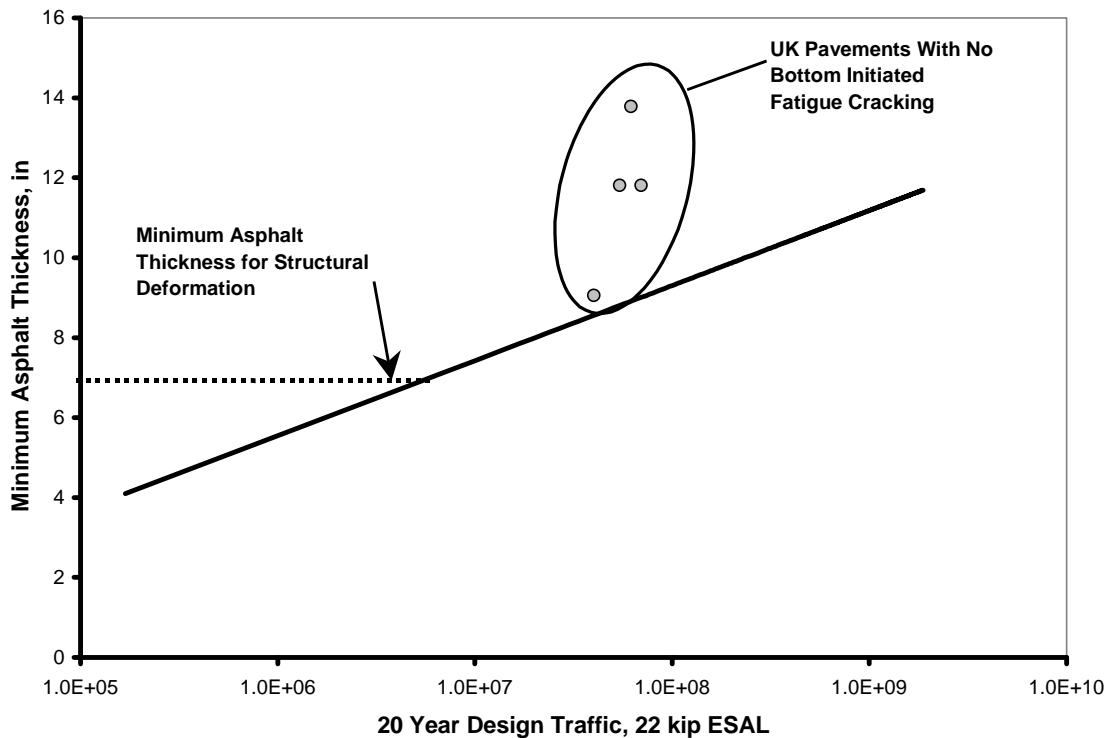


Figure 10. Example of Minimum Asphalt Thicknesses to Resist Bottom Initiated Fatigue Cracking With Observed Performance of Four UK Pavement Sections.

Aging

The example presented above does not consider the important effect of aging on either the applied or allowable strains. As a pavement ages, the modulus of the HMA will increase due to the increased stiffness of the asphalt binder resulting in lower applied strains. Aging will also affect the healing rate for the HMA. Although no data is currently available for the effect of aging on the healing rate, it is reasonable to expect that the healing rate will decrease significantly on aging resulting in lower allowable strains for full healing. Early research on healing by Bonnaure, et. al (24) showed that healing rates were much greater in softer binders. The effect of aging can be incorporated in the procedure outlined above, by computing allowable and applied strains as a function of pavement age. The global aging model currently incorporated in the MEPDG provides a method for computing aged modulus values (29). Additional research proposed in the laboratory studies discussed in Task D will be required to develop a model of the effect of aging on HMA healing and the allowable strains that result in

full healing. For perpetual pavement design, it may only be necessary to perform the analysis for highly aged conditions.

Climate and Mixed Traffic Effects

The MEPDG currently provides excellent capabilities to evaluate the effects of climate and mixed traffic on the applied strains at the bottom of the asphalt layer. This capability can be used with the allowable strains described above to determine the HMA thickness needed to resist bottom initiated fatigue cracking.

Reliability

Because the computations involved in the analysis do not require substantial computer time, reliability can be included in the analysis using Monte-Carlo simulation. This approach has already been implemented in the PerRoad program (15). In fact, the allowable strains computed based on rest periods can be input as the threshold criteria for HMA the in the PerRoad program and the analysis for a single season can be performed.

Subtask B.1 Review Selected Literature

The preceding section presented a rational approach for incorporating an endurance limit for bottom initiated fatigue cracking in mechanistic-empirical pavement design methods. The method is based on maintaining tensile strain levels at the bottom of the HMA low enough to ensure that complete healing occurs between traffic loads and that there is no accumulation of damage at the bottom of the asphalt concrete. This is accomplished through the use of allowable strain levels that depend on the damage and healing properties of the HMA, the aging characteristics of the HMA, the duration of rest periods between traffic loads, and the temperature of the pavement. Several improvements to this preliminary procedure should be made based on a detailed review of selected literature. These improvements should be made before the detailed laboratory testing plans are developed in Task D. Areas where improvements should be considered are summarized below:

Duration of Rest Periods. In the preliminary procedure a very simple approach was used to estimate the duration of rest periods as a function of design traffic level.

Additional effort should be expended to establish representative rest period durations as a function of traffic level and roadway classification. Potential sources of information on the duration of rest periods include: the Highway Capacity Manual (30), data from traffic studies performed for the Long Term Pavement Performance Program (31), and the approach used in Strategic Highway Research Program (SHRP) Contract 005 (32).

MEPDG Modifications. It is envisioned that the design procedure will be implemented in the MEPDG. Because the MEPDG is an AASHTO product, any proposed changes, including research versions of the software, must be approved by AASHTO. AASHTO has approved a research version of the software for use in NCHRP 9-30A. It is envisioned that similar approval will be granted for this project.

A detailed review of the documentation and source code for the MEPDG will be required to determine specific modifications that will be needed to implement the approach. This review should concentrate on how the MEDPG addresses the following:

1. Climatic effects,
2. Mixed traffic (Currently hourly traffic distribution factors are not included in any flexible pavement analysis, they are only considered for the rigid pavement analysis. It may be necessary to tie daily truck traffic distributions to temperature distributions to accurately consider the effect of healing),
3. Vehicle speed effects,
4. Vehicle wander (Currently being considered for revision under NCHRP Project 9-30A),
5. Location of maximum strain at the bottom of the asphalt layer for various axle configurations,
6. Aging, and
7. Reliability.

The MEPDG source code should also be reviewed to determine how to remove the current bottom initiated fatigue cracking algorithm and implement the allowable strain approach.

Since the major new component of the design procedure is the determination of allowable strain levels that provide for complete healing between traffic loads, completed research on healing in HMA should be reviewed before finalizing the laboratory testing program. Several important publications addressing healing in HMA that should be reviewed are listed at the end of the Task 2 work description.

Subtask B.2 Finalize Preliminary Approach

In this Subtask, the preliminary design procedure described in this research plan will be improved based on the findings from the literature review conducted in Subtask B.1. The improved procedure will then be implemented in a research version of the MEPDG software, designated NCHRP9-44A_Version 0.1. The products of this subtask will be detailed documentation of the preliminary procedure and a modified research version of the MEPDG software. The documentation and software will be submitted as part of the first interim report that is scheduled for delivery during the 7th month of the project.

Subtask B.3 Incorporate Findings from Laboratory Studies

In Subtask B.3, the preliminary procedure and software developed in Subtask B.2 will be improved by adding the results from the laboratory studies conducted in Task D. The laboratory studies are envisioned to result in the following improvements:

1. Verification that time-temperature superposition can be applied to HMA rest periods. This is an assumption that has been included in the preliminary procedure described in this research plan.
2. Verification that healing in HMA is not affected by the strain level provided the strains are low enough that macrocracking does not occur.
3. Testing and data analysis procedures for determining mixture specific allowable strains levels for HMA. Under the current hierarchical structure of the MEPDG, this testing and analysis will be used in Level 1 analyses.

4. A model for estimating allowable strain levels as a function of mixture composition, binder properties, and age. This model will be used for Level 2 and Level 3 analyses, and for the analysis of pavement sections to be completed in Task E. Von Quintus (19, 20) developed a model to estimate the allowable strain levels at which no damage is retained in the HMA mixtures. It is estimated from the indirect tensile strength test, and is dependent on the mixture composition. Healing within this approach is captured through field calibration factors. A similar type of approach is expected for this research plan, but using healing directly.

The products of this subtask will be detailed documentation of the improved procedure and a modified research version of the MEPDG software designated NCHRP9-44A_Version 0.2 that will be used in Subtask E.3 for the analysis of selected accelerated pavement test and test road sections. This documentation and software will be further improved in Subtask B.4.

Subtask B.4 Modify Approach Based on Analysis of Accelerated Pavement Tests

In Subtask B.4, the improved procedure developed in Subtask B.3 will be further improved based on the analysis of selected accelerated pavement test and test road sections. The accelerated pavement test and test road sections will be selected in Subtask E.1 to exercise critical aspects of the design procedure. For example, the fatigue tests conducted at the FHWA Pavement Testing Facility provide data addressing the effect of temperature on HMA fatigue and healing. These field tests provide the ability to investigate time-temperature superposition as applied to rest periods. The structural sections from the NCAT test track provide data addressing the effect of thickness on HMA fatigue, while the WesTrack sections provide data on the effect of HMA material properties on fatigue. In all three cases, the applied strains should exceed the allowable strains for full healing. On the other hand, the original sections from the NCAT test track that are still in-service, should have applied strains that are below the allowable strains for full healing.

The products of this subtask will be detailed documentation of the improved procedure and a modified research version of the MEPDG software designated NCHRP9-44A_Version 0.3 that will be used in Subtask E.5 for the analysis of selected in-service pavement test sections. The

documentation and software will be submitted as part of the fourth interim report that is scheduled for delivery during the 30th month of the project.

Subtask B.5 Prepare Final Design Procedure

The final subtask in Task 2 is the preparation of the final design procedure. This will be accomplished after analysis of the in-service pavement calibration sections is completed in Subtask E.5. It is envisioned that design reliability will be the primary effort addressed in this final version of the design procedure.

The products of Subtask B.5 will be detailed documentation of the final procedure and a modified research version of the MEPDG software designated NCHRP9-44A_Version 1.0. The documentation and software will be submitted as part of the draft final report that is scheduled for delivery during the 45th month of the project.

Task B Milestones

Table 10 summarizes the major milestones for Task B. These are all associated with improvements to the preliminary design procedure described in this research plan, and the development of various modified research versions of the MEPDG software.

Table 10. Major Task B Milestones.

Milestone	Description	Months After Contract Award
B.1	Review Selected Literature	3
B.2	Preliminary Approach and NCHRP 944A_Version 0.1 Software	6
B.3	Incorporate Findings from Laboratory Studies into NCHRP 9-44A_Version 0.2 Software	27
B.4	Modify Approach Based on Analysis of Selected Accelerated Pavement Tests and NCHRP 9-44A_Version 0.3 Software	29
B.5	Prepare Final Design Procedure and NCHRP 9-44A_Version 1.0 Software	41

Task B Labor Estimate

Table 11 presents the estimated labor required for Task B. Table 11 presents estimated labor hours for each of the positions in the research management structure presented in Figure 5 and for programming assistance. Task 2 is estimated to require a total of 1240 man-hours of effort. This is approximately 10 percent of the total effort required for the project.

Table 11. Estimated Labor Hours for Task B.

Subtask	Principal Investigator	Statistician	Laboratory Team Leader	Pavement Team Leader	Data Support Team Leader	Programmer
Review Selected Literature	80	0	80	80	0	160
Finalize Preliminary Approach	40	0	20	20	0	160
Incorporate Findings from Laboratory Studies	40	0	40	0	0	160
Modify Approach Based on Analysis of Accelerated Pavement Tests	40	0	0	40	0	80
Prepare Final Design Procedure	80	0	20	20	0	80
Total	280	0	160	160	0	640

Task B Sources

Endurance Limit Studies

Carpenter, S.H., Ghuzlan, K.A., and Shen, S., “Fatigue Endurance Limit for Highway and Airport Pavements,” **Transportation Research Record No. 1832**, Transportation Research Board, Washington, D.C., 2003.

Carpenter, S.H., and Shen, S., “Application of the Dissipated Energy Concept in Fatigue Endurance Limit Testing,” **Transportation Research Record No. 1929**, Transportation Research Board, Washington, D.C., 2005.

Prowell, B., Brown, E., R., Daniel, J., Bhattacharjee, S., Von Quintus, H., Carpenter, S., Shen, S., Anderson, M., Swamy, A. K., and Maghsoodloo, S., “Endurance Limit of Hot Mix Asphalt Mixtures to Prevent Fatigue Cracking in Flexible Pavements,” Updated Draft Final Report, NCHRP 9-38, National Cooperative Highway Research Program, Washington, D.C., May, 2008.

Soltani, A., Solaimanian, M., and Anderson, D.A., “An Investigation of the Endurance Limit of Hot-Mix Asphalt Concrete Using a New Uniaxial Fatigue Protocol,” **Report Number FHWA-HIF-07-002**, Federal Highway Administration, Washington, D.C.,

HMA Healing Studies

Bonnaure, F.P, Huibers, A.H.J.J., Boonders, A., “A Laboratory Investigation of the Influence of Rest Periods on the Fatigue Response of Bituminous Mixes,” **Proceedings, Association of Asphalt Paving Technologists**, Vol. 51, 1982.

Carpenter, S.H., and Shen, S., “Application of the Dissipated Energy Concept in Fatigue Endurance Limit Testing,” **Transportation Research Record No. 1929**, Transportation Research Board, Washington, D.C., 2005.

Kim, B. and Roque, R., “Evaluation of Healing Property of Asphalt Mixtures,” **Transportation Research Record No. 1970**, Transportation Research Board, Washington, D.C., 2006.

Kim, Y.R., Little, D.N., and Benson, F.C., “Chemical and Mechanical Evaluation of Healing of Asphalt Concrete,” **Journal of the Association of Asphalt Paving Technologists**, Vol. 59, 1990.

Little, D. N., Lytton, R. L., Williams, D., and Chen, C. W., “Microdamage Healing in Asphalt and Asphalt Concrete, Volume I: Microdamage and Microdamage Healing Project Summary Report,” **Report Number FHWA-RD-98-141**, Federal Highway Administration, Washington, D.C., June 2001.

Pronk, A.C., “Partial Healing, “A New Approach for the Damage Process During Fatigue Testing of Asphalt Specimens,” **Asphalt Concrete Simulation, Modeling, and Experimental Characterization**, Geotechnical Special Publication No. 146, American Society of Civil Engineers, Reston, VA, 2005.

MEPDG

National Cooperative Highway Research Program, <http://www.trb.org/mepdg/guide.htm> (accessed June 30, 2008).

Rest Periods

Hajek, J. J., Selezneva, O., I., Mladenovic, G., and Jiang, Y., J., “Estimating Cumulative Traffic Loads, Volume II: Traffic Data Assessment and Axle Load Projection for the Sites With Acceptable Axle Weight Data, Final Report for Phase 2,” **Report Number FHWA-RD-03-094**, Federal Highway Administration, Washington, D.C., March, 2005.

Lytton, R L; Uzan, J; Fernando, E G; Roque, R; Hiltunen, D; Stoffels, S M, “Development And Validation Of Performance Prediction Models And Specifications For Asphalt Binders And Paving Mixes,” **Report Number SHRP-A-357**, Strategic Highway Research Program, Washington, D.C., 1993.

Task C. Database Management

Task C includes the development and management of a database to store and analyze data generated in Task D, Laboratory Testing, and Task E, Analysis of Pavement Sections. It is envisioned that the database will be an adaptation of the one developed in NCHRP Project 9-30. Task C has been divided into three subtasks:

- C.1 Develop a Plan to Use the NCHRP 9-30 Database
- C.2 Develop Needed Tables,
- C.3 Input and Manage Data

Each of these subtasks are described in detail below.

Subtask C.1 Develop a Plan to Use the NCHRP 9-30 Database

In NCRHP Project 9-30 a database called M-E Distress Prediction Models (M-E_DPM) was developed to provide an appropriate database structure for storing all HMA pavement data required for the continued improvement of mechanistic-empirical pavement distress prediction models (33). It was envisioned that this database would serve future mechanistic-empirical development efforts such as the HMA Endurance Limit Validation Study. Consequently, M-E_DPM was designed to be flexible to accommodate changes in models and test procedures. The database was developed in Microsoft Access to take advantage of the standard and custom features available for entering and storing data, querying data, and generating reports. It consists of three parts that are briefly described below:

- **Descriptive Database.** This part of the database includes text files that document details for the data included in the model inputs portion of the database. This part of the database provides the flexibility to define the new type of data that will be needed in the HMA Endurance Limit Validation Study.
- **Model Inputs.** This part of the database includes the data required to execute the mechanistic-empirical models. The data are contained in tables that define (1)

pavement structure, (2) material properties, (3) traffic, and (4) climate. For the HMA Endurance Limit Validation Study new material properties associated with the allowable strain levels for full healing will be required.

- **Performance Data.** This part of the database includes various measures of pavement distress including (1) area of alligator cracking, (2) longitudinal cracking, (3) transverse cracking, (4) rutting, (5) smoothness, and (6) other distresses such as potholes and the extent of patching. Additional detail concerning the performance data will be required by the Endurance Limit Validation Study to differentiate bottom-initiated cracking from surface initiated cracking.

In Subtask C.1, the current version of M-E_DPM and its documentation will be reviewed and a plan will be developed for modifying this database for use in the analysis of the pavement sections in Task E. M-E_DPM is currently being improved and additional data is being added in NCHRP Project 9-30A. The key HMA property needed for the analysis approach described earlier in this plan is the allowable strains for full healing, which will be a function of HMA damage and healing properties, age, and climate. The laboratory experiments in Task D will establish methods for measuring the HMA damage and healing properties and will develop models for estimating these properties from mixture composition and binder properties that can be easily measured on field cores. The required material property data tables will have to be added to the model inputs portion of M-E_DPM. The extent of bottom-initiated fatigue cracking will be the pavement distress needed for the analysis of the pavement sections. Only the extent of surface cracking is currently contained in M-E_DPM; therefore, additional tables will be needed to store this data. The data will be obtained from the crack coring operations described in Task E.

A plan for storing the data from the Task D laboratory experiments will also be developed in Subtask C.1. This will likely be a separate database that can be linked to M-E_DPM upon completion of the analysis of the laboratory experiments and the development of the models and procedures for computation of allowable strains for full healing.

Subtask C.2 Develop Needed Tables

In Subtask C.2, the various tables required to use M-E_DPM in the HMA Endurance Limit Validation Study will be developed. Work in this task will be coordinated with the data collection and analysis activities in Tasks 4 and 5.

Subtask C.3 Input and Manage Data

Data from the project will be entered into the database and managed in Subtask C.3. This subtask includes entering the data, verifying the entered data, and extracting data in support of the analyses that will be performed in Tasks 4 and 5 of the project. Subtask C.3 will be active during the majority of the project.

Task C Milestones

Table 12 summarizes the major milestones for Task C. These are all associated with the modification of M-E_DPM for use in this project. In addition to the major milestones listed in Table 12, data entry and management will occur as needed from month 8 through the completion of Tasks 3, 4, and 5 in month 41 of the project.

Table 12. Major Task C Milestones.

Milestone	Description	Months After Contract Award
C.1	Database Plan	8
C.2	Tables for Laboratory Data	10
C.3	Tables for Analysis of Accelerated Pavement Tests	15
C.4	Tables for Analysis of In-Service Pavement Sections	23
C.5	Final Database	41

Task C Labor Estimate

Table 13 presents the estimated labor required for Task C. Table 13 presents estimated labor hours for each of the positions in the research management structure presented in Figure 5 and for programming/engineering assistance. Task C is estimated to require a total of 876 man-hours of effort. This is approximately 6 percent of the total effort required for the project.

Table 13. Estimated Labor Hours for Task C.

Subtask	Principal Investigator	Statistician	Laboratory Team Leader	Pavement Team Leader	Data Support Team Leader	Programmer/Engineer
Develop Plan to Use NCHRP 9-30 Database	20	0	10	10	80	0
Develop Needed Tables	0	0	0	0	80	240
Input and Manage Data	0	0	0	0	40	396
Total	20	0	10	10	200	636

Task C Sources

Von Quintus, H.L., Schwartz, C., McQuen, R., and Andrei, D., “Experimental Plan for Calibration and Validation of Hot-Mix Asphalt Performance Models for Mix and Structural Design,” Final Report for National Cooperative Highway Research Program Project 9-30, National Cooperative Highway Research Program, January, 2004.

Quarterly Reports for NCHRP Project 9-30A.

Task D. Laboratory Studies

In Task D a series of laboratory experiments addressing critical aspects of the allowable strain limit design procedure described earlier in Task B will be designed and executed. Table 14 summarizes the laboratory experiments that are needed.

Experiment 1 is a screening study to identify the mixture compositional factors that affect healing and therefore, the allowable strain levels in HMA. The results from this experiment will be used in the remaining experiments. Experiment 2 addresses a major assumption that was made in developing the allowable strain limit procedure that was described in Task 2. In this experiment healing rates will be determined using different strain levels. This experiment will be conducted on mixtures from Experiment 1 that have high and low healing rates. Experiment 3 is a study to verify the applicability of time-temperature superposition to healing in HMA. This was the second major assumption included in the development of the allowable strain limit procedure described in Task 2. Experiment 3 will be conducted on a mixture from Experiment 1 that exhibits a moderate healing rate. Testing and analysis methods for determining allowable strain limits that result in complete healing will be developed in Experiment 4. This experiment

will include testing and analysis of selected mixtures from Experiment 1 and mixtures used in the endurance limit testing completed in NCHRP 9-38. This experiment will generate the Level 1 test procedure for use with the modified version of the MEPDG. In the last experiment, Experiment 5, a wide range of mixtures will be tested using the methods developed in Experiment 4 to develop predictive models relating the allowable strain limits to mixture compositional factors. This last experiment will generate the relationships between allowable strain and easily measured mixture compositional properties that will be used in the analysis of the pavement sections in Task E. These relationships will provide the Level 2 and 3 analysis for the modified version of the MEPDG.

Table 14. Summary of Proposed Laboratory Experiments.

Experiment	Topic	Factors
1	Mixture Compositional Factors Affecting Healing in HMA	<ul style="list-style-type: none"> • Binder Type • Binder Age • Effective Binder Content • Air Voids • Design Compaction • Gradation • Filler Content
2	Effect of Applied Strain on Healing	<ul style="list-style-type: none"> • Strain Level • Healing Rate From Experiment 1
3	Effect of Temperature and Rest Period Duration on Healing	<ul style="list-style-type: none"> • Temperature • Rest Period Duration
4	Development of Testing and Analysis Procedures to Determine Allowable Strain Levels	<ul style="list-style-type: none"> • Healing Rate From Experiment 1 • Mixtures From NCHRP 9-38
5	Estimation of Allowable Strain Levels from Mixture Composition	<ul style="list-style-type: none"> • Mix Compositional Factors Affecting Damage Accumulation • Significant Factors From Experiment 1 • Temperature • Rest Period Duration

For each experiment, detailed laboratory work plans will be prepared based on the experiment descriptions and preliminary designs in this research plan and the results from completed experiments. The experiments will then be executed and the resulting data analyzed. Pertinent interim findings from the laboratory studies will be included in the quarterly progress reports. The laboratory testing and analysis will be fully documented in the third interim report that will

be submitted at the end of the 22nd month of the project. The five experiments are described in greater detail below.

Subtask D.1 Experiment 1: Mixture Compositional Factors Affecting Healing in HMA

Experimental Design

Past studies of healing in HMA have assumed that only the properties of the binder affect the healing characteristics of the mixture (7, 24, 34). Experiment 1 is a screening study that will use an appropriate statistical design to verify or refute this assumption and to identify mixture compositional factors affecting healing in HMA that should be included in Experiment 5.

Experiment 1 is based on a Plackett-Burman experimental design. This is a specific type of partial factorial experiment that can simultaneously assess the effect of multiple factors with a limited amount of testing. It is routinely used in ruggedness testing to quickly assess the effect of a number of controllable test factors. ASTM E 1169 presents detailed information on the design and analysis of Plackett-Burman experiments. Inherent to this type of statistical design is the assumption that the effect of each of the factors on the result is independent. Therefore, the observed effect resulting from simultaneous variation of several factors is simply the sum of the individual effects. Since screening experiments are concerned with identifying significant effects and not necessarily the form of the effect, each factor is evaluated at only two levels. Replication is included in the experiment to estimate the variance of a single measurement.

A Plackett-Burman design with replication to simultaneously evaluate 7 factors requires only 16 tests, two for each of the specific combinations shown in Table 15. The seven factors are designated by letters *A* through *G*. A “+” indicates high levels for the factors while a “-“ indicates low levels. Thus, determination 1 will be made with factors *A*, *B*, *C* and *E* at high levels, and factors *D*, *F*, and *G* at low levels. The order of the tests should be randomized within each replication of the experiment. ASTM E1169 describes designs for other numbers of factors.

Table 15. Design for a Two Level, Seven Factor Plackett-Burman Experiment.

Determination	Factor						
	<i>A</i>	<i>B</i>	<i>C</i>	<i>D</i>	<i>E</i>	<i>F</i>	<i>G</i>
1	+	+	+	-	+	-	-
2	-	+	+	+	-	+	-
3	-	-	+	+	+	-	+
4	+	-	-	+	+	+	-
5	-	+	-	-	+	+	+
6	+	-	+	-	-	+	+
7	+	+	-	+	-	-	+
8	-	-	-	-	-	-	-

Selection of Factors

The selection of factors for Experiment 1 was based on a review of literature concerning fatigue damage and healing in HMA. The factors are discussed individually below.

Binder Type. Several studies of fatigue and healing in HMA have shown that binder properties affect the fatigue response of the mixture (35). The Shell fatigue equation is, perhaps, the earliest example (36). It included the penetration index, which was an early measure of the rheology of the binder. Research into healing that has been conducted at the Texas Transportation Institute has shown that the properties of the binder affect healing (34).

Less information is available on the effect of polymer modification on the fatigue and healing characteristics HMA. Using continuum damage analysis, Lee, et. al demonstrated better fatigue resistance for mixtures incorporating SBS modified binders (37). Recent research on healing conducted at the University of Illinois using one neat and one polymer modified binder showed the mixture with the polymer modified binder had improved healing characteristics compared to the mixture with the neat binder (7). In both of these studies, the neat and polymer modified binders were different grades.

Clearly, Experiment 5 will have to include a wide variety of binders, both neat and modified, from different sources. In an attempt to better quantify the effect of polymer

modification on healing, Experiment 1 will use two binders from the same source having the same performance grade, one neat and one modified with styrene butadiene styrene (SBS). The recommended binders are neat PG 70-22 and a modified PG 70-22 produced by adding SBS polymer to neat PG 58-28 binder obtained from the same refinery as the neat PG 70-22.

Binder Aging. It is generally assumed by pavement and materials engineers that binder aging has a detrimental effect on the fatigue life of asphalt mixtures. With this in mind, it is interesting that only one study was identified where the effect of binder aging on laboratory fatigue results was directly evaluated (38). In most laboratory fatigue studies, unaged or short-term aged binders of different consistencies were used, and the results generalized to describe the effect of mixture stiffness on fatigue life. The general conclusions drawn from these studies that used relatively unaged binders are (35):

1. For continuous, controlled stress flexural testing, which is typically associated with thick asphalt pavements, laboratory fatigue life increases with increasing mixture stiffness.
2. For continuous, controlled strain flexural testing, which is typically associated with thin asphalt pavements, laboratory fatigue life decreases with increasing mixture stiffness.
3. When the results from either controlled stress or controlled strain flexural tests are used in a mechanistic-empirical analysis of pavements with 6 or more inches of asphalt, the predicted fatigue life increases with increasing mixture stiffness.

These conclusions imply that binder aging improves the fatigue life of pavements with relatively thick asphalt layers. Because unaged and short-term aged binders were used in these studies, the important effect of binder embrittlement was not included in the analysis. As asphalt binders age, they become, not only stiffer, but also more brittle due to oxidation.

Recently, researchers at the Texas Transportation Institute performed controlled strain flexural fatigue testing on compacted specimens from two mixtures that were aged for 0, 3, and 6 months at 60 °C (38). Three months of aging at 60 °C simulates 3 to 6 years of field service for Texas conditions while 6 months of aging simulates 6 to 12 years of field service (38). The loose mix for all specimens was short-term oven aged for 4 hours at 135 °C prior to compaction. Fatigue lives were 25 percent shorter for specimens aged for three months, and 50 percent shorter for specimens aged for six months (38). The study also included direct tension strength tests. In these tests strength increased while the strain at failure decreased with increased aging, confirming that the mixtures become stiffer and more brittle on aging (38). Aged, brittle mixtures would be expected to have significantly poorer healing characteristics compared to unaged, ductile mixtures. Short-term and long-term aged mixtures will be included in Experiment 1. The short-term aging will be done for 4 hours at 135 °C as specified in AASHTO R30 for mixture performance testing. The long-term aged specimens will be oven aged for 120 hours at 85 °C in accordance with AASHTO R30. Since the effects of aging are binder specific, preliminary dynamic modulus and tensile strength tests should be conducted to ensure that the selected binders exhibit significant stiffening and embrittlement as a result of the laboratory, long-term aging process.

Effective Binder Content. Models for predicting the fatigue life of asphalt concrete based on the results of continuous laboratory fatigue tests all indicate that fatigue life increases as the mixture becomes increasingly rich in asphalt binder (39). These models use either the effective volumetric binder content of the mixture, *VBE*, or voids filled with asphalt, *VFA*, to indicate the richness of the mixture. Binder content effects have not been included in past studies of healing in asphalt concrete.

It is reasonable to expect that richer mixtures may have improved healing characteristics, resulting in improved fatigue lives, and higher allowable strains for complete healing. Binder content will, therefore, be one of the factors included in Experiment 1. Volumetric design procedures for asphalt mixtures set minimum limits for the effective binder content of the mixture. These limits depend on the nominal maximum aggregate

size; increasing with decreasing nominal maximum aggregate size. Since this project is concerned with fatigue cracking that initiates at the bottom of the asphalt layer, a typical 25 mm base course mixture will be used. The minimum effective binder content for 25 mm mixtures in AASHTO M323 is 8.0 percent by volume. The recommended production tolerance for asphalt content in ASTM D 3535 is ± 0.5 percent by weight, which is approximately ± 1 percent for the effective binder content by volume. These are reasonable ranges for use in Experiment 1.

Air Voids. Nearly all laboratory fatigue studies have found the air void content of the mixture to be a significant factor affecting mixture fatigue life (35, 39). Fatigue life decreases with increasing air voids. It is reasonable to expect that air voids will also have a significant effect on healing in asphalt concrete mixtures. Based on typical compaction specifications, specimen air void contents of 4 and 8 percent will be included in Experiment 1.

Design Compaction. An interesting finding in NCHRP Report 567, *Volumetric Requirements for Superpave Mix Design*, is that the fatigue life of asphalt concrete mixtures is significantly affected by the design compaction level; increasing as the design gyration level increases (39).

Design compaction level was included in Experiment 1 to determine if healing properties of asphalt mixtures are affected by the design compaction level. Considering the current design compaction levels in AASHTO R35, the recommendations in NCHRP Report 573, *Superpave Mix Design: Verifying the Gyration Levels in the N_{design} Table* (40) and approximate equivalencies between Marshall and gyratory compaction (39), design gyration levels of 65 and 100 will be used in Experiment 1.

Gradation. The WesTrack project demonstrated that there is a difference in the fatigue life of coarse-graded mixtures compared to fine-graded mixtures. Significantly more cracking was observed in the coarse-graded mixture sections (41). Mixture gradation has

not been found to be a significant factor in fatigue models based on analysis of laboratory test data.

As a result of the WesTrack experience, gradation was included in Experiment 1 to determine if healing is different in coarse-graded compared to fine-graded mixtures. The primary control sieve designation in AASHTO M323 will be used to distinguish between coarse-graded and fine-graded mixtures. For 25 mm mixtures, the 4.75 mm sieve is the primary control sieve and mixtures with less than 40 percent passing the 4.75 mm sieve are considered coarse-graded.

Filler Content. Like aging, the effect of filler on the fatigue life of asphalt concrete has not been systematically investigated. Currently, the influence of mineral filler on HMA properties is being studied in NCHRP Project 9-45. The dust to binder ratio, defined as the percent by weight passing the 0.075 mm sieve divided by the effective binder content by weight of total mixture, is used in AASHTO M323 to control the filler content of mixtures. A reasonable median value for the dust to binder ratio for design is 1.0. The recommended production tolerance for the percent passing the 0.075 mm sieve in ASTM D 3535 is ± 3.0 percent. This range is considered reasonable for Experiment 1.

Table 16 summarizes the factors and factor levels to be included in Experiment 1.

Experiment 1 requires the selection of a neat and polymer modified binder from the same source and having the same performance grade, and the design of four 25 mm mixtures.

- 100 gyration coarse-graded
- 100 gyration fine-graded
- 65 gyration coarse-graded
- 65 gyration fine-graded

Table 16. Summary of Proposed Experiment 1.

Determination	Factor						
	<i>Binder</i>	<i>Aging</i>	<i>Binder Content</i>	<i>Air Voids</i>	N_{design}	<i>% Passing 4.75 mm</i>	<i>Filler</i>
1	Polymer	LTOA	+ 0.5	4.0	100	Coarse	Low
2	Neat	LTOA	+ 0.5	8.0	65	Fine	Low
3	Neat	STOA	+ 0.5	8.0	100	Coarse	High
4	Polymer	STOA	- 0.5	8.0	100	Fine	Low
5	Neat	LTOA	- 0.5	4.0	100	Fine	High
6	Polymer	STOA	+ 0.5	4.0	65	Fine	High
7	Polymer	LTOA	- 0.5	8.0	65	Coarse	High
8	Neat	STOA	- 0.5	4.0	65	Coarse	Low

In designing these mixtures, the target effective binder content for all mixtures should be kept constant at approximately 8.5 percent by volume, which will result in design voids in the mineral aggregate (VMA) of 12.5 percent. The design dust to binder ratio should also be kept constant for the four mixtures at approximately 1.0. These binder selection and mixture design requirements will eliminate major interactions between the factors. During binder selection, preliminary dynamic modulus and tensile strength tests should be conducted on specimens after short- and long-term aging to ensure that the selected binders exhibit significant stiffening and embrittlement as a result of the long-term aging.

The factor levels for binder content and filler will be obtained by making the appropriate adjustment to the design mixture during batching. The factor levels for aging will be obtained by appropriately aging the loose mixture and, for long-term aging, the test specimen. Finally, the factor levels for air voids will be obtained by compacting specimens to the height needed to achieve the target air voids.

Replicate tests for each determination in Table 16 will be made. This results in a total of 16 healing tests for Experiment 1.

Test Procedure

The objective of Experiment 1 is to identify the mixture compositional factors that affect healing in asphalt concrete. To evaluate healing, a pulsed, strain controlled fatigue test must be used. Either direct tension or flexural beam fatigue tests may be used, but the loading must be such that a rest period is included after each load pulse. Figure 12 presents a schematic of the required loading. The amount of healing that occurs will be evaluated by conducting fatigue tests at 20 °C using two rest periods: 0 sec (continuous loading), and 3 sec. The modulus of the specimen will be recorded for each load pulse. For each test, the accumulated damage in the specimen will be determined from the ratio of the current modulus to the initial modulus. Figure 13 presents a schematic of the expected results when significant healing occurs.

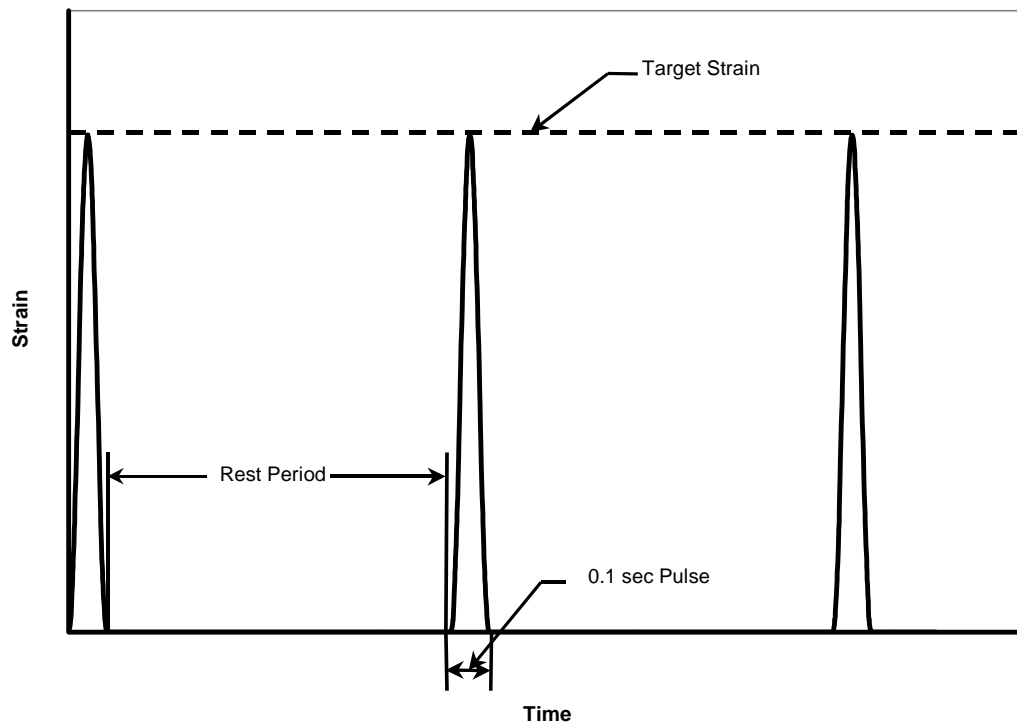


Figure 11. Schematic of Pulsed, Strain Controlled Fatigue Loading.

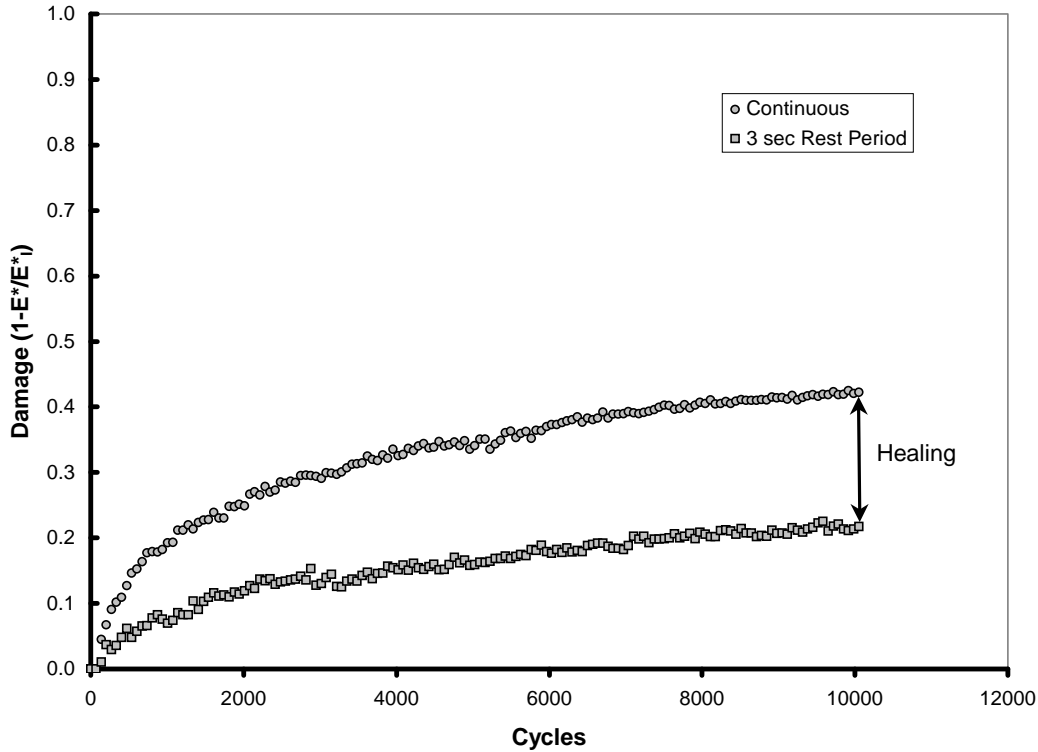


Figure 12. Expected Results When Healing is Significant.

The same strain level must be used for all specimens tested in Experiment 1. The strain level should be selected to produce a high degree of damage, approximately 30 to 40 percent, in the specimens after 10,000 cycles when tested with continuous loading. Fifty percent damage is typically used as the failure criterion for controlled strain tests. A maximum of 10,000 cycles was selected because tests using the 3 sec rest period will require approximately 8.6 hours to complete. Selection of an appropriate strain level will require some initial trial and error testing with selected combinations. For example, the combination of factors used in Determination 6 in Table 16 (polymer modified binder, short-term aging, high binder content, low air voids) would be expected to give low amounts of damage during the testing. On the other had, the combination of factors used in Determination 7 (polymer modified binder, long-term aging, low binder content, high air voids) would be expected to give high amounts of damage during the testing. Initial testing with these combinations at various strain levels will be needed to select an appropriate strain level for the testing.

Data Analysis

For Experiment 1, healing is defined as the difference in damage between continuous loading and loading with 3 sec rest period at 30,000 cycles. Linear regression is an efficient method for analyzing the resulting healing data. The healing can be fit to a linear model of the form:

$$Y = B_0 + B_1X_1 + B_2X_2 + B_3X_3 + B_4X_4 + B_5X_5 + B_6X_6 + B_7X_7 + Error \quad (17)$$

where:

Y = healing

X_i = seven factors included in the experiment

B_i = model coefficients

Error = model error

From this analysis, the statistical significance of the model coefficients can be used to determine which factors affect healing in HMA. For statistically significant factors, the model coefficients can be used to select appropriate factor levels to be used in other experiments. Combinations yielding low, moderate, and high levels of healing in Experiment 1 will be used in Experiments 2, 3, and 4. Significant factors identified in Experiment 1 will be included in Experiment 5.

Subtask D.2 Experiment 2: Effect of Applied Strain on Healing

Experimental Design

One of the major assumptions that was made in developing the allowable strain limit design approach described in Task 2 is that healing in HMA is independent of the applied strain level. Early healing research provided some data supporting this assumption, but the testing was not specifically designed to evaluate the effect of strain level (24).

In Experiment 2, the healing tests described for Experiment 1 will be conducted using three different strain levels. Two different mixtures from Experiment 1 will be used: one exhibiting a high amount of healing and one exhibiting a low amount of healing. All tests will be conducted at 20 °C. The strain level used in Experiment 1 will be the medium strain level for Experiment 2. Tests at higher and lower strain levels will be added to complete the factorial. In selecting the high strain level, it is important that the strain be such that macro-cracking does not occur during

the tests. Three replicates will be tested for each mixture. The experimental design is summarized in Table 17.

Table 17. Strain Level Experiment.

Mixture	Strain Level	Replicates
Low Healing	Low	3
	Medium	3
	High	3
High Healing	Low	3
	Medium	3
	High	3

Data Analysis

Analysis of variance will be used to analyze the data from Experiment 2. For each mixture a one-way analysis of variance will be conducted. It is anticipated that this analysis will confirm that healing in HMA is not significantly affected by the applied strain level, provided the strains are low enough that macro-cracking does not occur.

Subtask D.3 Experiment 3: Effect of Temperature and Rest Period Duration on Healing Experimental Design

The second major assumption that was made in developing the allowable strain limit design approach described in Task 2 is that time-temperature superposition can be applied to the rest periods to account for the effect of varying temperatures. The objective of Experiment 3 is to confirm that this assumption is valid. Previous research on healing clearly showed that healing effects were greater at higher temperatures (24). It is reasonable to expect that time-temperature superposition will apply to rest period effects as it does for many other aspects of asphalt material response. It is well known that time-temperature superposition is valid for measures of binder and mixture stiffness. Time-temperature superposition is also an integral part of the continuum damage approach to fatigue analysis that has become popular with a number of researchers (42, 43, 44).

In Experiment 3, the healing tests described for Experiment 1 will be conducted using a factorial of temperatures and rest period duration. A single mixture from Experiment 1, one exhibiting a moderate amount of healing, will be used. Two replicates will be tested for each mixture. The experimental design is summarized in Table 18. In addition to the healing tests outlined in Table 18, dynamic modulus tests will be performed on replicate specimens at the temperatures and frequencies listed in Table 19 to determine time-temperature shift factors for the mixture. The dynamic modulus testing will be performed in accordance with NCHRP 9-29: PT1, *Determining the Dynamic Modulus and Flow Number for Hot Mix Asphalt (HMA) Using the Simple Performance Test System (45)*.

Table 18. Experimental Design for Experiment 3.

Mixture	Temperature, C	Rest Period, sec	Replicates
Moderate Healing	4	0	2
	4	0.1	2
	4	1	2
	4	10	2
	10	0	2
	10	0.1	2
	10	1	2
	10	10	2
	20	0	2
	20	0.1	2
	20	1	2
	20	10	2
	30	0	2
	30	0.1	2
	30	1	2
	30	10	2
	40	0	2
	40	0.1	2
	40	1	2
	40	10	2

Table 19. Temperature and Frequency Combinations for Dynamic Modulus Tests.

Temperature, C	Frequency, Hz
4	10
4	1
4	0.1
4	0.01
10	10
10	1
10	0.1
10	0.01
20	10
20	1
20	0.1
20	0.01
30	10
30	1
30	0.1
30	0.01
40	10
40	1
40	0.1
40	0.01

Data Analysis

The data analysis for Experiment 3 is somewhat more complicated than that for Experiments 1 and 2. First, time-temperature shift factors must be determined from the dynamic modulus measurements. Then the time-temperature shift factors will be applied to the rest periods to shift the measured healing data. If time-temperature superposition applies to the rest periods, then the healing results will form a continuous function after shifting.

Dynamic Modulus Master Curve and Shift Factors

Equation 18 presents a modified version of the dynamic modulus master curve equation included in the MEPDG that is appropriate for this analysis (46).

$$\log|E^*| = \delta + \frac{(\log|E^*|_{\max} - \delta)}{1 + e^{\beta + \gamma \log f_r}} \quad (18)$$

where:

- $|E^*|$ = dynamic modulus
- f_r = reduced frequency, Hz
- $|E^*|_{\max}$ = limiting maximum modulus
- δ , β , and γ = fitting parameters

A second order polynomial can be used to describe the time-temperature shift factors:

$$\log[A(T)] = a_1(T_R - T) + a_2(T_R - T)^2 \quad (19)$$

where:

- $A(T)$ = time-temperature factor
- T = test temperature
- T_R = reference temperature (normally 20 °C)
- a_1 , a_2 = fitting coefficients

The reduced frequency in Equation 18 is given by:

$$\log f_r = \log f + a_1(T_R - T) + a_2(T_R - T)^2 \quad (20)$$

where:

- f_r = reduced frequency at the reference temperature
- f = loading frequency at the test temperature

Substituting Equation 20 into Equation 18 yields the final form of the dynamic modulus master curve equation.

$$\log|E^*| = \delta + \frac{(\log|E^*|_{\max} - \delta)}{1 + e^{\beta + \gamma[\log f + a_1(T_R - T) + a_2(T_R - T)^2]}} \quad (21)$$

The limiting maximum modulus, $|E^*|_{\max}$, in Equation 21 is estimated from mixture volumetric properties using the Hirsch model (47) and a limiting binder modulus of 1 GPa (145,000 psi), using Equations 22 and 23. Christensen and Anderson recommended 1 GPa as a reasonable estimate of the glassy modulus for all asphalt binders (48).

$$|E^*|_{\max} = P_c \left[4,200,000 \left(1 - \frac{VMA}{100} \right) + 435,000 \left(\frac{VFA \times VMA}{10,000} \right) \right] + \frac{1 - P_c}{\left[\frac{\left(1 - \frac{VMA}{100} \right)}{4,200,000} + \frac{VMA}{435,000(VFA)} \right]} \quad (22)$$

where

$$P_c = \frac{\left(20 + \frac{435,000(VFA)}{VMA} \right)^{0.58}}{650 + \left(\frac{435,000(VFA)}{VMA} \right)^{0.58}} \quad (23)$$

$|E^*|_{\max}$ = limiting maximum mixture dynamic modulus, psi

VMA = Voids in mineral aggregates, %

VFA = Voids filled with asphalt, %

Using the limiting maximum modulus estimated from the volumetric properties of the test specimens, the fitting coefficients (δ , β , γ , a_1 , and a_2) are determined by numerical optimization of Equation 21 using the measured modulus data. The optimization can be performed using the Solver function in Microsoft EXCEL®. This is done by setting up a spreadsheet to compute the sum of the squared errors between the logarithm of the average measured dynamic moduli at each temperature/frequency combination and the values predicted by Equation 21.

$$\sum error^2 = \sum_1^n \left(\log |\hat{E}^*|_i - \log |E^*|_i \right)^2 \quad (24)$$

where:

$\sum error^2$ = sum of squared errors

n = number of temperature/frequency combinations used in the testing

$\log|\hat{E}^*|_i$ = value predicted by Equation 20 for each

temperature/frequency combination

$\log|E^*|_i$ = logarithm of the average measured dynamic modulus for each

temperature/frequency combination.

The time-temperature shift factors are then determined from Equation 18 using the fitting coefficients, a_1 and a_2 , obtained from the numerical optimization.

Reduced Rest Period

Knowing the time-temperature shift factors from the dynamic modulus testing, the results of the healing tests will be shifted according to Equation 25. If time-temperature superposition applies to the rest periods, then the healing results will form a continuous function after shifting. This is shown schematically in Figure 14.


$$\log(RP_R) = \log(RP) - \log(A_T) \quad (25)$$

where:


RP_R = duration of the rest period at the reference temperature, sec

RP = actual duration of the rest period, sec

A_T = linear viscoelastic time temperature shift factor obtained from dynamic modulus testing.

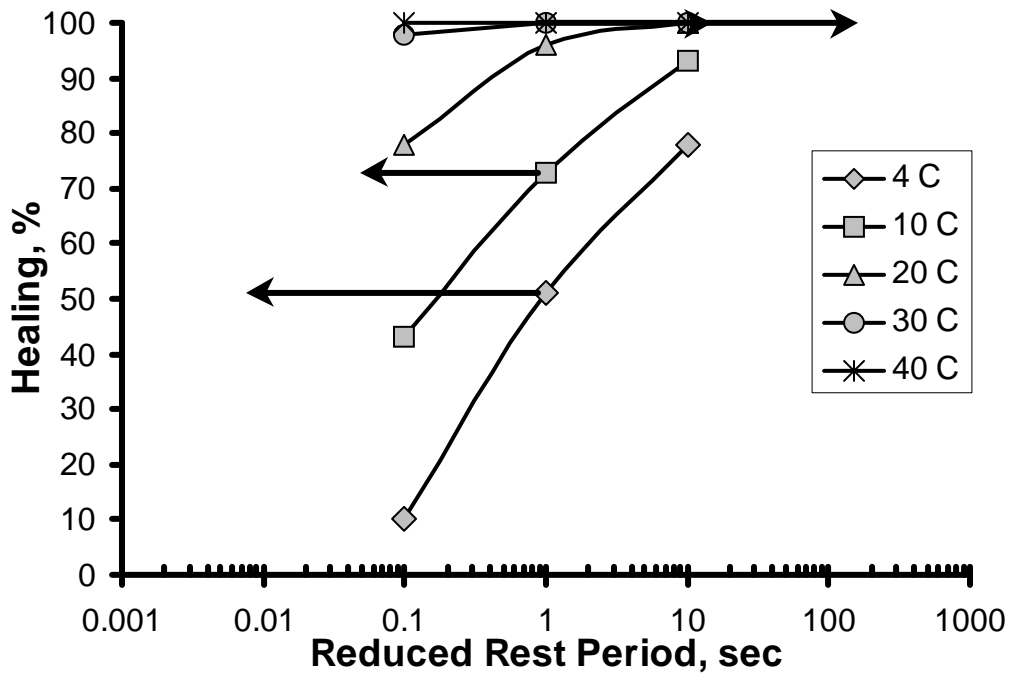

a. Original Data

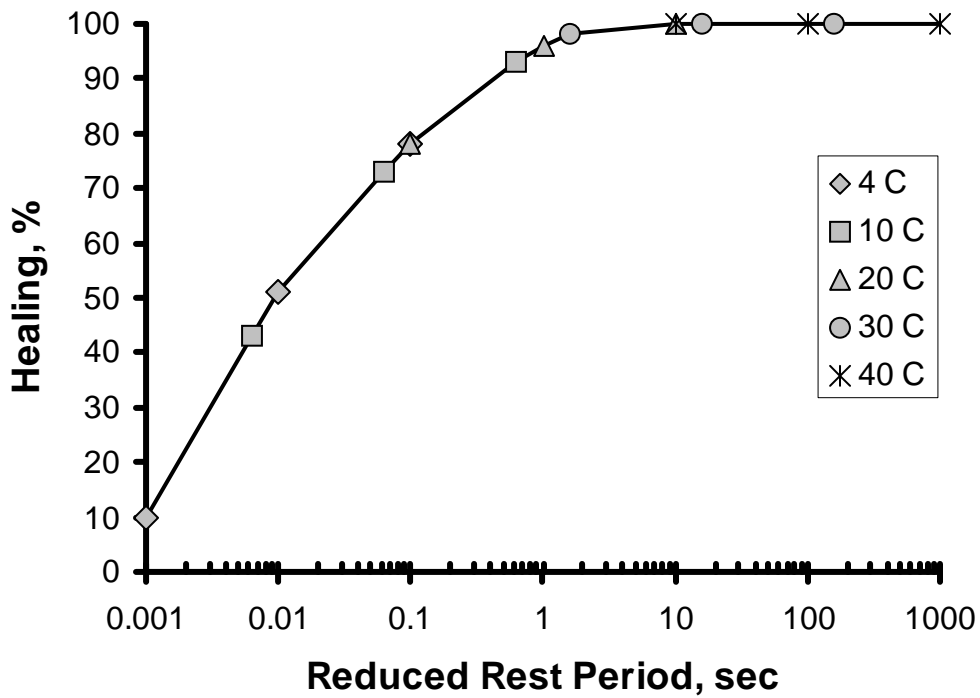

a. Shifted Data

Figure 13. Schematic of Time-Temperature Superposition Applied to Rest Periods.

Subtask D.4 Experiment 4: Development of Testing and Analysis Procedures to Determine Allowable Strain Levels

Possible Approaches

In Experiment 4, testing and analysis procedures for determining the allowable strain levels will be developed. One approach, using flexural fatigue testing and the ratio of dissipated energy change (RDEC) method was illustrated in the description of Task 2. A second approach based on cyclic direct tension testing and continuum damage analysis is also possible. Brief descriptions of these two approaches are presented below.

Ratio of Dissipated Energy Change

Recently a substantial amount of HMA fatigue research has been performed at the University of Illinois (4, 5, 7). This research has concentrated on using the ratio of dissipated energy change to describe the fatigue response of HMA. The basic premise of this research is that the change in dissipated energy per cycle of loading is related to the growth of damage that occurs in HMA. The dissipated energy for each cycle of loading is the area within the stress-strain hysteresis loop generated for that cycle of loading. The ratio of dissipated energy change is defined as the average change in dissipated energy between two cycles divided by the dissipated energy from the first of the two cycles:

$$RDEC_a = \frac{(DE_a - DE_b)}{(b - a) \times DE_a} \quad (26)$$

where:

$RDEC_a$ = ratio of dissipated energy change for cycle a

DE_a = dissipated energy for cycle a

DE_b = dissipated energy for cycle b

For a given mixture a plot of the ratio of dissipated energy change as a function of loading cycles forms a broad “U” shape as shown in Figure 15. The ratio of dissipated energy change initially decreases, then reaches a broad plateau, where a constant percentage of the input energy is being converted to damage, then finally increases as the sample begins to fail. Because of the high variability of the cyclic dissipated energy measurements due to the small amount of energy

dissipated in each cycle, statistical methods were developed to determine the plateau value (5). Lower plateau values imply lower damage per cycle. The plateau value for a given mixture depends on the mixture properties, the applied strain level, and the duration of rest periods. Plateau values decrease with decreasing applied strain and increasing rest period duration (7). The effect of mixture properties on the plateau value is not clear from the research that has been completed to date. From tests on a number of mixtures, the University of Illinois researchers also found a unique relationship between the plateau value and number of cycles to 50 percent reduction in stiffness, the traditional definition of failure in constant strain fatigue tests (7).

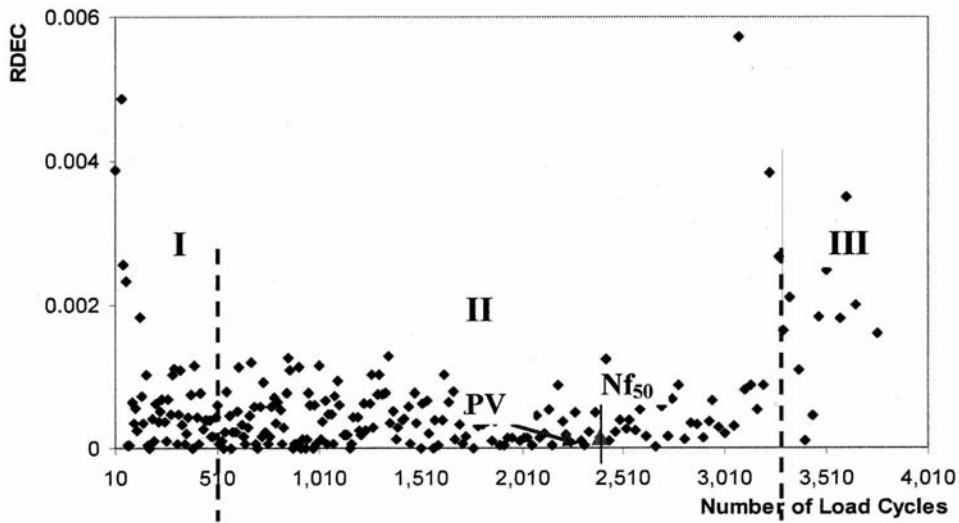


Figure 14. Typical Plot of Ratio of Dissipated Energy Change Versus Loading Cycles (6).

$$PV = 0.4429 \times (N_f)^{-1.1102} \quad (27)$$

where:

PV = plateau value

N_f = number of cycles to 50 percent stiffness reduction

The University of Illinois research further found that an HMA mixture will exhibit endurance limit behavior when the plateau value is 6.74×10^{-9} or less, which based on Equation 27 corresponds to a traditional fatigue life of 1.1×10^7 cycles or greater.

The testing and analysis required to use the ratio of dissipated energy change to establish allowable strain limits for complete healing is summarized below:

1. Conduct dynamic modulus tests on the mixture and develop a dynamic modulus master curve and associated time-temperature shift factors.
2. Conduct continuous loading, controlled strain flexural fatigue tests at 20 °C using different strain levels to develop a relationship between the plateau value and the applied strain (Equations 4 and 5 in Task 2).
3. Conduct pulsed, controlled strain flexural fatigue tests at a moderate strain level using various temperatures and rest periods to determine a relationship between the plateau value and reduced rest period (Equations 2 and 3 in Task 2).
4. Combine the relationships from Steps 2 and 3 to form a relationship for the plateau value as a function of applied strain level and reduced rest period (Equations 6 and 7 in Task 2).
5. Substitute the relationship from Step 4 into the unique plateau value – number of cycles to 50 percent stiffness reduction relationship (Equation 27) established by the University of Illinois research (Equations 8 and 9 in Task 2).
6. Solve the equation developed in Step 5 for the allowable strain level for full healing by substituting a value greater than 1.1×10^7 for the number of cycles to 50 percent stiffness reduction (Equations 10 and 11 in Task 2).

Continuum Damage Analysis

Continuum damage analysis has recently been introduced as a rapid method for characterizing fatigue properties of HMA (44). Pioneering work in the application of continuum damage analysis to HMA was performed at the North Carolina State University (42). Since its introduction, continuum damage analysis has been used by several researchers in the United States and abroad. The analysis is usually applied to the results of direct tension cyclic fatigue tests or monotonic direct tension tests, although an approximate solution has been developed for use with flexural fatigue tests (44).

Continuum damage analysis models the decay of the modulus of the mixture with increasing load cycles. Figure 16 shows typical cyclic direct tension data. In traditional continuum damage analysis, the curves for different strain levels and temperatures are collapsed into a unique relationship by introducing an internal state variable, S , to represent the current damage in the material. The internal state variable is difficult for many practicing engineers to understand and can only be computed using approximate, numerical integration. Additionally, traditional continuum damage analysis assumes that even very small levels of strain induce damage in the material, implying that asphalt concrete does not exhibit endurance limit behavior. Recently Christensen and Bonaquist, simplified continuum damage analysis and included the direct consideration of the endurance limit (49). This improved analysis uses the concept of reduced cycles defined by Equation 28 to collapse the data shown in Figure 16 into a unique relationship. The endurance limit of asphalt concrete is accounted for using the concept of effective strain. Effective strain is defined as applied strain minus the endurance limit. This innovation in continuum damage analysis allows for the calculation of endurance limits from relatively limited fatigue data.

$$N_R = N_{R-ini} + N \left(\frac{f_0}{f} \right) \left(\frac{|E^*|_{LVE}}{|E^*|_{LVE/0}} \right)^{2\alpha} \left(\frac{\varepsilon^E}{\varepsilon_0^E} \right)^{2\alpha} \left[\frac{1}{a(T/T_0)} \right] \quad (28)$$

Where

N_R = reduced cycles

N_{R-ini} = initial value of reduced cycles, prior to the selected loading period

N = actual loading cycles

F_0 = reference frequency (10 Hz suggested)

f = actual test frequency

$|E^*/_{LVE}$ = undamaged (linear viscoelastic or LVE) dynamic modulus under given conditions, lb/in²

$|E^*/_{LVE/0}$ = reference initial (LVE) dynamic modulus, lb/in² (the LVE modulus at 20°C is suggested)

α = continuum damage material constant with a typical value of about 2.0

ε^E = effective applied strain level = applied strain minus the endurance limit strain

ε_0^E = reference effective strain level (0.0002 suggested)

$a(T/T_0)$ = shift factor at test temperature T relative to reference temperature T_0

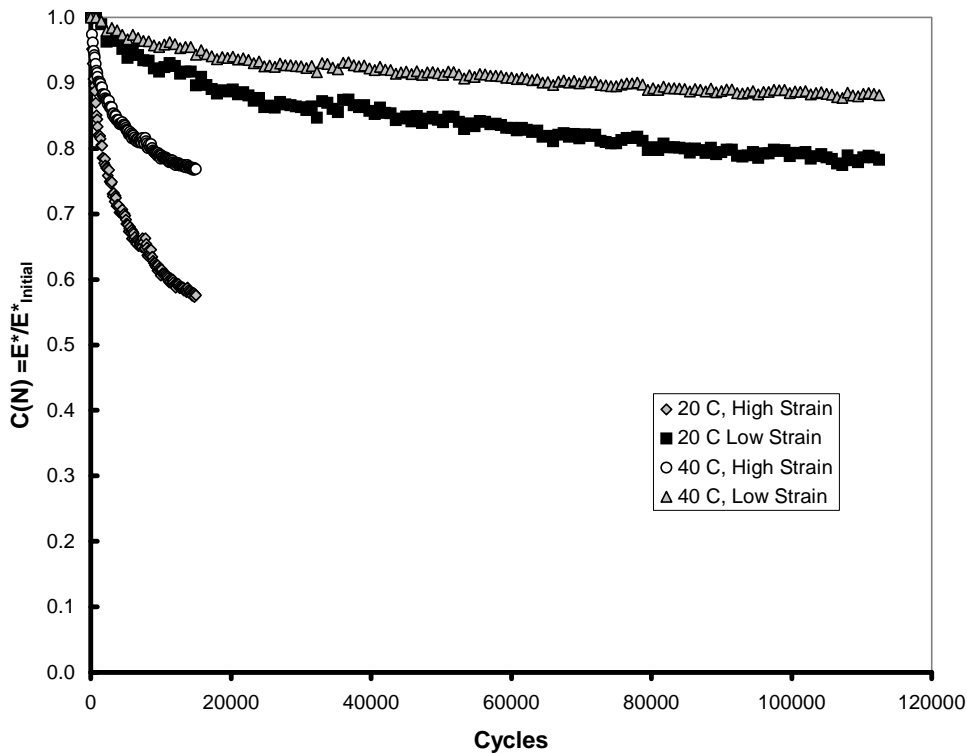


Figure 15. Typical Damage Ratio Curves From a Cyclic Direct Tension Fatigue Test.

Analysis of uniaxial fatigue data using the reduced cycles approach is done using the following procedure.

1. Select the reference conditions. The suggested reference strain is 0.000200, peak-to-peak. The recommended reference temperature is 68 °F (20°C). The reference modulus should be the undamaged dynamic modulus or linear viscoelastic LVE modulus at 68 °F (20°C). The reference frequency should be 10 Hz—the same as the most commonly used test frequency for modulus and fatigue testing of asphalt concrete mixtures.
2. Perform dynamic modulus master curve testing on two samples to determine time-temperature shift factors for the mixture.
3. Test a total of four to eight specimens, two to four at both 39.2 °F (4°C) and 68 °F (20°C). Other temperatures may be used if desired, but temperatures much higher or lower than these might prove difficult to test using the procedures given here. At each test temperature, the specimens should be tested at different strain levels for each test.
4. Set up a spreadsheet to compute the damage ratio, C , and the reduced cycles for each test. The damage ratio is given by Equation 29:

$$C = \frac{|E^*|_n}{|E^*|_{LVE}} \quad (29)$$

where:

C = damage ratio

$|E^*|_n$ = damaged modulus at cycle n

$|E^*|_{LVE}$ = undamaged (linear viscoelastic or LVE) dynamic modulus

Reduced cycles are calculated using Equation 28 and value of 2.00 for the continuum damage constant α and an endurance limit strain of zero. Variation in the applied strain during the test can be accounted for by splitting the data up into a number of segments, calculating reduced cycles for each segment, and adding this value to the initial value calculated at the end of the previous segment.

The LVE modulus can be estimated by visual examination of a plot of $|E^*|$ as a function of loading cycles at the lowest strain level tested. The LVE modulus should be within a few percent of the maximum observed value.

In some tests, macro damage (“localization”) might occur, which means that data beyond this point is not valid for analysis using continuum damage methods. Macro damage is indicated when there is a sudden drop in the modulus, or if modulus values suddenly become erratic, rather than decreasing smoothly. Data after macro damage has occurred should be eliminated from the analysis.

5. Fit Equation 30 to the C versus N_R data.

$$C = \frac{1}{1 + (N_R/K_1)^{K_2}} \quad (30)$$

where

K_1 = cycles to 50 % damage = the fatigue half-life

K_2 = fitting parameter

Linear regression can be used for the fitting by performing a logarithmic transformation of Equation 30 to produce:

$$\ln\left(\frac{1}{C} - 1\right) = A + B \ln N_R \quad (31)$$

where:

$$A = -K_2(\ln K_1)$$

$$B = K_2$$

A problem in practical application of this approach is that because of noise in the experimental data at low strains, the measured modulus can approach the LVE, resulting in very noisy data when it is transformed using Equation 31. For this reason, a weighted least squares approach to linear regression should be used, with a weight of $N_R^{0.5}$. This

approach gives very little weight to data points representing little or no damage, while giving relatively more weight to data points associated with more heavily damaged states. This prevents noisy data collected at low temperatures and/or low strains from skewing the function relating C and N_R , and also results in a more ideal distribution of the residuals.

6. Keeping the value of α at 2.00, adjust the endurance limit strain for the data at 68 °F (20°C) until the R^2 value for the regression is maximized. Then adjust the endurance limit strain value for the data at 39.2 °F (4°C), again, until the R^2 value for the regression is maximized.

Although it is possible to vary the value of α , it has been found that excellent convergence of the data is generally possible while keeping α at 2.00 for all asphalt concrete mixtures tested to date using this procedure. However, if the steps above do not result in complete convergence, it might be necessary to vary the assumed value of α .

Figure 17 presents a typical fatigue damage curve developed using the procedure described above.

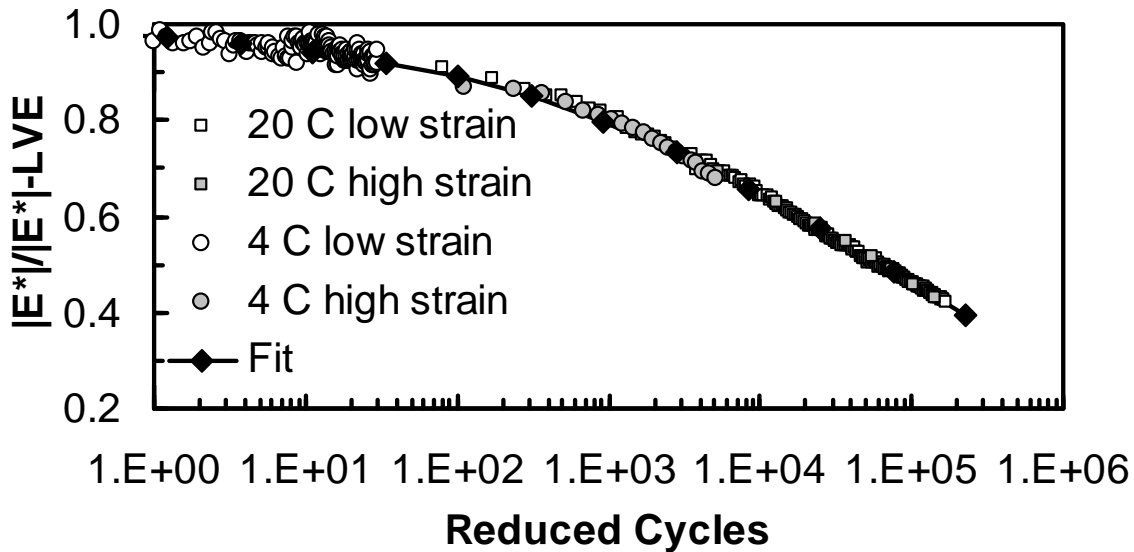


Figure 16. Typical Damage Relationship From Continuum Damage Analysis.

Continuum damage analysis has not been applied to pulsed fatigue tests where intermittent healing is permitted to occur. It is expected that the endurance limit will increase as the duration of rest period increases. The testing and analysis required to use continuum damage analysis to establish allowable strain limits for complete healing is summarized below:

1. Conduct dynamic modulus tests on the mixture and develop a dynamic modulus master curve and associated time-temperature shift factors.
2. Conduct cyclic direct tension controlled strain fatigue tests using various temperatures, strain levels, and rest periods.
3. Perform continuum damage analysis and determine the endurance limit for each of the test conditions.
4. Develop a relationship of the endurance limit as a function of temperature and rest period using time-temperature superposition if appropriate.
5. The endurance limit relationship developed in Step 4 is the allowable strain for full healing.

It should be noted that the allowable strains from the continuum damage analysis will likely be lower than the allowable strains developed using flexural fatigue testing and the RDEC method. The reason is the endurance limit in the continuum damage analysis is defined as the strain below which no measurable damage occurs in the mixture. The endurance limit in the RDEC approach is defined as the strain that results in less than a 50 percent reduction in the modulus of the material after an infinite number of loading cycles.

Experimental Design and Data Analysis

The two approaches are very similar. In both cases the rate of damage accumulation should depend on the HMA properties, the applied strain level, the temperature, and the duration of rest periods. The allowable strain limit for design is the strain level for specific temperatures and rest

periods where no damage accumulates in the HMA. The primary issue for both approaches is determining the testing conditions that provide for an efficient and robust analysis. This includes:

- Strain levels,
- Test temperatures,
- Duration of rest periods,
- Number of replicates.

The results of Experiments 1, 2, and 3 will provide initial estimates for the testing conditions. Data will then be collected on two mixtures from Experiment 1, one exhibiting a low healing rate and one exhibiting a high healing rate using a wider than estimated range and more intervals for each of the testing conditions. The analysis will then be repeated using a reduced data set to determine the optimum testing conditions. Tests using the optimum testing conditions will then be conducted on selected mixtures from NCHRP 9-38 and the results will be compared to the endurance limit strain levels determined in NCHRP 9-38.

Subtask D.5 Experiment 5: Estimation of Allowable Strain Levels from Mixture Composition

The final experiment that will be conducted is one to establish a predictive model to estimate allowable strain levels from mixture composition. This is an extremely important experiment for two reasons. First, it is unlikely that original materials or appropriate size field specimens will be available from the calibration pavement sections; therefore, estimates of allowable strain levels will be needed for the Task E analyses. Using the models developed in Experiment 5, estimates of allowable strain levels can be made using test data from standard tests on a small number of cores removed from the pavement sections. Second, a method of estimating allowable strain levels will also be needed for use in Level 2 and 3 design with the modified version of the MEPDG. The testing and analysis procedure developed in Experiment 4 will provide methods for Level 1 analysis. The predictive model developed in Experiment 5 will provide relationships for Level 2 and Level 3 analyses.

Experiment Design

Regression analysis will be used to develop a predictive model to estimate allowable strain levels from mixture composition. In Experiment 5 a database of allowable strains and mixture properties will be assembled by performing the analysis developed in Experiment 4 on a representative sample of HMA base course mixtures. Since it is envisioned that the model will be used for both analysis of existing pavements and the design of future pavements, the mixtures tested should include past, current, and likely future features that affect HMA fatigue response and healing. For example the base course of many existing pavements was designed using Marshall compaction resulting in somewhat richer mixtures than designed today using gyratory compaction. If healing is found to be much greater in modified binders, then it may be likely that modified binders will be considered for base courses in the future, an uncommon practice today.

Guidance on the factors and their ranges to be included in Experiment 5 will be obtained from Experiment 1. As discussed previously, the following factors have been identified as potentially affecting the allowable strain levels:

- Binder grade
- Binder modification
- Aging
- Effective Binder Content
- Air Voids
- Design Compaction
- Gradation
- Filler Content

The purpose of Experiment 1 is to narrow this list to the factors that significantly affect the fatigue damage and healing characteristics of HMA. The results of Experiment 1 and a review of past and current mixture design and mixture production specifications will be used to determine the specific factors and the ranges that must be included in Experiment 5. It is envisioned that approximately 30 mixtures will be tested in Experiment 5. It is not necessary

that Experiment 5 be a full or partial factorial design. The major experimental design requirements are that (1) the mixtures that are selected to be representative of base courses (2) they span the desired range of each important factor, and (3) at least three levels are included for each factor so that non-linear analyses can be made.

Data Analysis

The database of allowable strains and associated mixture compositional properties will be analyzed using graphical and regression techniques. First scatter plots will be prepared for each of the factors included in the experiment to determine appropriate mathematical functions for the model. At this point consideration will be given to using a more general factor that combines some of the individual factors. For example, the effects of binder grade and aging could both be addressed using the rheological index obtained from a binder master curve. Or the effects of air voids and effective binder content could both be addressed using the voids in the mineral aggregate or voids filled with asphalt. Additionally, consideration will be given to using easily measured or estimated mechanical properties such as indirect tensile strength or modulus.

Once appropriate model forms have been identified using graphical analysis, a regression analysis will be performed to determine the model coefficients. Most likely the relationships will be non-linear resulting in the need to use numerical optimization. Several statistical packages are available for performing non-linear regression analyses.

The final step in the process, which is often overlooked, is to evaluate the appropriateness of the model. There are several analyses that must be performed to evaluate the model including:

- 1. Goodness of Fit.** Two measures of the goodness of fit of the model should be evaluated. The first is the square of the correlation coefficient, R^2 , which is the percentage of the variance of the criterion variable explained by the predictor variables. The second measure of the goodness of fit of the model is the standard error of estimate, S_e , which is the standard deviation of the errors. The standard error of estimate has the same units as the criterion, and its magnitude is a direct indicator of the model errors. If the model

provides a good prediction, the standard error of estimate should be much lower than the standard deviation of the data used to fit the model.

2. **Statistical Significance of the Predictor Variables.** Only statistically significant predictor variables should be included in the model. If predictor variables that are not statistically significant are included, then irrational effects may be predicted for important predictor variables. The standard error of the parameter estimates should be used in a t-test to determine if each of the model parameters is significantly different from zero.
3. **Residual Analysis.** An analysis of the residuals or errors should always be performed to ensure that the underlying assumptions of regression analysis are not violated by the model. The model errors should (1) be independent, (2) have zero mean, (3) have a constant variance across all predictor variables, and (4) be normally distributed. Plots of the residuals as a function of the predictor variables should be used to identify bias in the model and to identify potential violations of the underlying regression assumptions.
4. **Reliability of the Model.** Confidence intervals should be constructed to assess the reliability of the model. Since the model will be used to predict properties for design and analysis, the width of prediction intervals for the model are of primary concern. The prediction interval is the confidence interval associated with the prediction of a future value.

Task D Milestones

Table 20 summarizes the major milestones for Task D. These are all associated with the design, execution, and analysis of the five laboratory experiments.

Table 20. Major Task D Milestones.

Milestone	Description	Months After Contract Award
D.1	Select Analysis Approach and Prepare Detailed Work Plan for Experiment 1	5
D.2	Complete Experiment 1	8
D.3	Detailed Work Plan for Experiments 2	8
D.4	Complete Experiment 2	10
D.5	Detailed Work Plan for Experiment 3 and Experiment 4	10
D.6	Complete Experiment 3	11
D.7	Complete Experiment 4	13
D.8	Detailed Work Plan for Experiment 5	13
D.9	Complete Experiment 5	21

Task D Labor Estimate

Table 21 presents the estimated labor required for Task D. Table 21 presents estimated labor hours for each of the positions in the research management structure presented in Table 5 and for laboratory technicians. Task D is estimated to require a total of 3,893 man-hours of effort. This is approximately 30 percent of the total effort required for the project.

Table 21. Estimated Labor Hours for Task D.

Subtask	Principal Investigator	Statistician	Laboratory Team Leader	Pavement Team Leader	Data Support Team Leader	Technicians
Experiment 1: Mixture Compositional Factors Affecting Healing	4	4	34	0	0	388
Experiment 2: Effect of Applied Strain on Healing	4	4	24	0	0	214
Experiment 3: Effect of Temperature and Rest Period Duration on Healing	8	4	57	0	0	242
Experiment 4: Testing and Analysis Procedures for Allowable Strain Levels	54	16	98	0	0	392
Experiment 5: Estimation of Allowable Strain Levels from Mixture Composition	146	40	270	0	0	1890
Total	216	68	483	0	0	3126

Task D Sources

HMA Fatigue

Christensen, D.W., and Bonaquist, R.F., “Volumetric Requirements for Superpave Mix Design,” **NCHRP Report 567**, National Cooperative Highway Research Program, Washington, D.C., 2006.

Rao Tangella, S.C.S., Craus, J., Deacon, J.A., and Monismith, C.L., “Summary Report on Fatigue Response of Asphalt Mixtures,” **Report Number SHRP-A/IR-90-011**, Strategic Highway Research Program, Washington, D.C., 1990.

Shook, J. F., F. N. Finn, M. W. Witzak, and C. L. Monismith, “Thickness Design of Asphalt Pavements—The Asphalt Institute Method,” **Proceedings, Fifth International Conference on the Structural Design of Asphalt Pavements**, Vol. 1, The University of Michigan and The Delft University of Technology, August 1982

University of California, Berkeley, Asphalt Research Program, Institute of Transportation Studies, *Fatigue Response of Asphalt-Aggregate Mixes*, **Report SHRP-404**, Washington, D.C.: National Research Council, 1994.

Walubita, L.F., Epps-Martin, A., Jung, S. H., Glover, C. J., Park, E.S., Chowdhury, A., and Lytton, R. L., “Comparison of Fatigue Analysis Approaches for Two Hot Mix Asphalt Concrete (HMAC) Mixtures,” **Report Number FHWA/TX-05/0-4468-2**, Texas Department of Transportation, Austin, TX, August, 2005.

Healing in HMA

Influence of Rest Periods on the Fatigue Response of Bituminous Mixes,” **Proceedings, Association of Asphalt Paving Technologists**, Vol. 51, 1982.

Carpenter, S.H., and Shen, S., “Application of the Dissipated Energy Concept in Fatigue Endurance Limit Testing,” **Transportation Research Record No. 1929**, Transportation Research Board, Washington, D.C., 2005.

Kim, B. and Roque, R., “Evaluation of Healing Property of Asphalt Mixtures,” **Transportation Research Record No. 1970**, Transportation Research Board, Washington, D.C., 2006.

Kim, Y.R., Little, D.N., and Benson, F.C., “Chemical and Mechanical Evaluation of Healing of Asphalt Concrete,” **Journal of the Association of Asphalt Paving Technologists**, Vol. 59, 1990.

Little, D. N., Lytton, R. L., Williams, D., and Chen, C. W., “Microdamage Healing in Asphalt and Asphalt Concrete, Volume I: Microdamage and Microdamage Healing Project Summary Report,” **Report Number FHWA-RD-98-141**, Federal Highway Administration, Washington, D.C., June 2001.

Pronk, A.C., "Partial Healing, "A New Approach for the Damage Process During Fatigue Testing of Asphalt Specimens," **Asphalt Concrete Simulation, Modeling, and Experimental Characterization**, Geotechnical Special Publication No. 146, American Society of Civil Engineers, Reston, VA, 2005.

Ratio of Dissipated Energy Change

Carpenter, S.H., Ghuzlan, K.A., and Shen, S., "Fatigue Endurance Limit for Highway and Airport Pavements," **Transportation Research Record No. 1832**, Transportation Research Board, Washington, D.C., 2003.

Carpenter, S.H., and Shen, S., "Application of the Dissipated Energy Concept in Fatigue Endurance Limit Testing," **Transportation Research Record No. 1929**, Transportation Research Board, Washington, D.C., 2005.

Carpenter, S.H., and Shen, S., "Dissipated Energy Approach to Study Hot-Mix Asphalt Healing in Fatigue," **Transportation Research Record No. 1970**, Transportation Research Board, Washington, D.C., 2006.

Prowell, B., Brown, E., R., Daniel, J., Bhattacharjee, S., Von Quintus, H., Carpenter, S., Shen, S., Anderson, M., Swamy, A. K., and Maghsoodloo, S., "Endurance Limit of Hot Mix Asphalt Mixtures to Prevent Fatigue Cracking in Flexible Pavements," Updated Draft Final Report, NCHRP 9-38, National Cooperative Highway Research Program, Washington, D.C., May, 2008.

Continuum Damage Analysis

Christensen, D.W., and Bonaquist, R.F., "Practical Application of Continuum Damage Theory to Fatigue Phenomena in Asphalt Concrete Mixtures," **Journal of the Association of Asphalt Paving Technologists**, Vol. 74, 2005

Kim, Y. R. and Little, D. N. "One Dimensional Constitutive Modeling of Asphalt Concrete," **ASCE Journal of Engineering Mechanics**, Vol. 116, No. 4, 1990

Kim, Y. R., Little, D. N., and Lytton, R. L., "Use of Dynamic Mechanical Analysis (DMA) to Evaluate the Fatigue and Healing Potential of Asphalt Binders in Sand Asphalt Mixtures," **Journal of the Association of Asphalt Paving Technologists**, Vol. 71, 2002

Kim, Y.R., Lee, H. J., and Little, D. N., "Fatigue Characterization of Asphalt Concrete Using Viscoelasticity and Continuum Damage Theory," **Journal of the Association of Asphalt Paving Technologists**, Vol. 66, 1997.

Lee, H. J., and Kim, Y. R. "A Uniaxial Viscoelastic Constitutive Model for Asphalt Concrete Under cyclic Loading," **ASCE Journal of Engineering Mechanics**, Vol. 124, 1998, No. 11.

Statistical Analysis

American Society for Testing Materials, “ASTM Designation E 1169-02: Standard Guide for Conducting Ruggedness Tests,” **Annual Book of ASTM Standards**, Vol. 14.02.

Statistica for Windows. [Computer software]. StatSoft, Inc., Tulas, Oklahoma, 1994.

Task E. Analysis of Pavement Sections

The final task in the HMA Endurance Limit Validation Study is an analysis of full-scale pavement sections using the allowable strain limit design procedure formulated in Task 2 and improved through the laboratory experiments in Task D. Two types of full-scale pavement sections will be analyzed. First data from selected accelerated pavement tests and test roads will be used to test critical elements of the procedure. These include the effects of temperature, applied strain, and material properties on the allowable strain levels. Results from these analyses will be used to further improve the allowable strain limit design procedure for use in analysis of the second type of full-scale pavement: in-service pavement sections. For the in-service pavements, both cracked and uncracked pavements will be analyzed. These analyses will be used to calibrate the procedure and serve as validation of the concept of an endurance limit for flexible pavement design. It is important to recognize that the allowable strain limit design procedure is not intended to be a tool for predicting the extent of bottom initiated cracking with time and traffic like the MEPDG fatigue model. Its purpose is to identify design features that minimize the possibility of bottom initiated fatigue cracking. Thus field calibration of the allowable strain limit design procedure will be easier and likely more precise than the calibration that was completed for the MEPDG fatigue model. Task E has been divided into five subtasks:

- E.1 Review Data Sources and Select Sections for Analysis
- E.2 Obtain Materials and Data for Accelerated Pavement Tests and Test Roads
- E.3 Perform Testing and Analyze Accelerated Pavement Tests and Test Roads
- E.4 Obtain Materials and Data for In-Service Pavement Sections
- E.5 Perform Testing and Analyze In-Service Pavement Sections

Each of these subtasks are described in detail below.

Subtask E.1 Review Data Sources and Select Sections for Analysis

In this subtask the sources identified in this research plan will be reviewed considering the final preliminary approach developed in Subtask 2.2 and specific pavement sections will be selected for subsequent analysis. Subtask E.1 will begin immediately after the preliminary approach is finalized in Subtask 2.2. Initial selection of sections for analysis will be documented in the second interim report that will be submitted at the end of the 13th month of the project. This initial selection will be reviewed as results from the laboratory experiments become available and adjusted as needed. Two types of full-scale pavements: accelerated pavement tests and test roads, and in-service pavements will be selected for analysis. The sections that follow describe specific pavement sections that are recommended for consideration in Task E.

Accelerated Pavement Tests and Test Roads

Selected, well documented accelerated pavements tests and test roads will serve the important role of verifying critical aspects of the allowable strain limit design procedure. Specific elements of the procedure that can be verified include:

1. The overall engineering reasonableness of the approach,
2. Applicability of time-temperature superposition to healing and allowable strains,
3. Independence of healing on applied strain, and
4. Effect of material properties on allowable strains.

Although there are now a number of accelerated pavement testing devices and test road facilities in the United States, few of the testing programs have addressed fatigue of HMA in a structured manner. For flexible pavements, accelerated pavement testing has mostly been used to investigate rutting in HMA surfaces, or to evaluate specific materials or design features. Only four projects were identified where structured, full-scale testing was conducted that is useful in verifying the above aspects of the allowable strain limit design procedure. The following projects are recommended for analysis:

- Fatigue tests conducted during the Superpave validation study at the FHWA Pavement Test Facility (50).
- Sections at the NCAT Test Track that have remained in service from the first cycle through the current cycle (51).
- Sections from the WesTrack experiment containing mixtures with different composition (41).
- Sections from the structural design experiment performed at the NCAT Test Track (52, 53).
- Selected sections from the MNRoad project (54).

Although the MNRoad sections are actually in-service pavements loaded with normal traffic, they are included in the verification studies because there are a number of sections that can be analyzed and all of the sections are exposed to the same environmental conditions. If MNRoad sections are included in the calibration, then only a limited number of sections can be used, otherwise the analysis will be biased toward the environmental and construction conditions at MNRoad. The sections that follow describe analyses that should be conducted considering the preliminary design approach described in Task 2.

Overall Engineering Reasonableness

All of the accelerated pavement tests will be used to judge the engineering reasonableness of the allowable strain limit design procedure. An analysis of each section using the procedure should provide the correct conclusion concerning cracking in the pavement. For sections that have cracked, the analysis should show that the allowable strain levels were exceeded. For sections that have not yet cracked, such as the first cycle sections at the NCAT Test Track that remain in-service, the analysis should show that the allowable strain levels were not exceeded.

It should be noted that the allowable strain limit design procedure developed in Task 2 does not require the pavement to exhibit endurance limit behavior. Equations 8 and 9 in Task 2 can be solved for the allowable strains for any number of loading cycles. Endurance limit behavior occurs when the number of cycles to failure exceeds 1.1×10^7 . This will be very useful for analysis of the structural sections at the NCAT test track. Table 22 presents the HMA

thicknesses in the NCAT structural sections (51). For the materials used in the base course of these sections, analysis can be done assuming endurance limit behavior, then the analysis can be repeated using the observed load cycles to failure and the allowable and actual strains can be compared.

Table 22. HMA Thicknesses in NCAT Structural Sections

Section	2003 Construction		2006 Construction	
	HMA Thickness, in	HMA Base Binder	HMA Thickness, in	HMA Base Binder
N1	5	Polymer 76-22	7	Neat PG 67-22
N2	5	Neat 67-22	7	Polymer 76-22
N3	9	Neat 67-22	NA	NA
N4	9	Polymer 76-22	NA	NA
N5	7	Polymer 76-22	7	Neat PG 67-22
N6	7	Neat 67-22	NA	NA
N7	7	Neat 67-22	NA	NA
N8	7 (rich bottom)	Neat 67-22	10	Polymer 76-28
N9	NA	NA	14	Polymer PG 76-28
N10	NA	NA	8	Polymer PG 70-22

The MNRoad sections also provide the opportunity to perform a systematic analysis of the overall reasonableness of the approach for pavements of different thickness and composition exposed to the same traffic and environment. At MNRoad, sections were constructed using different thicknesses, design compaction levels, and binders. Table 23 summarizes the main line HMA cells at MNRoad that could be used in the verification analyses (54). Although bottom initiated fatigue cracking was not reported as a distress for any of the HMA sections in the last condition report (55), the pavements have received seven years of additional traffic and selected sections will remain in service after reconstruction is completed in 2008 and 2009 (54).

Table 23. Summary of MNRoad Mainline HMA Pavement Sections.

Section	HMA Thickness, in	Design Compaction	Binder
1	6.0	75 Blow Marshall	PG 58-28
2	6.1	35 Blow Marshall	PG 58-28
3	6.3	50 Blow Marshall	PG 58-28
4	9.1	Gyratory	PG 58-28
14	10.9	75 Blow Marshall	PG 58-28
15	11.1	75 Blow Marshall	PG 64-22
16	8.0	Gyratory	PG 64-22
17	7.9	75 Blow Marshall	PG 64-22
18	7.9	50 Blow Marshall	PG 64-22
19	7.8	35 Blow Marshall	PG 64-22
20	7.8	35 Blow Marshall	PG 58-28
21	7.9	50 Blow Marshall	PG 58-28
22	7.9	75 Blow Marshall	PG 58-28
23	8.2	50 Blow Marshall	PG 58-28

Applicability of Time-Temperature Superposition to Rest Periods

The fatigue experiment that was conducted during the Superpave validation study at the FHWA Pavement Testing Facility provides an excellent opportunity to validate that application of time-temperature superposition to rest periods. In this study, accelerated pavement tests were conducted with the FHWA Accelerated Loading Facility on two pavements at three different pavement temperatures. The tests were performed when ambient air temperatures were low. An infrared heating system was used to maintain the pavement temperatures (50). Table 24 summarizes the tests that were performed. Analysis of these tests at different temperatures using the allowable strain limit design procedure will provide validation of the use of time-temperature superposition to model HMA healing effects.

Table 24. FHWA Pavement Testing Facility Superpave Fatigue Experiment.

HMA Thickness, mm	Binder	Load, kN	10 °C	19 °C	28 °C
100	AC-5	53	X	X	X
	AC-20	53	X	X	X
200	AC-5	53	X	X	X
	AC-20	53	X	X	X

The instrumented structural sections at the NCAT Test Track can be used to evaluate the effect of damage and healing during different temperature conditions. Measured strains and deflections in these sections can be used to determine the effects of rest periods on healing at different temperatures. Within the current loading experiment, four of the structural test sections are instrumented.

Independence of Healing on Strain Level

The FHWA Superpave validation study fatigue experiments also provide the opportunity to verify that healing is independent of strain level. Since the same mixtures were tested at the same temperature and load in two different pavement structures, the effect of strain level on healing can be evaluated. The thicker pavement has significantly lower tensile strains at the bottom of the HMA compared to the thinner pavement. The structural sections at the NCAT Test Track and sections at MNRoad where the same base course material was used in pavements of different thicknesses can also be used to verify that healing is independent of strain level.

Effect of Material Properties on Allowable Strains

All four recommended projects can be used to assess how well the allowable strain limit design procedure addresses the effect of changes in mixture composition. The WesTrack experiment included variations in gradation, filler content, binder content, and in-place density (41). A single asphalt binder and aggregate source were used in the original sections. In the replacement sections a different aggregate was used (41). As shown in Table 22, the structural sections at the NCAT Test Track includes pavements of the same thickness made with a polymer modified PG 76-22 binder and a neat PG 67-22 binder. The FHWA experiment included two neat binders, AC-5 and AC-20. Finally as shown in Table 23, the MNRoad project includes sections of the same thickness designed with different compaction and two different binders.

The predictive model developed in Experiment 5 of Task D addresses the effect of material properties on allowable strains. The effects predicted by this model can be compared to the observed effects within each of the experiments.

In-Service Pavement Sections

Calibration of the allowable strain limit design procedure will be performed using in-service pavements. Analyses will be conducted for a number of sections, both cracked and uncracked, using the procedure. Sections from the LTPP program (56) and pavements that have received perpetual pavement awards from the Asphalt Pavement Alliance (57) were considered for use in the calibration. The LTPP sections were selected because these sections have received extensive monitoring over a number of years, and distress, deflection, and material property data are available from the LTPP database (56). Since sufficient sections for the analysis are available from the LTPP program, only these sections are included in this research plan.

LTPP Sections

In NCHRP Project 9-38, analyses were conducted using data from the LTPP database to determine if an endurance limit for HMA could be identified from field data (6). The following assumptions were made in these analyses:

1. Alligator cracking reported in the LTPP database initiated at the bottom of the section.
2. Wheel path longitudinal cracking reported in the LTPP database initiated at the surface.
3. The endurance limit can be defined by a single value of strain that is independent of temperature, mixture modulus, and type of mixture.

From these analyses, an endurance limit could not be definitively identified. The NCHRP 9-38 research team hypothesized that one of the reasons why an endurance limit could not be defined is that the endurance limit is mixture composition dependent and it varies with temperature.

Figures 18 and 19 compare the amount of fatigue cracking (percent of wheel path area) from the most recent LTPP distress survey with HMA thickness and maximum tensile strain at the bottom of the HMA, respectively. As shown and expected, the test sections with thinner HMA layers and higher tensile strains generally exhibit more fatigue cracking.

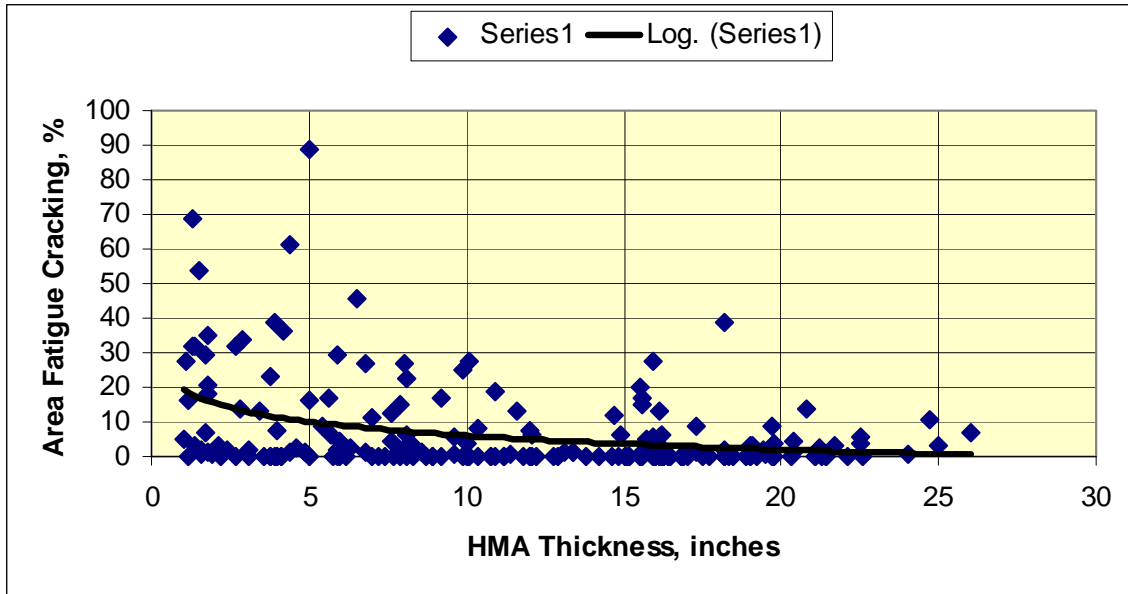


Figure 17. Comparison of Area Fatigue Cracking (Area Alligator Cracking Based on a Percent of Wheel Path Area) and HMA Layer Thickness (6).

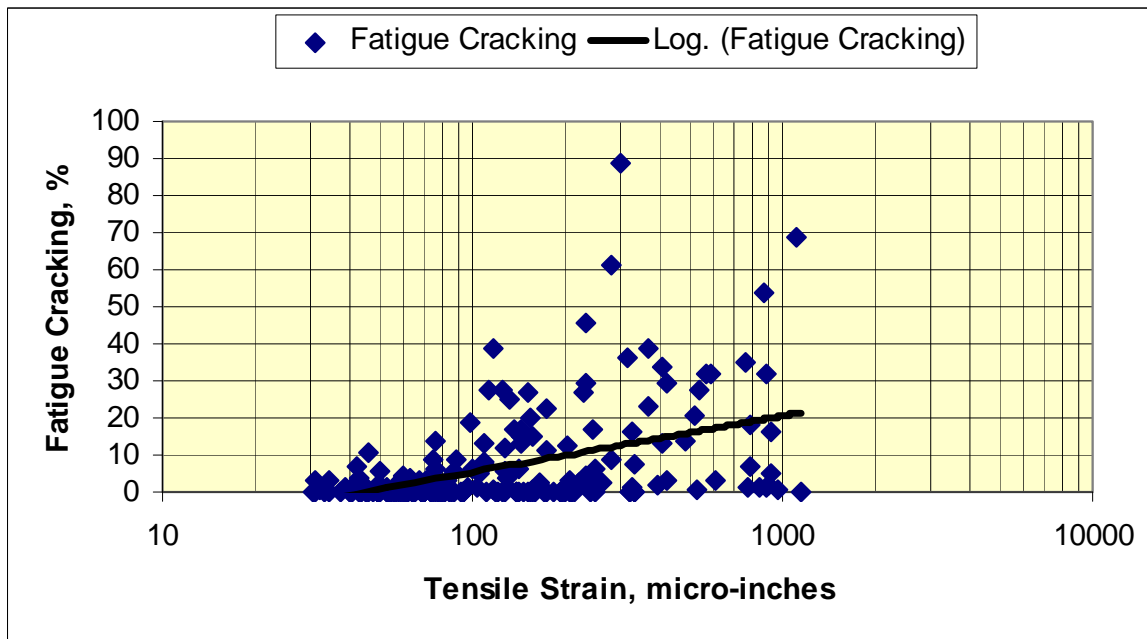


Figure 18. Comparison of the Area Fatigue Cracking for and Maximum Tensile Strain Computed at the Bottom of the HMA Layer (6).

A number of test sections with thick HMA layers and low tensile strains, however, have levels of fatigue cracking exceeding 5 percent. Reasons given for the cracking in these sections included (6):

- Misclassification of longitudinal cracking as alligator cracking.
- The presence of construction defects, such as high air voids, debonding of layers, etc.
- Moisture damage in the section,
- The endurance limit is dependent on the quality of the HMA base; therefore, sections with poor HMA base quality require lower strains to exhibit endurance limit behavior.

Forensic evaluation of the thick HMA sections with reported alligator cracking was recommended for future endurance limit validation studies.

An observation of the data in Figures 18 and 19 that was not made by the NCHRP Project 9-38 research team is the pavements in the LTPP database are generally properly designed to resist fatigue cracking for the level of traffic that they have received. This is indicated by the large number of sections having zero alligator cracking. This is particularly true for pavements having maximum tensile strains at the bottom of the asphalt layer below about 100 microstrain when calculated using the equivalent annual layer moduli for each pavement layer. Figure 20 presents a plot of tensile strain at the bottom of the asphalt layer versus HMA layer thickness that was used to develop Figure 19. From Figure 20 tensile strains of 100 microstrain correspond to approximately 10 inches of HMA, which is similar to the thicknesses reported for the heavily trafficked pavements in the United Kingdom having no evidence of bottom initiated fatigue cracking (9). This observation suggests that the thick sections with high levels of alligator cracking likely contain construction defects and should not be included in the calibration of the allowable strain limit design procedure. Forensic evaluation of these sections should definitely be conducted, but not as part of the HMA Endurance Limit Validation Study.

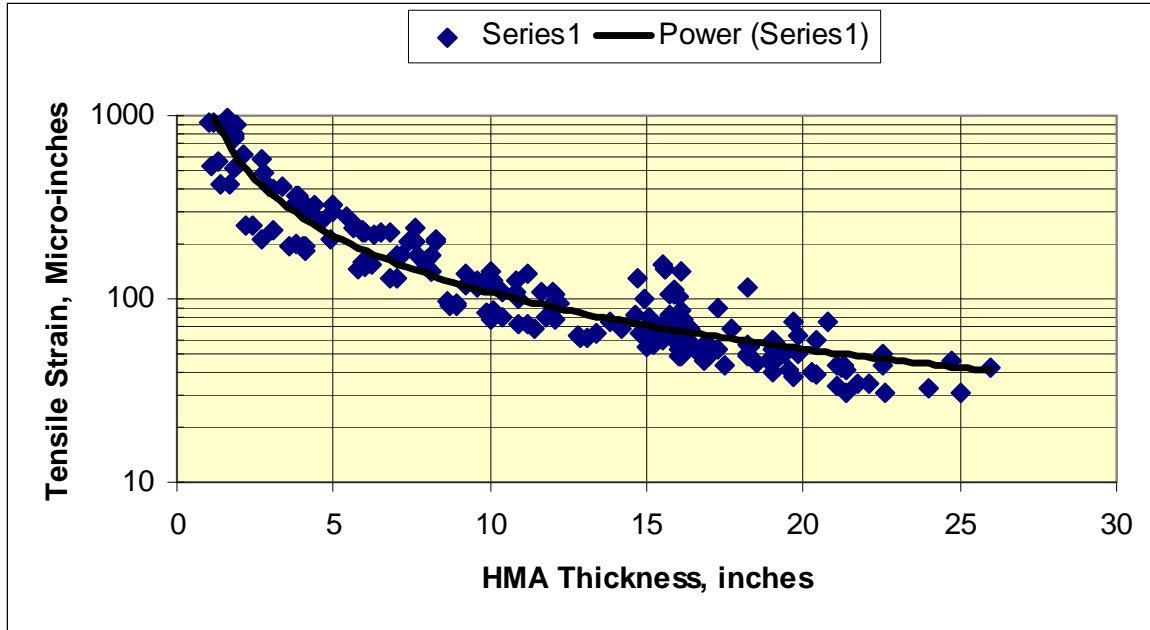


Figure 19. Comparison of the Maximum Tensile Strain at the Bottom of the HMA Layer and HMA Thickness (6).

Table 25 presents the preliminary test matrix for using LTPP sections to calibrate the allowable strain limit design procedure. Since the procedure is not intended for prediction of the extent of cracking in a pavement section, but rather as a tool to identify design features to minimize the potential for bottom initiated fatigue cracking, an extremely large data set is not required. The recommended matrix includes a total of 32 pavement sections: 16 not exhibiting alligator cracking and 16 exhibiting low to moderate amounts of alligator cracking. An equal number of sections from the four environmental zones are included in the matrix. Only pavements with HMA thicknesses exceeding 8 inches are included. Subgrade deformation becomes an important consideration in thinner HMA pavements.

Table 25. Preliminary Matrix for Field Calibration of the Allowable Strain Limit Design Procedure.

Environment	HMA Thickness, in	No Alligator Cracking	Low Alligator Cracking
Wet Freeze	8 to 12	2	2
	>12	2	2
Wet No Freeze	8 to 12	2	2
	>12	2	2
Dry Freeze	8 to 12	2	2
	>12	2	2
Dry No Freeze	8 to 12	2	2
	>12	2	2

Table 26 presents a summary of applicable LTPP sections for each of the cells in the experimental matrix. Information from the LTPP database on these sections and others that may be considered is presented in Appendix A. Specific sections to be included in the calibration effort will be selected in Subtask E.1. Items that should be considered in the final selection include:

- Current status of the section (active or out of service).
- Willingness of the state agency to assist with providing traffic control for distress verification and seismic testing, and to provide limited coring to investigate cracking and obtain samples for laboratory testing.
- Consistency of time series distress data for the section in the LTPP database.
- Consistency of time series deflection data for uncracked sections.
- Availability of traffic information or an estimate of traffic for the section.

Table 26. LTPP Sections Recommended for Consideration.

Climate	HMA Total Thickness, in.	Fatigue or Alligator Cracking	
		None	Appreciable
Wet-No Freeze	8 to 12	12-0101; 12-0103; 22-0114; 40-0160	01-0101; 05-0114; 12-0107; 40-0114
	>12	05-3071; 12-0106; 12-0104; 13-4113; 22-0116; 40-0115	01-0111; 05-0115; 05-0116
Dry-No Freeze	8 to 12	35-0111; 35-0103; 35-0107	04-0162; 48-1070
	>12	04-1065; 35-0106; 48-0116	04-1062; 04-0116
Dry-Freeze	8 to 12	32-0101; 32-0105	16-9034; 30-0114; 32-0103
	>12	31-0115; 31-0116; 32-0106; 32-0104	30-0116; 30-0115; 30-0124
Wet-Freeze	8 to 12	19-0101; 19-0105; 55-01114; 55-C901	19-0103; 55-C960
	>12	19-0112; 26-0115; 39-0902; 55-0116	39-0106; 39-0112; 39-0903

Subtask E.2 Obtain Materials and Data for Accelerated Pavement Tests and Test Roads

The primary activity required in Subtask E.2 is extracting the data required for analysis of the accelerated pavement tests and test road sections from various research reports. This includes information on the pavement structure, loading, environmental conditions, material properties, and distress for each section that will be analyzed. The data will be entered into the database and managed in Subtask C.2.

The inputs needed to apply the allowable strain limit design procedure to accelerated pavement tests and test roads are similar to those required for current mechanistic-empirical design, such as the MEPDG. Table 27 summarizes the required inputs. The elements in bold in Table 27 are ones required by the allowable strain limit design procedure that are not included in current mechanistic-empirical analysis. Since mechanistic-empirical pavement analyses were included in the recommended projects, most of the information needed for the analyses are in published reports for the projects or available from the project websites (41, 50, 51, 52, 53, 54, 58).

Table 27. Summary of Required Inputs for Allowable Strain Limit Design.

Category	Required Input
Pavement Structure	Layer thicknesses Layer moduli Layer Poisson's ratios Mixture composition and binder properties for HMA base
Traffic	Axle configuration Tire configuration Tire loads Tire pressure Speed Wander Rest Period
Environmental	Pavement temperature history Base modulus history Subgrade modulus history

It is envisioned that the model for predicting allowable strains in HMA developed in Experiment 5 of Task D will relate allowable strains to mixture composition and binder properties. The required mixture composition data are available in the published research reports; however, it is expected that binder properties in addition to the performance grade of the binder will be required. Extensive testing of the binders used in the FHWA Superpave validation study, WesTrack, and MNRoad was completed during NCHRP Project 9-19 (59, 60, 61). Therefore, the only material sampling and testing that will be needed for analysis of the accelerated pavement tests and test roads will be characterization of the binders used in the structural sections at the NCAT Test Track. One quart samples of these binders will be requested from NCAT or the test section sponsors.

The required performance data for the recommended projects are included in published reports. Updated information on performance of the MNRoad test sections is available by request through the MNRoad website (54). Traffic loading for the 2006 sections included in the structural sections at the NCAT Test Track is scheduled for completion in the Fall of 2008 (51).

Subtask E.3 Perform Lab Testing and Analyze Accelerated Pavement Tests and Test Roads

The only laboratory testing envisioned in Subtask E.3 is further characterization of the binders used in the structural test sections from the NCAT test track. It is unlikely that master curves characterizing the flow characteristics of the binders over a wide temperature range and for various aging conditions are available; therefore, they will have to be developed. Master curves are developed by testing the binder at multiple temperatures and frequencies using the dynamic shear rheometer, AASHTO T315, and conducting bending beam rheometer tests, AASHTO T313, at multiple temperatures.

For each accelerated pavement test and test road section, an analysis will be performed with the research version of the MEPDG software, NCHRP9-44A_Version 0.2, using section specific material properties, loading, and environment. Two analyses will be performed. For all sections an analysis will be conducted to determine the allowable strains that will produce endurance limit behavior (full healing). Then, for those sections that have exhibited cracking an analysis will be performed using the observed cycles to first cracking. Comparisons will be made within projects and between projects to verify the following aspects of the allowable strain limit design procedure:

- The overall engineering reasonableness of the approach,
- Applicability of time-temperature superposition to healing and allowable strains,
- Independence of healing on applied strain, and
- Effect of material properties on allowable strains.

Pertinent interim results from these analyses will be discussed in the quarterly progress reports. The analyses will be thoroughly documented in the fourth interim report submitted at the end of the 30th month of the project.

Subtask E.4 Obtain Materials and Data for In-Service Pavement Sections

In this Subtask, data and materials needed to analyze each of the LTPP sections included in the final matrix of in-service pavements will be obtained. First, the most recent data for the test

section will be retrieved from the LTPP database (56). This data will be entered into the project database and managed under Subtask C.2. The relevant data for the analyses include:

- Traffic.
- Time-series deflection data.
- Time-series fatigue cracking.
- Time-series longitudinal cracking.
- Layer material properties.

A site visit to each of the selected pavement sections is required. The site visit will include:

1. A visual condition survey to confirm the distresses obtained from the LTPP database,
2. Non-destructive testing at various locations in the section using the Portable Seismic Pavement Analyzer (PSPA) (62, 63) to identify damage in the base layers that is not apparent from surface distress measurements.
3. Coring to obtain 3 to 5 full depth samples for laboratory testing, and
4. Additional coring to confirm the distress survey and seismic testing. If cracks are present, cores will be taken through selected cracks to confirm where the cracks initiated and confirm the cause of cracking.

Each site visit will require two full days. It is envisioned that the necessary traffic control and coring will be provided by the state highway agencies. Their willingness to participate in the field testing is an important consideration in the final selection of pavements for analysis.

Subtask E.5 Perform Lab Testing and Analyze In-Service Pavement Sections

Laboratory Testing

The pavement section cores will be used to determine modulus values for analysis of the seismic test data and to obtain the properties of the HMA base for use in the predictive model developed in Experiment 5 of Task D. This model will relate allowable strains for full healing to easily measured volumetric properties of the mixture and flow characteristics of the binder. Mixture properties will be obtained from normal volumetric analysis of the cores. The binder

will be recovered to determine the required binder properties. A preliminary testing plan is presented in Table 28 assuming that an indirect tensile strength will be used in the model and a binder master curve will be required to characterize the flow properties of the binder in the predictive model developed in Experiment 5 of Task D.

Table 28. Preliminary Testing Plan for Cores From the LTPP Sections.

Test	Method	Number	Reason
Bulk specific gravity	AASHTO T169	3	Volumetric properties
Indirect Tensile Modulus	Modified AASHTO T322	3	Analysis of seismic data
Indirect Tensile Strength	AASHTO T322	3	Mixture strength
Asphalt content	AASHTO T164	3	Volumetric properties
Sieve analysis	AASHTO T30	3	Gradation
Aggregate bulk specific gravity	AASHTO T84 AASHTO T85	1 1	Volumetric properties
Binder Recovery	AASHTO T170	3	Obtain binder for rheological testing
Dynamic Shear Rheometer	AASHTO T315	Frequency sweep at 6 temperatures	Binder master curve
Bending Beam Rheometer	AASHTO T313	3 temperatures	Binder master curve

Analysis

Analysis of the LTPP sections will be performed using the research version of the MEPDG software, NCHRP9-44A_Version 0.3, developed in Subtask 2.4. The analysis will involve performing simulations for each of the 32 pavement sections to determine the frequency at which the allowable strains for full healing (endurance limit behavior) are exceeded. For all of the simulations, the best available information on the traffic and unbound layers will be used.

Since the field data consists of cracked and uncracked sections, the analysis will produce binary data (either cracked or uncracked) as shown schematically in Figure 21. From this data a model for the probability that bottom initiated cracking will occur can be developed using the logistic function given in Equation 32.

$$p = \frac{e^{[b_0 + b_1(PE)]}}{1 + e^{[b_0 + b_1(PE)]}} \quad (32)$$

where:

p = probability of bottom initiated fatigue cracking

PE = percent of axle loads with strains exceeding the endurance limit

b_0 and b_1 = fitting parameters

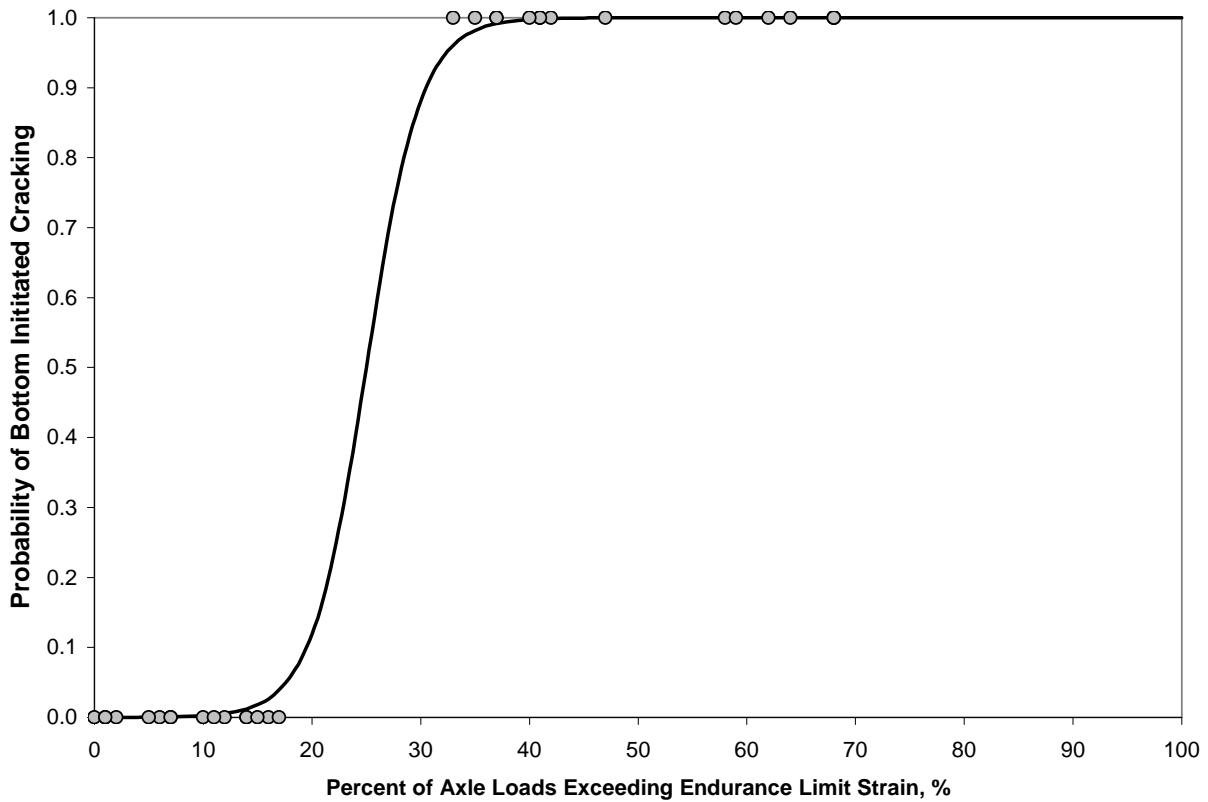


Figure 20. Schematic of Field Section Data Analysis.

Jackknifing as described in Research Results Digest Number 283 (64) can be used to assess the accuracy of the of the model coefficients without having to separate the 32 sections into calibration and validation subsets. Jackknifing is performed by systematically removing one of the sections, calibrating the model using the remaining sections, then predicting the value of the section that was removed. For the section that was removed, the model error, e_i , is computed as the difference between the predicted and measured values. The process of withholding,

calibrating, and determining the error is repeated until each section has been removed. This process produces n values of the error from which the following jackknifing goodness of fit statistics can be computed.

$$S_e = \left[\frac{1}{v} \sum_{i=1}^n e_i^2 \right]^{0.5} = \left[\frac{1}{v} \sum_{i=1}^n (\hat{Y}_i - Y_i)^2 \right]^{0.5} \quad (33)$$

where

S_e = standard error

e_i = errors computed from jackknifing

n = number of measurements taken

v = degrees of freedom = n minus number of unknowns

\hat{Y}_i = predicted value for the i^{th} jackknifing set

Y_i = measured value for the i^{th} jackknifing set

$$R^2 = 1 - \left[\left(\frac{S_e^2}{S_y^2} \right) \left(\frac{n-p}{n-1} \right) \right] \quad (34)$$

where

R^2 = explained variance

S_e = standard error

S_y = standard deviation of the measured data

n = number of measurements taken

p = number of unknowns

$$bias = \sum_{i=1}^n e_i \quad (35)$$

where

e_i = errors computed from jackknifing

n = number of measurements taken

The advantage of jackknifing is the goodness of fit statistics are based on predictions of measurements that are not included in the calibration. They are, therefore, better estimates of the accuracy of future predictions than goodness of fit statistics based on calibration using the full data set. The stability of the model can also be assessed by performing the jackknifing again by withholding two sets of measurements and calibrating using the remaining $n-2$ measurements. For $n-2$ jackknifing, two errors are computed for each set of two measurements that are withheld. The change in the jackknifing goodness of fit statistics between $n-1$ and $n-2$ jackknifing is an indicator of the stability of the statistics. Stable goodness of fit statistics indicate a model with reliable prediction accuracy.

Pertinent interim results from these analyses will be discussed in the quarterly progress reports. The analyses will be thoroughly documented in the fifth interim report submitted at the end of the 42nd month of the project.

Task E Milestones

Table 29 summarizes the major milestones for Task E. Initially the emphasis of the project will be on the formulation of the design procedure and the laboratory testing and analysis. This provides substantial time for compiling the accelerated pavement test and test road data and for final selection of the LTPP sections. After the laboratory testing and analysis are complete, the emphasis of the project shifts to collection and analysis of the data from the LTPP sections.

Table 29. Major Task E Milestones.

Milestone	Description	Months After Contract Award
E.1	Initial Selection of Sections for Analysis	12
E.2	Final Selection of LTPP Sections for Analysis	20
E.3	Compile Data From Accelerated Pavement Tests and Test Roads	24
E.4	Complete Analysis of Accelerated Pavement Tests and Test Roads	27
E.5	Complete Data Collection for LTPP Sections	32
E.6	Complete Testing and Analysis of LTPP Sections	35

Task E Labor Estimate

Table 30 presents the estimated labor required for Task E. Table 30 presents estimated labor hours for each of the positions in the research management structure presented in Figure 5, engineering support for collection and analysis of the pavement sections, and technician support for laboratory testing. Task E is estimated to require a total of 4,900 man-hours of effort. This is approximately 38 percent of the total effort required for the project.

Table 30. Estimated Labor Hours for Task E.

Subtask	Principal Investigator	Statistician	Laboratory Team Leader	Pavement Team Leader	Data Support Team Leader	Engineers	Technicians
E.1 Review Data Sources and Select Sections for Analysis	16	8	0	28	0	320	0
E.2 Obtain Materials and Data for Accelerated Pavement Tests and Test Roads	20	0	0	28	0	280	0
E.3 Perform Lab Testing and Analyze Accelerated Pavement Tests and Test Roads	36	16	4	108	0	512	32
E.4 Obtain Materials and Data for In-Service Pavement Sections	20	0	0	100	0	1280	0
E.5 Perform Lab Testing and Analyze In-Service Pavement Sections	90	30	90	90	0	512	1280
Total	182	54	94	354	0	2904	1312

Task E Sources

FHWA Superpave Validation Study

Stuart, K.D., Mogawer, W.S., and Romero, P., “Validation of the Superpave Asphalt Binder Fatigue Cracking Parameter Using an Accelerated Loading Facility,” **Report Number FHWA-RD-01-093**, Federal Highway Administration, Washington, D.C., 2002.

NCHRP Project 9-19, “Binder Characterization, Team Report BC-4, “Rheological Characterization of the FHWA-ALF Binders,” PDF File No, 04-E, CRP-CD-46, National Cooperative Highway Research Program, 2005.

MnRoad

Minnesota Department of Transportation. <http://www.dot.state.mn.us/mnroad/> (accessed June, 2008).

Palmquist, D., Worel, B., Zerfas, W., “2002 Hot-Mix Asphalt Mainline Test Cell Condition Report,” Minnesota Department of Transportation, September 6, 2002.

Worel, B., “MnRoad Database Guide,” Minnesota Department of Transportation, January, 2006.

NCHRP Project 9-19, “Binder Characterization, Team Report BC-3, “Rheological Characterization of the MnRoad Binders,” PDF File No. 04-D, CRP-CD-46, National Cooperative Highway Research Program, 2005.

LTPP Sections

Federal Highway Administration. <http://www.ltp-products.com/DataPave/index.asp> (accessed June, 2008).

National Cooperative Highway Research Program, <http://www.trb.org/mepdg/guide.htm> (accessed June 30, 2008).

NCAT Test Track

National Center for Asphalt Technology. <http://www.pavetrack.com/> (accessed June, 2008).

Timm, D. West, R., Priest, A., Powell, B., Selvaraj, I., Zhang, J., and Brown, R., “Phase II NCAT Test Track Results,” **NCAT Report 06-05**, National Center for Asphalt Technology, Auburn University, Auburn, AL, December, 2006.

Timm, D. and Priest, A., “Material Properties of the 2003 NCAT Test Track Structural Study,” **NCAT Report 06-01**, National Center for Asphalt Technology, Auburn University, Auburn, AL, April, 2006.

Willis, J., and Timm, D., “Forensic Investigation of a Rich Bottom Pavement”, **NCAT Report 06-04**, National Center for Asphalt Technology, Auburn University, Auburn, AL, December, 2006.

Timm, D.H., Priest, A.L., and McEwen, T. V., “Design and Instrumentation of the Structural Pavement Experiment at the NCAT Test Track,” **NCAT Report 04-01**, National Center for Asphalt Technology, Auburn University, Auburn, AL, April, 2004.

Brown, E.R., Cooley, L.A., Hanson, D., Lynn, C., Powell, B., Prowell, B., and Watson, D., “NCAT Test Track Design, Construction, and Performance,” **NCAT Report 02-12**,

National Center for Asphalt Technology, Auburn University, Auburn, AL, November, 2002.

Westrack

Epps, J. A., Hand, A., Seeds, S., Schultz, T., Alavi, S., Ashmore, C., Monismith, C., Deacon, J.A., Harvey, J.T., and Leahy, R., "Recommended Performance Related Specifications for Hot-Mix Asphalt Construction: Results of the WesTrack Project," **NCHRP Report 455**, National Cooperative Highway Research Program, Washington, D.C., 2002.

NCHRP Web-Only Document 111: "Recommended Performance Related Specifications for Hot-Mix Asphalt Construction: Results of the WesTrack Project," http://onlinepubs.trb.org/onlinepubs/nchrp/nchrp_w111.pdf (accessed June, 2008).

NCHRP Project 9-19, "Binder Characterization, Team Report BC-5, "Rheological Characterization of the WesTrack Binders," PDF File No, 04-F, CRP-CD-46, National Cooperative Highway Research Program, 2005.

Seismic Pavement Analyzer

Geomedia Research and Development, <http://geomedia.us/> (accessed June, 2008)

McDaniel, M., Yuan, D., Chen, D., and Nazarian, S., "Use of Seismic Pavement Analyzer in Forensic Studies in Texas," **Nondestructive Testing of Pavements and Backcalculation of Moduli, Third Volume, ASTM STP 1735**, American Society for Testing and Materials, West Conshohoken, PA, 2000.

Nazarian, Soheil, et al., Development of Structural Field Testing of Flexible Pavement Layers, Project No. 1735, Final Report, University of Texas at El Paso, Center for Materials and Research, El Paso, Texas, 2002.

Nazarian, S., Baker, M. R., and Crain, K., "Development and Testing of a Seismic Pavement Analyzer," **Report Number SHRP-H-377** Strategic Highway Research Program, Washington, D.C., 1993.

Steyn, W., and Sadzik, E., "Application of the Portable Seismic Pavement Analyzer (PSPA) for Pavement Analysis," <http://hdl.handle.net/1024/1246>, 2007.

Von Quintus, et al., Nondestructive Testing Technology for Quality Control and Acceptance of Flexible Pavement Construction; Volume I - Procedure Manual, Final Report, NCHRP Project 10-65, June 2008.

Schedule of Tasks

The HMA Endurance Limit Validation Study will require 48 months to complete. Figure 22 presents a Gantt Chart for the project with the critical path identified. Table 31 presents a complete listing of milestones for the project.

Perhaps the most critical task in the project is Task B.2, Finalize Preliminary Approach, because the procedure assembled in this task will shape the final design of the laboratory experiments and the final selection of in-service pavements for analysis. Once the preliminary design procedure is finalized, then the critical path shifts to the laboratory studies in Task D. When the laboratory studies are completed, the critical path splits. The development of NCHRP944A_Version 0.2 of the research MEPDG software in Task 2.3 becomes critical. This version of the software will be used to analyze the accelerated pavement and test road data in Task E.3. Then based on the finding from these analyses, NCHRP944A_Version 0.3 will be developed for the calibration studies using data from the LTPP sections. The collection of data from the LTPP sections in Task E.4 also becomes critical. The site visits required in this task can not begin until the form of the model for predicting allowable strains from mixture composition is determined. The final field coring and laboratory testing plans will depend on the form of the model developed in Task D.5. The schedule provides 12 months to perform the 32 site visits. This is a compressed schedule for the site visits and likely will require at least two field engineers to complete the work as scheduled.

Analysis of the LTPP sections can begin as soon as the NCHRP944A_Version 0.3 is completed in Task B.4. Laboratory testing of the field cores will lag the site visits by approximately 1 month; therefore, the data required to analyze most of the LTPP sections will be available when NCHRP944A_Version 0.3 is completed.

The final tasks of the project begin after the calibration analyses are completed in Task E.5. This includes development of the final design procedure, NCHRP9-44A_Version 1.0 of the software, and the preparation of the final report for the project.

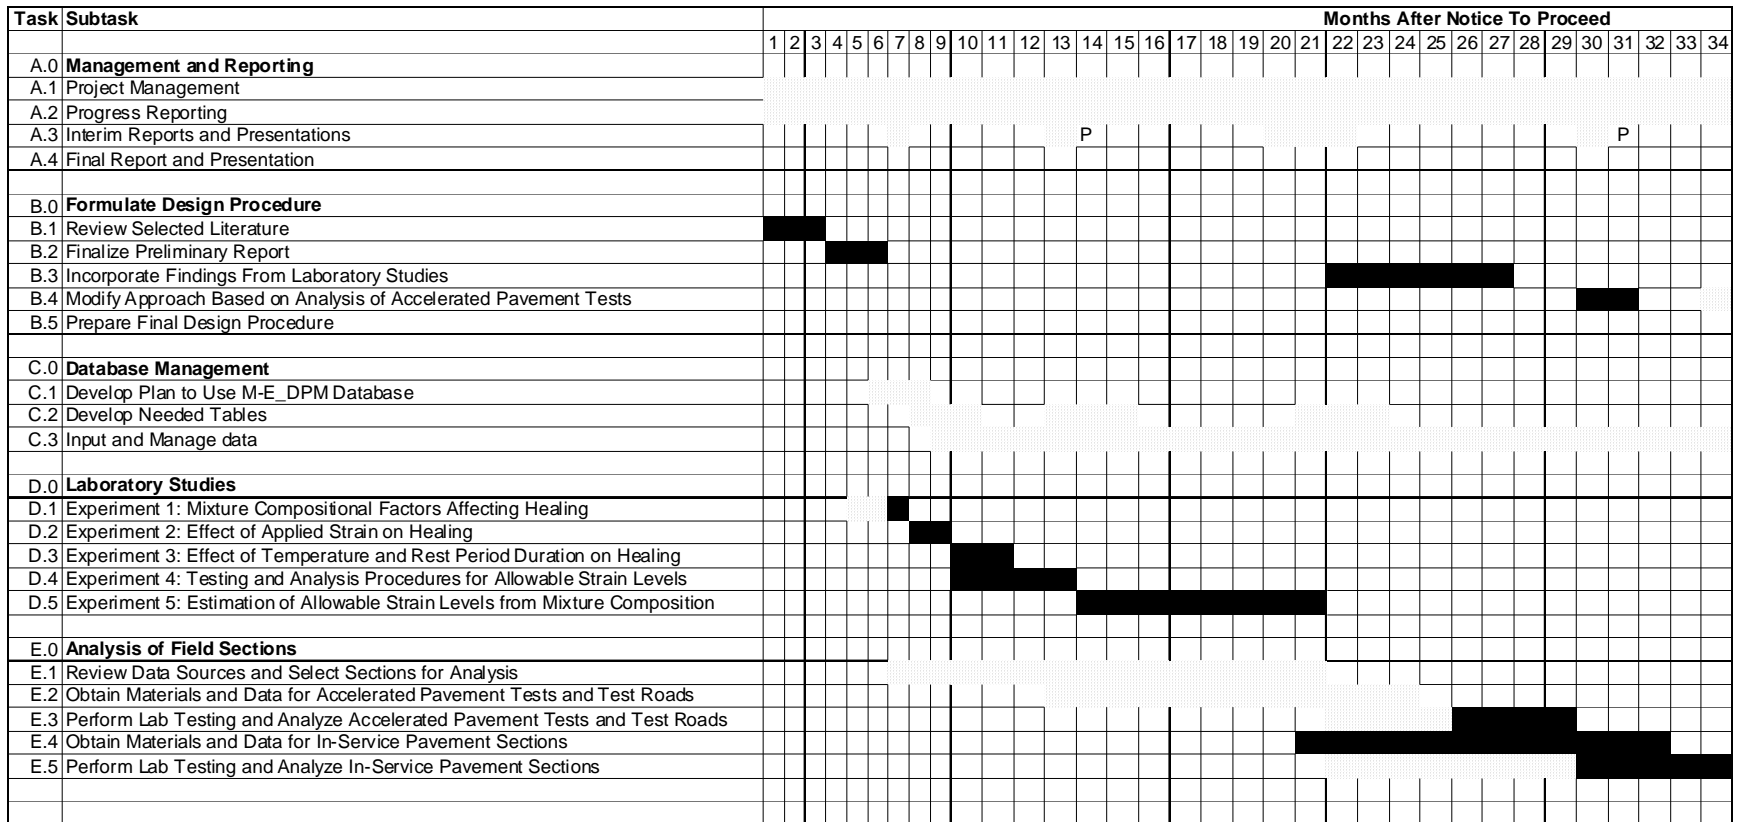


Figure 22. Project Schedule With Critical Path Shown in Black.

Figure 22. Project Schedule With Critical Path Shown in Black.

Table 31. Project Milestone Summary.

Month	Milestone	Description
1	A.1	Initial work assignments
2		
3	A.2	1 st quarterly progress report
4	B.1	Review selected literature
5	D.1	Select analysis approach and prepare detailed work plan for Experiment 1
6	A.3	2 nd quarterly progress report
	B.2	Preliminary approach and NCHRP Project 9-44A Version 0.1 software
7	A.4	1 st interim report: Preliminary design procedure and laboratory analysis approach
8	C.1	Database plan
	D.2	Complete Experiment 1
	D.3	Detailed work plan for Experiment 2
9	A.5	3 rd quarterly progress report
10	C.2	Tables for laboratory data
	D.4	Complete Experiment 2
	D.5	Detailed work plans for Experiments 3 and 4
11	D.6	Complete Experiment 3
12	A.6	4 th quarterly progress report
	E.1	Initial selection of pavement sections for analysis
13	A.7	2 nd interim report: Selection of pavement sections for analysis
	D.7	Complete Experiment 4
	D.8	Detailed work plan for Experiment 5
14	A.8	1 st presentation to the NCHRP panel: Interim reports 1 and 2
15	A.9	5 th quarterly progress report
16	C.3	Tables for analysis of accelerated pavement tests
17		
18	A.10	6 th quarterly progress report
19		
20	E.2	Final selection of LTPP sections for analysis
21	A.11	7 th quarterly progress report
	D.9	Complete Experiment 5
22	A.12	3 rd interim report: Analysis of laboratory studies
23	C.4	Tables for analysis of in-service pavement sections
24	A.13	8 th quarterly progress report
	E.3	Compile data from accelerated pavement sections and test roads
25		
26		
27	A.14	9 th quarterly progress report
	B.3	Incorporate findings from laboratory studies into NCHRP 9-44A Version 0.3 software
	E.4	Complete analysis of accelerated pavement tests and test roads
28		
29	B.4	Modify approach based on analysis of selected accelerated pavement tests and NCHRP 9-44A Version 0.3 software
30	A.15	10 th quarterly progress report
	A.16	4 th interim report: Design procedure incorporating findings from laboratory studies and analysis of accelerated pavement tests
31	A.17	2 nd presentation to NCHRP Panel: Interim reports 3 and 4
32	E.5	Complete data collection for LTPP sections
33	A.18	11 th quarterly progress report
34		
35	E.6	Complete testing and analysis of LTPP sections
36	A.19	12 th quarterly progress report
37		
38		
39	A.20	13 th quarterly progress report
40		
41	B.5	Prepare final design procedure and NCHRP 9-44A Version 1.0 software
	C.5	Final database
42	A.21	5 th interim report: Analysis of validation sections and final design procedure
	A.22	14 th quarterly progress report
43		
44		
45	A.23	Submit preliminary draft final report
	A.24	15 th quarterly progress report
46	A.25	3 rd presentation to the NCHRP panel: Preliminary draft final report and recommendations for implementation and additional research
47		
48	A.26	Submit revised final report

Budget

The budget for the project is based on the labor hour estimates provided in the Task by Task Description of the Research Plan and the loaded hourly rates presented in Table 32 for various categories of labor. Travel costs were included for the panel meetings in Task A.3 and for the LTPP site visits in Task E.4. Printing costs were also included in Task A.3 for each of the Interim Reports and the Final Report. The overall budget is presented in Figure 23. Details of the travel and printing estimates are provided in Tables 33 and 34, respectively.

Table 32. Labor Costs Used in Budget Preparation.

Labor Category	Loaded Hourly Rate
Senior Engineers and Statistician	\$150.00
Engineers and Programmers	\$100.00
Technicians	\$85.00
Administrative Support	\$60.00

Table 33. Travel Cost Estimate.

Task	Item	Detail	Estimate
A.3	Transportation	3 presentations × 2 people × \$800 per trip	\$4,800
A.3	Lodging & Per Diem	3 presentations × 2 people × 2 days × \$265/day	\$3,180
Task 1.3 Total			\$7,980
E.4	Airfare	2 person × 16 projects × \$800 per site	\$25,600
E.4	Rental Car	1 car × 4 days × 16 sites × \$75.00/day	\$4,800
E.4	Lodging & Per Diem	2 × 5 days × 16 sites × \$120.00/ day	\$19,200
Task E.4 Total			\$49,600

Table 34. Estimate of Report Printing Costs.

Report	Pages	Copies	Cost /Page	Cost
Interim 1	300	20	\$0.05	\$300
Interim 2	300	20	\$0.05	\$300
Interim 3	300	20	\$0.05	\$300
Interim 4	300	20	\$0.05	\$300
Interim 5	300	20	\$0.05	\$300
Revised Final	300	100	\$0.05	\$1,500
Total				\$3,000

Task/Subtask	Estimated Level of Effort				Estimated Costs						
	Staff Hours				Labor						
	Senior Engineer	Engineer/ Programmer	Technician	Support	Senior Engineer	Engineer/ Programmer	Technician	Support	Travel	Printing	Total
A.0 Management and Reporting											
A.1 Project Management	424			40	\$63,600			\$2,400			\$66,000
A.2 Progress Reporting	210			20	\$31,500			\$1,200			\$32,700
A.3 Interim Reports and Presentations	780			80	\$117,000			\$4,800	\$7,980		\$129,780
A.4 Final Report and Presentation	420			40	\$63,000			\$2,400		\$3,000	\$68,400
Task A Total	1834			180	\$275,100			\$10,800	\$7,980	\$3,000	\$296,880
B.0 Formulate Design Procedure											
B.1 Review Selected Literature	240	160			\$36,000	\$16,000					\$52,000
B.2 Finalize Preliminary Report	80	160			\$12,000	\$16,000					\$28,000
B.3 Incorporate Findings From Laboratory Studies	80	160			\$12,000	\$16,000					\$28,000
B.4 Modify Approach Based on Analysis of Accelerated Pavement Tests	80	80			\$12,000	\$8,000					\$20,000
B.5 Prepare Final Design Procedure	120	80			\$18,000	\$8,000					\$26,000
Task B Total	600	640			\$90,000	\$64,000					\$154,000
C.0 Database Management											
C.1 Develop Plan to Use M-E DPM Database	120				\$18,000	\$0					\$18,000
C.2 Develop Needed Tables	80	240			\$12,000	\$24,000					\$36,000
C.3 Input and Manage data	40	396			\$6,000	\$39,600					\$45,600
Task C Total	240	636			\$36,000	\$63,600					\$99,600
D.0 Laboratory Studies											
D.1 Experiment 1: Mixture Compositional Factors Affecting Healing	42		388		\$6,300		\$32,980				\$39,280
D.2 Experiment 2: Effect of Applied Strain on Healing	32		214		\$4,800		\$18,190				\$22,990
D.3 Experiment 3: Effect of Temperature and Rest Period Duration on Healing	69		242		\$10,350		\$20,570				\$30,920
D.4 Experiment 4: Testing and Analysis Procedures for Allowable Strain Levels	168		392		\$25,200		\$33,320				\$58,520
D.5 Experiment 5: Estimation of Allowable Strain Levels from Mixture Composition	456		1890		\$68,400		\$160,650				\$229,050
Task D Total	767		3126		\$115,050		\$265,710				\$380,760
E.0 Analysis of Field Sections											
E.1 Review Data Sources and Select Sections for Analysis	52	320			\$7,800	\$32,000					\$39,800
E.2 Obtain Materials and Data for Accelerated Pavement Tests and Test Roads	48	280			\$7,200	\$28,000					\$35,200
E.3 Perform Lab Testing and Analyze Accelerated Pavement Tests and Test Roads	164	512	32		\$24,600	\$51,200	\$2,720				\$78,520
E.4 Obtain Materials and Data for In-Service Pavement Sections	120	1280			\$18,000	\$128,000			\$49,600		\$195,600
E.5 Perform Lab Testing and Analyze In-Service Pavement Sections	300	512	1280		\$45,000	\$51,200	\$108,800				\$205,000
Task E Total	684	2904	1312		\$102,600	\$290,400	\$111,520		\$49,600		\$554,120
Grand Total	4125	4180	4438	180	\$618,750	\$418,000	\$377,230	\$10,800	\$57,580	\$3,000	\$1,485,360

Figure 21. Project Budget.

The total cost of the the project is \$1,485,360. Figure 24 provides a estimate of monthly expenditures for the project. Monthly expenditures reach approximately \$52,000 per month when the laboratory experiments are being conducted.

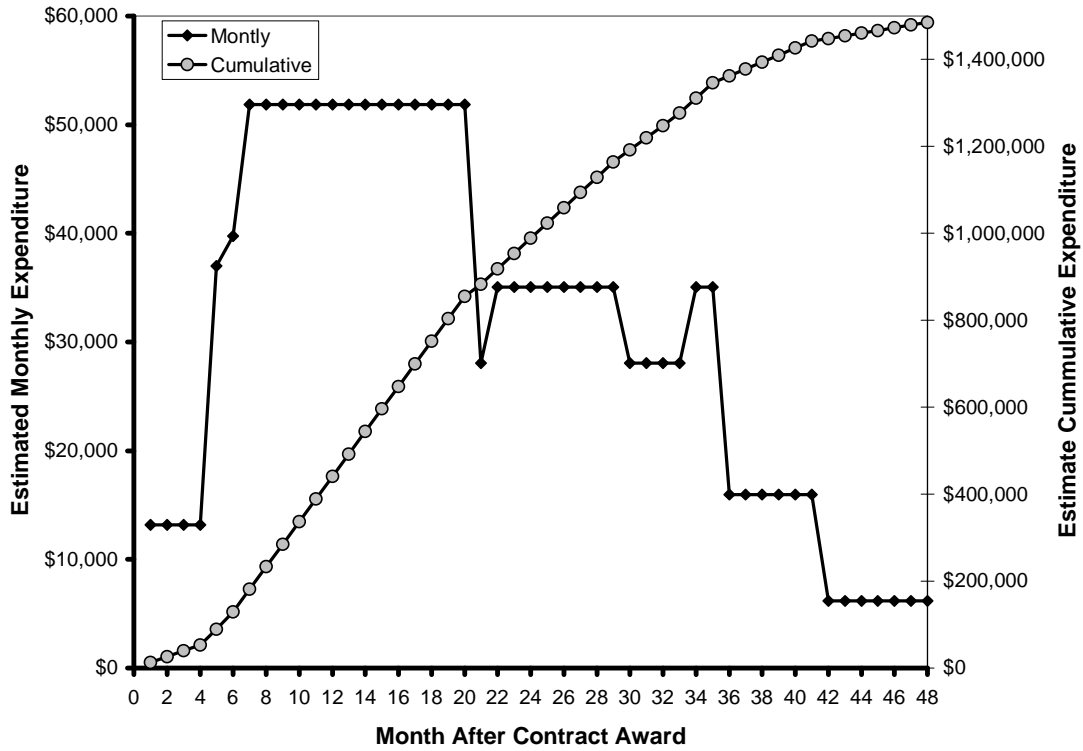


Figure 22. Estimated Monthly and Cumulative Expenditures.

References

1. Advanced Asphalt Technologies, LLC, “Hot Mix Asphalt Endurance Limit Workshop: Executive Summary,” National Cooperative Highway Research Program Project 9-44, November, 2007.
2. Monismith, C.L., and McLean, D.B., “Structural Design Considerations,” **Proceedings of the Association of Asphalt Paving Technologists**, Vol. 41, 1972.
3. Newcomb, D.E., Buncher, M., and Huddleston, I.J., “Concepts of Perpetual Pavements,” **Transportation Research Circular Number 503, Perpetual Bituminous Pavements**, Transportation Research Board, Washington, D.C., December, 2001.
4. Carpenter, S.H., Ghuzlan, K.A., and Shen, S., “Fatigue Endurance Limit for Highway and Airport Pavements,” **Transportation Research Record No. 1832**, Transportation Research Board, Washington, D.C., 2003.
5. Carpenter, S.H., and Shen, S., “Application of the Dissipated Energy Concept in Fatigue Endurance Limit Testing,” **Transportation Research Record No. 1929**, Transportation Research Board, Washington, D.C., 2005.
6. Prowell, B., Brown, E., R., Daniel, J., Bhattacharjee, S., Von Quintus, H., Carpenter, S., Shen, S., Anderson, M., Swamy, A. K., and Maghsoodloo, S., “Endurance Limit of Hot Mix Asphalt Mixtures to Prevent Fatigue Cracking in Flexible Pavements,” Updated Draft Final Report, NCHRP 9-38, National Cooperative Highway Research Program, Washington, D.C., May, 2008.
7. Carpenter, S.H., and Shen, S., “Dissipated Energy Approach to Study Hot-Mix Asphalt Healing in Fatigue,” **Transportation Research Record No. 1970**, Transportation Research Board, Washington, D.C., 2006.
8. Kim, B. and Roque, R., “Evaluation of Healing Property of Asphalt Mixtures,” **Transportation Research Record No. 1970**, Transportation Research Board, Washington, D.C., 2006.
9. Nunn, M. and Ferne, B.W., “Design and Assessment of Long-Life Flexible Pavements,” **Transportation Research Circular Number 503, Perpetual Bituminous Pavements**, Transportation Research Board, Washington, D.C., December, 2001.
10. Brown, S.R., Thom, N.H., and Hakim, B.A., “Performance and Rehabilitation of Heavy-duty Pavements in the UK: Some Case Studies,” **Proceedings, International Symposium of Design and Construction of Long Lasting Asphalt Pavements**, National Center for Asphalt Technology, Auburn, AL, 2004.
11. Wu, Z., Siddiqui, Z.Q., Hossain, M., and Gisi, A.J., “Kansas Turnpike – An Example of Long Lasting Asphalt Pavement,” **Proceedings, International Symposium of Design and**

Construction of Long Lasting Asphalt Pavements, National Center for Asphalt Technology, Auburn, AL, 2004.

12. Uhlmeyer, J.S., Willoughby, K., Pierce, L.M., and Mahoney, J.P., “Top-Down Cracking in Washington State Asphalt Concrete Wearing Courses,” **Transportation Research Record No. 1730**, Transportation Research Board, Washington, D.C., 2000.
13. Procedural Manual for Agencies Conducting Research in the National Cooperative Highway Research Program, Transportation Research Board, August, 2006.
14. Preparing Your CRP Final Report, Transportation Research Board, September, 2006.
15. Timm, D., H., and Young, J., B., “Effects of Load Spectra and Variability on Perpetual Pavement Design,” **Proceedings, International Symposium of Design and Construction of Long Lasting Asphalt Pavements**, National Center for Asphalt Technology, Auburn, AL, 2004.
16. Witczak, M.W., “Use of HMA Fatigue Endurance Limits in the Mechanistic-Empirical Pavement Design Guide,” Presentation at the Hot Mix Asphalt Endurance Limit Workshop, August 1, 2007.
17. Thompson, M.R., and Carpenter, S.H., “Design Principles for Long Lasting Pavement,” **Proceedings, International Symposium of Design and Construction of Long Lasting Asphalt Pavements**, National Center for Asphalt Technology, Auburn, AL, 2004.
18. Sidess, A. and Uzan, J., “A Design Method for Perpetual Flexible Pavement in Israel,” **International Journal of Pavement Engineering**, February, 2008.
19. Von Quintus, H. L., “Hot-Mix Asphalt Layer Thickness Design for Longer Life Bituminous Pavements,” **Transportation Research Circular Number 503, Perpetual Bituminous Pavements**, Transportation Research Board, Washington, D.C., December, 2001.
20. Von Quintus, Harold L., “Application of the Endurance Limit in Mechanistic-Empirical Based Pavement Design Procedures,” paper prepared for presentation and publication at the International Conference on Perpetual Pavements, Columbus, Ohio, September 13-15, 2006.
21. Tsai, B.W., Harvey, J., Monismith, C., and Bejarano, M., “Calibration of Fatigue Surface Cracking Using Simplified Recursive Miner’s Law,” **Journal of the Association of Asphalt Paving Technologists**, Vol., 76, 2007.
22. Mun, S., Guddati, M. N., and Kim, Y. R., “Fatigue Cracking Mechanisms in Asphalt Pavements with Viscoelastic Continuum Damage Finite-Element Program,” **Transportation Research Record No. 1896**, Transportation Research Board, Washington, D.C., 2004.

23. Roque, R., B. Birgisson, B. Sangpetngam and Z. Zhang, "Hot Mix Asphalt Fracture Mechanics: A Fundamental Crack Growth Law for Asphalt Mixtures," **Journal of the Association of Asphalt Paving Technologists**, Vol. 71, 2002.
24. Bonnaure, F.P, Huibers, A.H.J.J., Boonders, A., "A Laboratory Investigation of the Influence of Rest Periods on the Fatigue Response of Bituminous Mixes," **Proceedings, Association of Asphalt Paving Technologists**, Vol. 51, 1982.
25. Chehab, G.R., Kim, Y.R., Schapery, R.A., Witczak, M.W., and Bonaquist, R., "Characterization of Asphalt Concrete in Uniaxial Tension Using a Viscoelastoplastic Continuum Damage Model," *Journal of the Association of Asphalt Paving Technologists*, Vol. 72, 2003.
26. Huang, Y. H., **Pavement Analysis and Design**, Englewood Cliffs, N.J.: Prentice-Hall, Inc., 1993.
27. Al-Qadi, I., Xie, W., and Elseifi, M., "Frequency Determination from Vehicular Loading Time Pulse to Predict Appropriate Complex Modulus in MEPDG," Paper P:reprint CD, Association of Asphalt Paving Annual Meeting and Technical Sessions, Philadelphia, PA, April 27-30, 2008.
28. Barksdale, R.G., "Compressive Stress Pulse Times in Flexible Pavements for Use in Dynamic Testing," **Highway Research Record 345**, Highway Research Board, Washington, D.C., 1971.
29. Mirza, M. W., and M. W. Witczak, "Development of a Global Aging System for Short and Long Term Aging of Asphalt Cements," **Journal of the Association of Asphalt Paving Technologists**, Vol. 64, 1995.
30. Transportation Research Board, **Highway Capacity Manual**, Special Report 209, Third Edition, Transportation Research Board, Washington, DC 1994.
31. Hajek, J. J., Selezneva, O., I., Mladenovic, G., and Jiang, Y., J., "Estimating Cumulative Traffic Loads, Volume II: Traffic Data Assessment and Axle Load Projection for the Sites With Acceptable Axle Weight Data, Final Report for Phase 2," **Report Number FHWA-RD-03-094**, Federal Highway Administration, Washington, D.C., March, 2005.
32. Lytton, R L; Uzan, J; Fernando, E G; Roque, R; Hiltunen, D; Stoffels, S M, "Development And Validation Of Performance Prediction Models And Specifications For Asphalt Binders And Paving Mixes," **Report Number SHRP-A-357**, Strategic Highway Research Program, Washington, D.C., 1993.
33. Von Quintus, H.L., Schwartz, C., McQuen, R., and Andrei, D., "Experimental Plan for Calibration and Validation of Hot-Mix Asphalt Performance Models for Mix and Structural Design," Final Report for National Cooperative Highway Research Program Project 9-30, National Cooperative Highway Research Program, January, 2004.

34. Little, D. N., Lytton, R. L., Williams, D., and Chen, C. W., "Microdamage Healing in Asphalt and Asphalt Concrete, Volume I: Microdamage and Microdamage Healing Project Summary Report," **Report Number FHWA-RD-98-141**, Federal Highway Administration, Washington, D.C., June 2001.
35. Rao Tangella, S.C.S., Craus, J., Deacon, J.A., and Monismith, C.L., "Summary Report on Fatigue Response of Asphalt Mixtures," **Report Number SHRP-A/IR-90-011**, Strategic Highway Research Program, Washington, D.C., 1990.
36. Bonnaure, R., Gravois, A., and Udron, J., "A New Method for Predicting the Fatigue Life of Bituminous Mixes," **Proceedings of the Association of Asphalt Paving Technologists**, Vol. 49, 1980.
37. Lee, H., J., Daniel, J.S., and Kim, Y.R., "Laboratory Performance Evaluation of Modified Asphalt Mixtures for Incheon Airport Pavements," **International Journal of Pavement Engineering**, Volume 1, Number 2, 2000.
38. Walubita, L.F., Epps-Martin, A., Jung, S. H., Glover, C. J., Park, E.S., Chowdhury, A., and Lytton, R. L., "Comparison of Fatigue Analysis Approaches for Two Hot Mix Asphalt Concrete (HMAC) Mixtures," **Report Number FHWA/TX-05/0-4468-2**, Texas Department of Transportation, Austin, TX, August, 2005.
39. Christensen, D.W., and Bonaquist, R.F., "Volumetric Requirements for Superpave Mix Design," **NCHRP Report 567**, National Cooperative Highway Research Program, Washington, D.C., 2006.
40. Prowell, B. D., and Brown, E. R., "Superpave Mix Design: Verifying the Gyrations Levels in the N_{design} Table," NCHRP Report 573, National Cooperative Highway Research Program, Washington, D.C., 2007.
41. Epps, J. A., Hand, A., Seeds, S., Schultz, T., Alavi, S., Ashmore, C., Monismith, C., Deacon, J.A., Harvey, J.T., and Leahy, R., "Recommended Performance Related Specifications for Hot-Mix Asphalt Construction: Results of the WesTrack Project," **NCHRP Report 455**, National Cooperative Highway Research Program, Washington, D.C., 2002.
42. Kim, Y.R., and Little, D.N., "One Dimensional Constitutive Modeling of Asphalt Concrete," **ASCE Journal of Engineering Mechanics**, Vol. 116, No. 4, 1990.
43. Lundstrom, R., and Isacsson, U., "Characterization of Asphalt Concrete Deterioration Using Monotonic and Cyclic Tests," **International Journal of Pavement Engineering**, Vol. 4, No. 3, September, 2003.
44. Christensen, D.W., and Bonaquist, R.F., "Practical Application of Continuum Damage Theory to Fatigue Phenomena in Asphalt Concrete Mixtures," **Journal of the Association of Asphalt Paving Technologists**, Vol. 74, 2005.

45. Advanced Asphalt Technologies, LLC, "NCHRP 9-29 Phase V Draft Final Report," National Cooperative Highway Research Program, July 30, 2007.
46. Advanced Asphalt Technologies, LLC, "NCHRP 9-29 Phase IV Draft Final Report," National Cooperative Highway Research Program, June, 2006.
47. Christensen, D.W., Pellinen, T, and Bonaquist, R.F., "Hirsch Model for Estimating the Modulus of Asphalt Concrete," **Journal of the Association of Asphalt Paving Technologists**, Vol. 72, 2003.
48. Christensen, D.W., and Anderson, D.A., "Interpretation of Dynamic Mechanical Test Data for Paving Grade Asphalt Cements," **Proceedings of the Association of Asphalt Paving Technologists**, Vol. 61, 1992.
49. Christensen, D.W., and Bonaquist, R., "Analysis of HMA Fatigue Data Using The Concepts of Reduced Loading Cycles and Endurance Limit," Submitted for Presentation and Publication at the 2009 Annual Meeting of the Associations of Asphalt Paving Technologists.
50. Stuart, K.D., Mogawer, W.S., and Romero, P., "Validation of the Superpave Asphalt Binder Fatigue Cracking Parameter Using an Accelerated Loading Facility," **Report Number FHWA-RD-01-093**, Federal Highway Administration, Washington, D.C., 2002.
51. National Center for Asphalt Technology. <http://www.pavetrack.com/> (accessed June, 2008).
52. Timm, D. West, R., Priest, A., Powell, B., Selvaraj, I., Zhang, J., and Brwon, R., "Phase II NCAT Test Track Results," **NCAT Report 06-05**, National Center for Asphalt Technology, Auburn University, Auburn, AL, December, 2006.
53. Timm, D. and Priest, A., "Material Properties of the 2003 NCAT Test Track Structural Study," **NCAT Report 06-01**, National Center for Asphalt Technology, Auburn University, Auburn, AL, April, 2006.
54. Minnesota Department of Transportation. <http://www.dot.state.mn.us/mnroad/> (accessed June, 2008).
55. Palmquist, D., Worel, B., Zerfas, W., "2002 Hot-Mix Asphalt Mainline Test Cell Condition Report," Minnesota Department of Transportation, September 6, 2002.
56. Federal Highway Administration. <http://www.ltpo-products.com/DataPave/index.asp> (accessed June, 2008).
57. Asphalt Pavement Alliance. <http://www.asphaltalliance.com/> (accessed June, 2008).

58. Worel, B., "MnRoad Database Guide," Minnesota Department of Transportation, January, 2006
59. NCHRP Project 9-19, "Binder Characterization, Team Report BC-4, "Rheological Characterization of the FHWA-ALF Binders," PDF File No, 04-E, CRP-CD-46, National Cooperative Highway Research Program, 2005.
60. NCHRP Project 9-19, "Binder Characterization, Team Report BC-5, "Rheological Characterization of the WesTrack Binders," PDF File No, 04-F, CRP-CD-46, National Cooperative Highway Research Program, 2005.
61. NCHRP Project 9-19, "Binder Characterization, Team Report BC-3, "Rheological Characterization of the MnRoad Binders," PDF File No. 04-D, CRP-CD-46, National Cooperative Highway Research Program, 2005.
62. Von Quintus, et al., Nondestructive Testing Technology for Quality Control and Acceptance of Flexible Pavement Construction; Volume I - Procedure Manual, Final Report, NCHRP Project 10-65, June 2008
63. Geomedia Research and Development, <http://geomedia.us/> (accessed June, 2008)
64. VonQuintus, H.L., Schwartz, C.E., McCuen, R.H., and Andrei, D., "Jackknife Testing – An Experimental Approach to Refine Model Calibration and Validation," **Research Results Digest Number 283**, National Cooperative Highway Research Program, Washington, D.C, December, 2003.

Appendix A: Recommended LTPP Test Sections

The following provides location and summary information for the LTPP test sections that are applicable for use in confirming the endurance limit and values. The distress information listed for each test sections are the values included within the LTPP database. Specifically, the longitudinal cracking and transverse cracking values are in meters, while the block and alligator cracking values are in square meters.

LTPP Site Identification Number: 0103
 Roadway or Route No.: US-280
 Date of Construction: April 1991

State: Alabama (01)
 Status: In Service

Location:

Longitude: 85.25 Latitude: 32.62 Elevation: 151

Pavement Cross Section:

Layer	Material Type	Thickness, inches
4	HMA Hot Mixed, Hot Laid HMA, Dense Graded (1)	1.5
3	HMA Hot Mixed, Hot Laid HMA, Dense Graded (1)	3.1
2	ATB Asphalt Treated Base (319)	7.4
1	Subgrade Soil Sandy Lean Clay (114)	---

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Sandy Lean Clay	6

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 200
 Type of Asphalt: PG64-22

	HMA	HMA	ATB	
Asphalt Content, %	5.1	4.0	4.3	
Air Voids, %	3.3	5.1	11.6	

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	83	61	24	6.7
HMA	90	66	48	21	7.2
ATB	90	65	42	18	5.6

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1994	0	0	0	0	2001	22.9	0	9.7	0
1995	0	0	0	0	2002	28.7	0	0	1.5
1996	0	0	0	0	2003	34.4	0	0	7.9
2000	34.9	0	30.6	0	2004	40.1	0	0	8.7
					2005	41.4	0	0	8.0

LTPP Site Identification Number: 0101
 Roadway or Route No.: US-280
 Date of Construction: April 1991

State: Alabama (01)
 Status: In Service

Location:

Longitude: 85.25 Latitude: 32.62 Elevation: 151

Pavement Cross Section:

Layer	Material Type	Thickness, inches
4	HMA Hot Mixed, Hot Laid HMA, Dense Graded (1)	1.3
3	HMA Hot Mixed, Hot Laid HMA, Dense Graded (1)	6.2
2	GB Crushed Stone, Granular Base (303)	7.9
1	Subgrade Soil Sandy Silt (145)	---

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Sandy Lean Clay	6

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 200
 Type of Asphalt: PG64-22

	HMA	HMA		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
HMA					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1995	0	0	0	0	2001	25.3	0	13.7	0.8
1996	1.2	0	4.5	0	2002	31.1	0	0	3.5
1997	0	0	37.5	0	2003	64.9	0	0	14.6
1998	3.0	0	0.2	0.3	2004	68.0	0	0	15.7
2000	38.6	0	16.2	0.6	2005	70.4	0	0	14.6

LTPP Site Identification Number: 0111 State: Alabama (01)
 Roadway or Route No.: US 280
 Date of Construction: April 1991 Status: In Service

Location:
 Longitude: 85.25 Latitude: 32.61 Elevation: 151

Pavement Cross Section:

Layer	Material Type	Thickness, inches
4,5	HMA Hot Mixed, Hot Laid AC, Dense Graded (1)	4.0
3	ATB Hot Mixed, Hot Laid AC Dense Graded Mix (319)	7.9
2	PATB Open-Graded Hot Laid Mix (325)	3.7
1	Subgrade Soil Silt with Sand (143)	---

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Silt with Sand	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 200
 Type of Asphalt: PG62-22

	HMA	HMA	ATB	PATB
Asphalt Content, %	5.2	4.0	4.3	2.2
Air Voids, %	3.3	5.1	11.6	---

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	83	61	24	6.7
HMA	90	66	48	21	7.2
ATB	90	65	42	18	5.6
PATB	71	19	10	7.0	4.3

Tensile Strain at Bottom of HMA Layer: 144.29

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1994	0	0	0	0	2001	92.7	0	0.5	0
1995	0	0	0	0	2001	67.8	0	0	1.2
1996	0	0	5.5	0	2003	86.4	0	0	2.4
2000	60.2	0	23.2	0	2004	86.9	0	0	3.3
					2005	89.0	0	0	3.5

LTPP Site Identification Number: 0116 State: Arizona (04)
 Roadway or Route No.: US 93
 Date of Construction: Jan. 1993 Status: In Service

Location:
 Longitude: 114.2 Latitude: 35.39 Elevation: 3580

Pavement Cross Section:

Layer	Material Type	Thickness, inches
4	AC	4.0
	Surface Seal (72), 2003	
3	HMA	12.1
	Hot Mixed, Hot Laid AC, Dense Graded (1)	
2	ATB	132
	Hot Mix, Hot Laid, AC, Dense Graded (1)	
1	Subgrade Soil	
	Silty Sand with Gravel (215)	

Traffic Data:

Number of Years with Data: 3
 AADTT (One-way): 1190 Year: 1995
 KESALS per year: 300

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Silty Sand with Gravel	4
	Last	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 200
 Type of Asphalt: _____

	HMA	ATB		
Asphalt Content, %	4.7	4.5		
Air Voids, %	10.3	6.1		

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	99	82	64	18	3.9
ATB	88	72	56	16	4.0

Tensile Strain at Bottom of HMA Layer: 142.48

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1995	0	0	0	0	2002	69.9	0	16.2	1.5
1998	0	0	0	0	2003	5.8	0	19.2	1.1
1999	1.4	0	2.1	0	2004	11.2	0	17.3	2.8
2000	4	0	3.3	0	2005	11.6	0	28.5	5.3
2001	9.9	0	22	0					

LTPP Site Identification Number: 04-0162 State: Arizona (04)
 Roadway or Route No.: US 93
 Date of Construction: Jan. 1993 Status: In Service

Location:
 Longitude: 114.2 Latitude: 35.39 Elevation: 3580

Pavement Cross Section:

Layer	Material Type	Thickness, inches
3	AC	9.0
2	Seal Coat (72), 2003	
2	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)
1	Subgrade Soil	Well Graded Gravel with Sand & Silt (261)

Traffic Data:

Number of Years with Data: 3
 AADTT (One-way): 1190 Year: 1995
 KESALS per year: 300

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Silty Sand with Gravel	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 200
 Type of Asphalt: _____

	HMA			
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1995	0	0	0	0	2002	1.7	0	3.8	2.0
1998	0	0	0	0	2005	2.8	0	4.5	10.4
1999	0	0	0	0	2006	4.4	0	1.4	20.4
2000	0	0	0	0					
2001	0	0	1.0	0					

LTPP Site Identification Number: 1062 State: Arizona (04)
 Roadway or Route No.: I 40
 Date of Construction: 10-1-1977 Status: Milled/Overlay; Friction Course

Location:
 Longitude: 113.34 Latitude: 35.19 Elevation: 5060

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
6	AC	Open-Graded Friction Course (82); 9-1999	0.3
5	AC	Open Graded, Sand Seal (2)	4.6 – after milling (5.8 – Original)
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	
3	ATB	Asphalt Treated Mixture (321)	11.2
2	TS	Lime Treated Mixture (338)	6
1	Subgrade Soil	Clayey Gravel with Sand (267)	54

Traffic Data:

Number of Years with Data: 8
 AADTT (One-way): 1900 Year: 1998
 KESALS per year: 1200

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Lime Treated Mixture	28
1	Clayey Gravel with Sand	15

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA			
Asphalt Content, %	5.3			
Air Voids, %	5.5			

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	80.5	57	48.5	14.5	7.4

Tensile Strain at Bottom of HMA Layer: 49.15

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1996	0	0	0	6.4	2005	7.0	0	1.4	0.6
1998	0	0	0	8.7					
2000	0	0	0	0					
2003	0	0	0	0					

LTPP Site Identification Number: 1065 State: Arizona (04)
 Roadway or Route No.: I 40
 Date of Construction: 10-1-1977 Status: Milled/Overlay; Friction Course

Location:
 Longitude: 113.26 Latitude: 35.2 Elevation: 5301

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	AC	Open-Graded Friction Course (82); 9-1999	0.3
4	AC	Hot Mixed, Hot Laid AC, Dense Graded (1)	5.3
3	TB	Asphalt Treated Mixture (319)	13.7
2	TS	Lime Treated Soil (338)	5
1	Subgrade Soil	Clayey Gravel with Sand (A-2-6)	---

Traffic Data:

Number of Years with Data: 8
 AADTT (One-way): 1900 Year: 1998
 KESALS per year: 1200

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Lime Treated Soil	28
1	Clayey Gravel with Sand	15

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA			
Asphalt Content, %	5.6			
Air Voids, %	4.2			

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	77	54.5	47.5	14.5	7.2

Tensile Strain at Bottom of HMA Layer: 39.96

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1992	0	0	0	0	2005	0	0	2.7	0.7
1998	0	0	0	12.2					
2000	0	0	0	0					
2003	0	0	0	0.3					

LTPP Site Identification Number: 0115 State: Arkansas (05)
 Roadway or Route No.: US 63
 Date of Construction: Jan. 1993 Status: In Service

Location:
 Longitude: 90.58 Latitude: 35.72 Elevation: 222

Pavement Cross Section:

Layer	Material Type	Thickness, inches
4	HMA Hot Mixed, Hot Laid AC, Dense Graded (1)	1.8
3	HMA Hot Mixed, Hot Laid AC, Dense Graded (1)	5.1
2	ATB Hot Mixed, Hot Laid, Dense Graded (319)	7.4
1	Subgrade Soil Silty Sand (214)	---

Traffic Data:

Number of Years with Data: 3
 AADTT (One-way): 800 Year: 1998
 KESALS per year: 776

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Silty Sand	---

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: ---
 Type of Asphalt: ---

	HMA	HMA	ATB	
Asphalt Content, %	4.5	3.7	2.95	
Air Voids, %	9.9	9.9	6.7	

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	98	78	53	12	5.0
HMA	91	61	43	20	6.0
ATB	77	47	35	16	4.5

Tensile Strain at Bottom of HMA Layer: 0.00

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1997	0	0	0	0	2003	21	0	0.7	7.7
2000	6.7	0	1.7	0.5	2004	22	0	0.8	8.9
2001	10.2	0	0	1.7	2005	25.4	0	0	12.6
2002	17.3	0	0	4.3					

LTPP Site Identification Number: 3071 State: Arkansas (05)
 Roadway or Route No.: US 71
 Date of Construction: 7-1-1987 Status: In Service

Location:
 Longitude: 94.15 Latitude: 36.26 Elevation: 1311

Pavement Cross Section:

Layer	Material Type	Thickness, inches
6	AC Seal Coat (72); Placed after construction	0.4
5	AC Seal Coat (71)	0.5
4	HMA Hot Mixed, Hot Laid AC, Dense Graded (1)	1.5
3	HMA Hot Mixed, Hot Laid AC, Dense Graded (1)	3.9
2	ATB Hot Mix, Hot Laid, Dense Graded (319)	10.5
1	Subgrade Soil Lean Clay (214)	---

Traffic Data:

Number of Years with Data: 6
 AADTT (One-way): 2925 Year: 1998
 KESALS per year: 3102

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Subgrade Soil/Lean Clay	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	HMA		
Asphalt Content, %	4.9	4.45		
Air Voids, %	3.7	6.0		

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	80	64	30	8.5
HMA	84	58	45	21	7.4

Tensile Strain at Bottom of HMA Layer: 69.28

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1991	0	0	0	0	1999	0	0	0	0
1994	0	0	1	0	2000	0	0	0	2.2
1995	0	0	0	0	2003	0.7	0	0	60.7
1997	0	0	0	0	2004	0.6	0	0	95.9

LTPP Site Identification Number: 0106 State: Florida (12)
 Roadway or Route No.: US 27
 Date of Construction: Jan. 1993 Status: In Service

Location:
 Longitude: 80.69 Latitude: 26.54 Elevation: 14

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	2.1
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	5.0
3	ATB	Hot Mixed, Hot Laid AC, Dense Graded (319)	8.4
2	GB	Crushed Stone (303)	4
1	Subgrade Soil	Silty Sand with Gravel (215)	87.6

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Crushed Stone	25
1	Silty Sand with Gravel	12

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	HMA	ATB
Asphalt Content, %	6.2	5.2	2.5
Air Voids, %	8.1	5.5	4.6

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	90	68	28	3.1
HMA	99	77	60	25	3.2
ATB					

Tensile Strain at Bottom of HMA Layer: 60.33

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1996	0	0	0	0	2003	0	0	0	0
2000	0	0	0	0	2004	0	0	1.7	1.1
2001	0	0	0	0	2005	0	0	2.3	1.3
2002	0	0	0	0					

LTPP Site Identification Number: 0104 State: Florida (12)
 Roadway or Route No.: US 27
 Date of Construction: Jan. 1993 Status: In Service

Location:
 Longitude: 80.69 Latitude: 26.54 Elevation: 14

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	1.9
3	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	4.9
2	ATB	Hot Mixed, Hot Laid, Dense Graded (319)	12.1
1	Subgrade Soil	Poorly Graded Sand with Silt and Gravel (205)	87.6

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Poorly Graded Sand with Silt and Gravel	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	HMA	ATB	
Asphalt Content, %	6.2	5.2	2.5	
Air Voids, %	4.2	3.9	5.9	

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	90	68	28	3.1
HMA	99	77	60	25	3.2
ATB					

Tensile Strain at Bottom of HMA Layer: 45.71

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1996	0	0	0	0	2003	0	0	0	0
2000	0	0	0	0	2004	0.2	0	0	0
2001	0	0	0	0	2005	0.5	0	1.2	0
2002	0	0	0	0					

LTPP Site Identification Number: 0101 State: Florida (12)
 Roadway or Route No.: US 27
 Date of Construction: Jan. 1993 Status: In Service

Location:
 Longitude: 80.69 Latitude: 26.54 Elevation: 14

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	2.0
3	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	4.8
2	GB	Crushed Stone (303)	8.1
1	Subgrade Soil	Silty Sand with Gravel (215)	68.4

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Crushed Stone	25
1	Silty Sand with Gravel	12

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: _____
 Type of Asphalt: _____

	HMA	HMA		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
HMA					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1996	0	0	0	0	2003	0	0	0	0
2000	0	0	0	0	2004	0.1	0	0	0.3
2001	0	0	0	0	2005	0.2	0	0	0.8
2002	0	0	0	0					

LTPP Site Identification Number: 0103 State: Florida (12)
 Roadway or Route No.: US 27
 Date of Construction: Jan. 1993 Status: In Service

Location:
 Longitude: 80.69 Latitude: 26.54 Elevation: 14

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	2.0
3	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	2.1
2	ATB	Hot Mixed, Hot Laid AC, Dense Graded (319)	8.0
1	Subgrade Soil	Poorly Graded Sand with Gravel & Silt (205)	87.6

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Silty Sand with Gravel	12

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	HMA	ATB	
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
HMA					
ATB					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1996	0	0	0	0	2003	0.6	0	0	0
2000	0	0	0	0	2004	2.6	0	0.6	0
2001	0	0	0	0	2005	3.4	0	7.8	0
2002	0	0	0.4	0					

LTPP Site Identification Number: 0107 State: Florida (12)
 Roadway or Route No.: US 27
 Date of Construction: Jan. 1993 Status: In Service

Location:
 Longitude: 80.69 Latitude: 26.54 Elevation: 14

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	3.8
3	ATB	Hot Mixed, Hot Laid AC, Dense Graded (325)	4.1
2	GB	Crushed Stone (303)	4.1
1	Subgrade Soil	Poorly Graded Sand with Gravel & Silt (205)	105.6

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Crushed Stone	25
1	Silty Sand with Gravel	12

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: _____
 Type of Asphalt: _____

	HMA	HMA	ATB
Asphalt Content, %			
Air Voids, %			

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
HMA					
ATB					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1996	0	0	0	0	2003	1.6	0	5.9	0
2000	0	0	0	0	2004	11.6	0	54.3	0.3
2001	0	0	0	0	2005	12.1	0	52.8	0.6
2002	0	0	0	0					

LTPP Site Identification Number: 0111 State: Florida (12)
 Roadway or Route No.: US 27
 Date of Construction: Jan. 1993 Status: In Service

Location:
 Longitude: 80.69 Latitude: 26.54 Elevation: 14

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	1.8
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	2.1
3	ATB	HMAC, Hot Laid, Dense Graded (319)	8.2
2	PATB	Open Graded Hot Mix, Hot Laid (325)	4.0
1	Subgrade Soil	Silty Sand with Gravel (215)	75.6

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Silty Sand with Gravel	12

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	HMA	ATB
Asphalt Content, %	6.1	5.2	
Air Voids, %	7.9	6.8	5.3

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	98	78	59	29	2.5
HMA	99	77	60	25	3.2
ATB					

Tensile Strain at Bottom of HMA Layer: 60.35

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1996	0	0	0	0	2003	0	0	0	0
2000	0	0	0	0	2004	0.3	0	8.0	1.2
2001	0	0	0	0	2005	0.5	0	13.1	1.6
2002	0	0	0	0					

LTPP Site Identification Number: 4113 State: Georgia (13)
 Roadway or Route No.: IH 95
 Date of Construction: 6-1-1977 Status: In Service

Location:
 Longitude: 81.61 Latitude: 31.08 Elevation: 13

Pavement Cross Section:

Layer	Material Type	Thickness, inches
	AC Seal Coat (71)	0.1
3	HMA Hot Mixed, Hot Laid AC, Dense Graded (1)	3.7
2	ATB Asphalt Treated Mixture (321)	11.5
1	Subgrade Soil Poorly Graded Sand with Silt (204)	---

Traffic Data:

Number of Years with Data: 6
 AADTT (One-way): 3703 Year: 1997
 KESALS per year: 1933

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Poorly Graded Sand with Silt	12

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	ATB		
Asphalt Content, %	5.31	4.14		
Air Voids, %	2.1	4.5		

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	99	63	46	27	3.7
ATB	74	47	40	22	3.9

Tensile Strain at Bottom of HMA Layer: 65.52

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1991	0	0	0	0	1999	0	0	0	0
1994	0	0	0	1	2000	0	0	0	0
1997	4.4	0	9.5	2					
1998	4.1	0	11.3	2.1					

LTPP Site Identification Number: 4119 State: Georgia (13)
 Roadway or Route No.: IH 75
 Date of Construction: 6-1-1978 Status: In Service

Location:
 Longitude: 84.21 Latitude: 34.09 Elevation: 815

Pavement Cross Section:

Layer	Material Type	Thickness, inches
5	AC Friction Course (2)	0.8
4	HMAA Hot Mixed, Hot Laid AC, Dense Graded (1)	2.0
3	ATB Hot Mixed, Hot Laid, Dense Graded (319)	13.8
2	GS Soil Agg. Mix (308)	16.4
1	Subgrade Soil Sandy Silt (145)	---

Traffic Data:

Number of Years with Data: 3
 AADTT (One-way): 5568 Year: 1996
 KESALS per year: 2906

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus ksi
1	Soil Agg. Mix	14
2	Sandy Silt	9

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	ATB		
Asphalt Content, %	5.6	4.75		
Air Voids, %	3.0	5.9		

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	96	75	61	17	9.5
ATB	72	63	52	15	8.5

Tensile Strain at Bottom of HMA Layer: 58.55

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1992	0	0	0	0					
1994	0	0	0	0					
1995	0	0	0	1.7					

LTPP Site Identification Number: 4112 State: Georgia (13)
 Roadway or Route No.: IH 95
 Date of Construction: 6-1-1977 Status: In Service

Location:
 Longitude: 81.6 Latitude: 31.02 Elevation: 13

Pavement Cross Section:

Layer	Material Type	Thickness, inches
4	AC Seal Coat (72)	0.1
3	HMA Hot Mixed, Hot Laid AC, Dense Graded (1)	3.2
2	ATB Hot Mixed, Hot Laid, Dense Graded (319)	12.7
1	Subgrade Soil Poorly Graded Sand (202)	---

Traffic Data:

Number of Years with Data: 6
 AADTT (One-way): 3703 Year: 1997
 KESALS per year: 1933

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Poorly Graded Sand	12

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	ATB		
Asphalt Content, %	5.69	4.63		
Air Voids, %	2.1	5.9		

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	99	59	44	31	3.5
ATB	84	51	44	25	3.5

Tensile Strain at Bottom of HMA Layer: 60.74

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1991	0	0	0	0	1998	0	0	0	0
1994	0	0	0	0	1999	0	0	0	0
1997	0	0	0	0	2000	0	0	0	0

LTPP Site Identification Number: 9034 State: Idaho (16)
 Roadway or Route No.: 95
 Date of Construction: 9-30-1988 Status: In Service

Location:
 Longitude: 116.5 Latitude: 48.42 Elevation: 2119

Pavement Cross Section:

Layer	Material Type	Thickness, inches
6	AC	0.6
5	AC	
4	HMA	2.9
3	HMA	6.0
2	GB	18.8
1	Subgrade Soil	---

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Poorly Graded Sand	

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: _____
 Type of Asphalt: _____

	HMA	HMA		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
HMA					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1994	0	0	44.5	0.7	2004	17.3	0	0	4.8
1997	2.3	0	66.2	5.3					
1998	2.3	0	68.8	3.5					
2001	0	0	0	0					

LTPP Site Identification Number: 2009 State: Indiana (18)
 Roadway or Route No.: ST 37
 Date of Construction: Jan. 1981 Status: Out of Service; 4-1999

Location:
 Longitude: 86 Latitude: 40.03 Elevation: 785

Pavement Cross Section:

Layer	Material Type	Thickness, inches
6	AC Seal Coat, Slurry Seal (72)	0.5
5	HMA Hot Mixed, Hot Laid AC, Dense Graded (1)	5.7
4	ATB Dense Graded, Cold Laid, Plant Mix (326)	6.5
3	PATB Open Graded, Hot Mix, Hot Laid (323)	3.3
2	GB Gravel, Uncrushed (302)	9.5
1	Subgrade Soil Sandy Lean Clay (114)	---

Traffic Data:

Number of Years with Data: 2
 AADTT (One-way): 481 Year: 1991
 KESALS per year: 408

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Gravel (uncrushed)	100
1	Sandy Lean Clay	7

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	ATB		
Asphalt Content, %	3.4			
Air Voids, %	6.6			

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	78	45	32	8.0	3.7
ATB					

Tensile Strain at Bottom of HMA Layer: 103.87

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1993	3.7	0	0	44.7					
1995	5.9	0	12	51.7					

LTPP Site Identification Number: 0112 State: Iowa (19)
 Roadway or Route No.: US 61
 Date of Construction: May 1992 Status: In Service

Location:
 Longitude: 91.25 Latitude: 40.70 Elevation: 530

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
6	HMA	Hot Mixed, Hot Laid AC, Dense Graded	2.5
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	2.1
4	ATB	HMAC, Hot Laid, Dense Graded	12.4
3	PATB	Open-Graded Hot-Mix, Hot Laid;	4.1
2	GS	Lean Clay with Sand	24
1	Subgrade Soil	Clay	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 425 Year: 1992
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Lean Clay with Sand	6
1	Clay	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: PG70-22

	HMA	ATB		
Asphalt Content, %	4.8	4.5		
Air Voids, %	10.0	8.5		

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	92	57	39		5.3
ATB	96	68	47		6.2

Tensile Strain at Bottom of HMA Layer: 43.50

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1995	0	0	0	0	2005	0.3	0	16.4	12.3
1999	0	0	1.2	10.4					
2001	0	0	5	17.3					
2002	0	0	0	6.3					

LTPP Site Identification Number: 0101 State: Iowa (19)
 Roadway or Route No.: US 61
 Date of Construction: May 1992 Status: In Service

Location:
 Longitude: 91.25 Latitude: 40.70 Elevation: 530

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	2.0
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded	6.0
3	GB	Crushed Stone Base (303)	8.0
2	GS	Embankment Soil; Clay with Gravel (104)	24
1	Subgrade Soil	Clay with Gravel (104)	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 425 Year: 1992
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Lean Clay with Sand	6
1	Clay	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: _____
 Type of Asphalt: PG70-22

	HMA	HMA		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
HMA					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1995	15.0	0	0	0	2005	0.8	0	0	14.8
1999	7.5	0	7.3	15.3					
2001	12.1	0	15.3	32.0					
2002	1.3	0	0	9.9					

LTPP Site Identification Number: 0103 State: Iowa (19)
 Roadway or Route No.: US 61
 Date of Construction: May 1992 Status: In Service

Location:
 Longitude: 91.25 Latitude: 40.70 Elevation: 530

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	2.1
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	1.7
3	ATB	Dense Graded Asphalt Treated Base (319)	8.4
2	GS	Embankment Soil; Clay with Gravel (104)	24
1	Subgrade Soil	Clay with Sand (107)	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 425 Year: 1992
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Lean Clay with Sand	6
1	Clay	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: _____
 Type of Asphalt: PG70-22

	HMA	HMA	ATB
Asphalt Content, %			
Air Voids, %			

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
HMA					
ATB					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1995	0	0	0	0	2005	9.8	0	0	12.5
1999	5.3	0	17.1	16.4					
2001	5.4	0	21.4	34.6					
2002	2.2	0	6.8	12.8					

LTPP Site Identification Number: 0105 State: Iowa (19)
 Roadway or Route No.: US 61
 Date of Construction: May 1992 Status: In Service

Location:
 Longitude: 91.25 Latitude: 40.70 Elevation: 530

Pavement Cross Section:

Layer	Material Type	Thickness, inches
5	HMA Hot Mixed, Hot Laid AC, Dense Graded (1)	1.8
4	HMA Hot Mixed, Hot Laid AC, Dense Graded (1)	1.7
3	ATB Dense Graded Asphalt Treated Base (319)	4.7
3	GB Crushed Stone Base (303)	4.0
2	GS Embankment Soil; Clay with Gravel (104)	24
1	Subgrade Soil Clay with Gravel (104)	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 425 Year: 1992
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Lean Clay with Sand	6
1	Clay	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: _____
 Type of Asphalt: PG70-22

	HMA	HMA	ATB	
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
HMA					
ATB					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1995	0	0	18.5	1.0	2005	1.1	0	0	23.0
1999	0	0	105.0	25.7					
2001	2.1	0	103.4	26.7					
2002	0.7	0	0	8.9					

LTPP Site Identification Number: 0115 State: Louisiana (22)
 Roadway or Route No.: US 171
 Date of Construction: Nov. 1992 Status: In Service

Location:
 Longitude: 93.20 Latitude: 30.33 Elevation: 27

Pavement Cross Section:

Layer	Material Type	Thickness, inches
5	HMA Hot Mixed, Hot Laid AC, Dense Graded (1)	1.7
4	HMA Hot Mixed, Hot Laid AC, Dense Graded (1)	5.3
3	ATB Hot Mixed, Hot Laid AC, Dense Graded (319)	9.0
2	GS Crushed Stone (131)	12.0
1	Subgrade Soil Lean Inorganic Clay (102)	---

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Crushed Stone	8
1	Lean Inorganic Clay	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	HMA	ATB
Asphalt Content, %	4.0	4.1	4.1
Air Voids, %	5.4	2.0	4.8

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	82	58	24	6.0
HMA	100	83	57	25	5.3
ATB					

Tensile Strain at Bottom of HMA Layer: 69.98

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1998	0	0	0	0					
1999	0	0	0	0					
2004	0	0	0	0					

LTPP Site Identification Number: 0116 State: Louisiana (22)
 Roadway or Route No.: US 171
 Date of Construction: Nov. 1992 Status: In Service

Location:
 Longitude: 93.20 Latitude: 30.33 Elevation: 27

Pavement Cross Section:

Layer	Material Type	Thickness, inches
5	HMA Hot Mixed, Hot Laid AC, Dense Graded (1)	1.9
4	HMA Hot Mixed, Hot Laid AC, Dense Graded (1)	2.8
3	ATB Hot Mixed, Hot Laid AC, Dense Graded (319)	11.3
2	GS Crushed Stone (131)	18.0
1	Subgrade Soil Lean Inorganic Clay (102)	---

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer No.	Material/Soil Type	Equivalent Resilient Modulus
2	Crushed Stone	8
1	Lean Inorganic Clay	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	HMA	ATB
Asphalt Content, %	4.0	4.1	4.1
Air Voids, %	2.1	3.3	6.1

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	82	58	24	6.0
HMA	100	83	57	25	5.3
ATB					

Tensile Strain at Bottom of HMA Layer: 69.28

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1998	0	0	0	0					
1999	0	0	0	0					
2004	0	0	0	0					

LTPP Site Identification Number: 0114 State: Louisiana (22)
 Roadway or Route No.: US 171
 Date of Construction: Nov. 1992 Status: In Service

Location:
 Longitude: 93.20 Latitude: 30.33 Elevation: 27

Pavement Cross Section:

Layer	Material Type	Thickness, inches
5	HMA Hot Mixed, Hot Laid AC, Dense Graded (1)	1.4
4	HMA Hot Mixed, Hot Laid AC, Dense Graded (1)	8.1
3	GB Crushed Stone (303)	11.4
2	GS Embankment, Silty Clay with Sand (133)	12.0
1	Subgrade Soil Lean Inorganic Clay (102)	---

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer No.	Material/Soil Type	Equivalent Resilient Modulus
3	Crushed Stone	8
1	Lean Inorganic Clay	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: _____
 Type of Asphalt: _____

	HMA	HMA		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
HMA					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1998	0	0	0	0					
1999	0	0	0	0					
2004	0	0	0	0					

LTPP Site Identification Number: 0124 State: Louisiana (22)
 Roadway or Route No.: US 171
 Date of Construction: Nov. 1992 Status: In Service

Location:
 Longitude: 93.20 Latitude: 30.33 Elevation: 27

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
6	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	1.3
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	5.9
4	ATB	Hot Mixed, Hot Laid, Plant Mix (319)	10.6
3	PATB	Open Graded, Hot Mix, Hot Laid (325)	3.6
2	GS	Embankment; Silt (141)	30
1	Subgrade Soil	Lean Inorganic Clay (102)	---

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Silt	8
1	Lean Inorganic Clay	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	HMA	ATB
Asphalt Content, %	4.0	4.1	4.1
Air Voids, %	5.3	2.9	6.8

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	82	58	24	6.0
HMA	100	83	57	25	5.3
ATB					

Tensile Strain at Bottom of HMA Layer: 41.06

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1998	0	0	0	0					
1999	0	0	0	0					
2004	0	0	0	0					

LTPP Site Identification Number: 0116
 Roadway or Route No.: US 27
 Date of Construction: Aug. 1995

State: Michigan (26)
 Status: Out of Service; 10-2002

Location:
 Longitude: 84.52 Latitude: 42.99 Elevation: 810

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded	1.8
3	HMA	Hot Mixed, Hot Laid AC, Dense Graded	2.1
2	ATB	HMAC	12.0
1	Subgrade Soil	Sandy Clay	---

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Sandy Clay	4

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 300
 Type of Asphalt: _____

	HMA	HMA	ATB	
Asphalt Content, %	5.1	5.0		
Air Voids, %	5.0	2.7	4.8	

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	78	47		
HMA	86	58	42		5.5
ATB					4.8

Tensile Strain at Bottom of HMA Layer: 106.03

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1995	0	0	0	0	2000	0	0	0	0
1996	0	0	0	0	2001	0	0	0	0
1998	0	0	0	0	2002	30.5	0	0	0
1999	0	0	0	0	2003	0	0	0	0

LTPP Site Identification Number: 0115
 Roadway or Route No.: US 27
 Date of Construction: Aug. 1995

State: Michigan (26)
 Status: Out of Service; 10-2002

Location:
 Longitude: 84.52 Latitude: 42.99 Elevation: 810

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	1.7
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded	1.6
3	HMA	Hot Mixed, Hot Laid AC, Dense Graded	2.6
2	ATB	HMAC	9.6
1	Subgrade Soil	Sandy Clay	---

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Sandy Clay	4

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 300
 Type of Asphalt: _____

	HMA	HMA	ATB	
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
HMA					
ATB					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1995	0	0	0	0	2000	0	0	0	0
1996	0	0	0	0	2001	0	0	0	0
1998	0	0	0	0	2002	105.7	0	0	0
1999	0	0	0	0	2003	0	0	0	0

LTPP Site Identification Number: 0116 State: Montana (30)
 Roadway or Route No.: Interstate 15
 Date of Construction: Oct. 1997 Status: In Service

Location:

Longitude: 111.53 Latitude: 47.41 Elevation: 3343

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded	4.7
3	ATB	Hot Mixed, Hot Laid AC, Dense Graded	12.6
2	SS	Embankment Soil; A2-4, (SP-SM)	24
1	Subgrade Soil	Poorly Graded Sand with Silt; A-2-6	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 800 Year: 1998
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Subgrade Soil	12

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: AC-10

	HMA	HMA	ATB	
Asphalt Content, %	5.0	5.0	4.7	
Air Voids, %	7.5	6.0	5.5	

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	85	45		6.0
HMA	88	57	39		4.2
ATB	84	48	32		4.5

Tensile Strain at Bottom of HMA Layer: 52.58

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1998	0	0	0	0	2002	3	0	0	0
1999	0	0	0	0	2003	8.1	0	0	0
2000	0	0	0	0	2004	55.4	0	0	0
2001	0.4	0	0	0	2005	0	0	0	0

LTPP Site Identification Number: 0114 State: Montana (30)
 Roadway or Route No.: Interstate 15
 Date of Construction: Oct. 1997 Status: In Service

Location:
 Longitude: 111.53 Latitude: 47.41 Elevation: 3343

Pavement Cross Section:

Layer	Material Type	Thickness, inches
5		
4	AC	Seal Coat
3	HMA	Hot Mixed, Hot Laid AC, Dense Graded
2	GB	Granular Base, Crushed Stone (303)
1	Subgrade Soil	Poorly Graded Sand with Silt; A-2-6

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 800 Year: 1998
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Subgrade Soil	12

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: _____
 Type of Asphalt: AC-10

	HMA			
Asphalt Content, %	5.0			
Air Voids, %	7.5			

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1998	0	0	0	0	2002	20.0	0	1.5	0
1999	0	0	0	0	2003	46.6	0	0	0
2000	5.9	0	0	0	2004	47.8	0	2.7	3.8
2001	9.0	0	5.1	0	2005	1.4	0	0	7.0

LTPP Site Identification Number: 0115 State: Montana (30)
 Roadway or Route No.: Interstate 15
 Date of Construction: Oct. 1997 Status: In Service

Location:
 Longitude: 111.53 Latitude: 47.41 Elevation: 3343

Pavement Cross Section:

Layer	Material Type	Thickness, inches
5		
4	AC	Seal Coat
3	HMA	Hot Mixed, Hot Laid AC, Dense Graded
2	ATB	Hot Mixed, Hot Laid AC, Dense Graded
1	Subgrade Soil	Poorly Graded Sand with Silt; A-2-6

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 800 Year: 1998
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Subgrade Soil	12

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: _____
 Type of Asphalt: AC-10

	HMA	ATB		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
ATB					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1998	0	0	0	0	2002	26.5	0	0	0
1999	0	0	0	0	2003	64.5	0	11.2	8.6
2000	0	0	0	0	2004	48.5	0	10.0	7.0
2001	23.1	0	0	0	2005	1.2	0	0	0

LTPP Site Identification Number: 0124 State: Montana (30)
 Roadway or Route No.: Interstate 15
 Date of Construction: Oct. 1997 Status: In Service

Location:
 Longitude: 111.53 Latitude: 47.41 Elevation: 3343

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded (1)	7.1
3	ATB	HMAC, Hot Laid, Central Plant Mix (319)	13.7
2	PATB	Open Graded, Hot Mixed, Hot Laid (323)	4.2
1	Subgrade Soil	Poorly Graded Sand with Silt	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 800 Year: 1998
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Poorly Graded Sand with Silt	8

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 400
 Type of Asphalt: AC-10

	HMA	HMA	ATB	
Asphalt Content, %	5.0	5.0	4.7	
Air Voids, %	7.5	6.0	5.5	

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	85	45		6.0
HMA	88	57	39		4.2
ATB	84	48	32		4.5

Tensile Strain at Bottom of HMA Layer: 31.16

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1998	0	0	0	0	2002	8	0	1.4	0
1999	0	0	0	0	2003	14.8	0	0	0
2000	0.6	0	3.3	0	2004	29.0	0	0	2.3
2001	4.3	0	5.4	0	2005	0.2	0	0	3.7

LTPP Site Identification Number: 0124 State: Nebraska (31)
 Roadway or Route No.: US 281
 Date of Construction: July 1995 Status: Out of Service: 9-2002

Location:
 Longitude: 97.62 Latitude: 40.07 Elevation: 1611

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	7.4
4	ATB	HMAC, Hot Laid, Central Plant Mix	10.5
3	PATB	Open Graded, Hot Mixed, Hot Laid	3.4
2	GS	Lean Inorganic Clay	24
1	Subgrade Soil	Lean Inorganic Clay	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 450 Year: 1997
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer No.	Material/Soil Type	Equivalent Resilient Modulus
2	Lean Inorganic Clay	5
1	Lean Inorganic Clay	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: PG64-22

	HMA	ATB		
Asphalt Content, %	4.5	4.5		
Air Voids, %	6.8	3.0		

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	87	74		6.9
ATB	97	72	53		3.9

Tensile Strain at Bottom of HMA Layer: 43.40

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1995	0	0	0	0					
1999	0	0	0	0					
2002	0	0	0	0					

LTPP Site Identification Number: 0115 State: Nebraska (31)
 Roadway or Route No.: US 81
 Date of Construction: July 1995 Status: In Service

Location:
 Longitude: 97.62 Latitude: 40.07 Elevation: 1611

Pavement Cross Section:

Layer	Material Type	Thickness, inches
4	HMA Hot Mixed, Hot Laid AC, Dense Graded	6.5
3	ATB HMAC	8.6
2	GS Lean Inorganic Clay; A-6	24
1	Subgrade Soil Lean Inorganic Clay; A-7-5	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 450 Year: 1997
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Lean Inorganic Clay	5
1	Lean Inorganic Clay	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	ATB		
Asphalt Content, %	4.8	4.1		
Air Voids, %	5.0	9.0		

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	87	74		6.9
ATB	97	72	53		3.9

Tensile Strain at Bottom of HMA Layer: 79.91

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1995	0	0	0	0					
1999	0	0	0	0					
2002	0	0	0	0					

LTPP Site Identification Number: 0116 State: Nebraska (31)
 Roadway or Route No.: US 81
 Date of Construction: July 1995 Status: In Service

Location:
 Longitude: 97.62 Latitude: 40.07 Elevation: 1611

Pavement Cross Section:

Layer	Material Type	Thickness, inches
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded; (1) 4.1
3	ATB	Hot Mixed, Hot Laid AC, Dense Graded (1) 12.2
2	GS	Lean Inorganic Clay; A-6 24.0
1	Subgrade Soil	Lean Inorganic Clay; A-7-6 ---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 450 Year: 1997
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer No.	Material/Soil Type	Equivalent Resilient Modulus
2	Lean Inorganic Clay	5
1	Lean Inorganic Clay	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: PG64-22

	HMA	ATB		
Asphalt Content, %	4.7	4.1		
Air Voids, %	4.5	7.0		

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	87	74		6.9
ATB	95	68	50		2.2

Tensile Strain at Bottom of HMA Layer: 70.02

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1995	0	0	0	0					
1999	0	0	0	0					
2002	0	0	0	0					

LTPP Site Identification Number: 0104 State: Nevada (32)
 Roadway or Route No.: Interstate 80
 Date of Construction: Aug. 1995 Status: In Service

Location:
 Longitude: 117.01 Latitude: 40.69 Elevation: 4550

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	7.3
4	ATB	Hot Mixed, Hot Laid, Plant Mix	12.4
3	GS	Soil Agg. Mix.	18.4
2	TS	Lime Treated Soil	12.0
1	Subgrade Soil	Silty Sand	---

Traffic Data:

Number of Years with Data: 1
 AADTT (One-way): 926 Year: 1996
 KESALS per year: 492

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
3	Lime Treated Soil	14
2	Soil Agg. Mix.	28
1	Silty Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: PG64-22

	HMA	ATB		
Asphalt Content, %	4.7	4.6		
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	96	73	62	21	5.6
ATB					

Tensile Strain at Bottom of HMA Layer: 37.37

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1996	0	0	0	0	2002	0	0	0	0
1998	0	0	18.8	0	2003	0	0	0	0.9
1999	5	0	0	0	2004	0	0	0	1.2
2000	0	0	0	0	2005	0	0	0	3.1
2001	0	0	0	0	2006	0	0	0	5.6

LTPP Site Identification Number: 0101 State: Nevada (32)
 Roadway or Route No.: Interstate 80
 Date of Construction: Aug. 1995 Status: In Service

Location:
 Longitude: 117.01 Latitude: 40.69 Elevation: 4550

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	7.2
4	GB	Crushed Gravel (304)	8.5
3	GS	Soil Agg. Mix, predominately coarse grained (308)	22.8
2	TS	Lime Treated Soil (338)	12.0
1	Subgrade Soil	Silty Sand (214)	---

Traffic Data:

Number of Years with Data: 1
 AADTT (One-way): 926 Year: 1996
 KESALS per year: 492

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Lime Treated Soil	14
3	Soil Agg. Mix.	28
1	Silty Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: _____
 Type of Asphalt: PG64-22

	HMA			
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1997	0	0	0	0	2002	1.2	0	10.6	0
1998	0	0	7.3	0	2003	0	0	12.0	0
1999	0	0	0	0	2004	0.9	0	0	1.3
2000	0.5	0	0.3	0	2005	1.6	0	0	2.5
2001	1.4	0	0	0	2006	2.0	0	0	6.5

LTPP Site Identification Number: 0103 State: Nevada (32)
 Roadway or Route No.: Interstate 80
 Date of Construction: Aug. 1995 Status: In Service

Location:
 Longitude: 117.01 Latitude: 40.69 Elevation: 4550

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	4.1
4	ATB	Hot Mixed, Hot Laid AC, Dense Graded	8.1
3	GS	Soil Agg. Mix.; coarse grained (308)	24.5
2	TS	Lime Treated Soil (338)	12.0
1	Subgrade Soil	Clayey Sand (216)	---

Traffic Data:

Number of Years with Data: 1
 AADTT (One-way): 926 Year: 1996
 KESALS per year: 492

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Lime Treated Soil	14
3	Soil Agg. Mix.	28
1	Clayey Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: _____
 Type of Asphalt: PG64-22

	HMA			
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1997	0	0	0	0	2002	28.8	0	0	0
1998	0	0	0	0	2003	32.9	0	0	0
1999	0	0	0	0	2004	34.1	0	0	0
2000	33.8	0	0	0					
2001	16.5	0	0	0					

LTPP Site Identification Number: 0105 State: Nevada (32)
 Roadway or Route No.: Interstate 80
 Date of Construction: Aug. 1995 Status: In Service

Location:
 Longitude: 117.01 Latitude: 40.69 Elevation: 4550

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
6	HMA	Hot Mixed, Hot Laid AC, Dense Graded	4.2
5	ATB	Hot Mixed, Hot Laid AC, Dense Graded	4.8
4	GB	Crushed Gravel (304)	3.6
3	GS	Soil Agg. Mix.; coarse grained (308)	23.7
2	TS	Lime Treated Soil (338)	12.0
1	Subgrade Soil	Silty Sand (214)	---

Traffic Data:

Number of Years with Data: 1
 AADTT (One-way): 926 Year: 1996
 KESALS per year: 492

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Lime Treated Soil	14
3	Soil Agg. Mix.	28
1	Silty Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: _____
 Type of Asphalt: PG64-22

	HMA	ATB		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
ATB					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1997	0	0	0	0	2002	0	0	1.5	0
1998	0	0	0	0	2003	1.3	0	0	0
1999	0.4	0	0	0	2004	1.5	0	0	0
2000	16.4	0	0	0					
2001	10.4	0	0	0					

LTPP Site Identification Number: 0106 State: Nevada (32)
 Roadway or Route No.: Interstate 80
 Date of Construction: Aug. 1995 Status: In Service

Location:
 Longitude: 117.01 Latitude: 40.69 Elevation: 4550

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
6	HMA	Hot Mixed, Hot Laid AC, Dense Graded	7.2
5	ATB	Hot Mixed, Hot Laid AC, Dense Graded	8.8
4	GB	Crushed Gravel (304)	3.7
3	GS	Soil Agg. Mix.; coarse grained (308)	18.3
2	TS	Lime Treated Soil (338)	12.0
1	Subgrade Soil	Clayey Sand (216)	---

Traffic Data:

Number of Years with Data: 1
 AADTT (One-way): 926 Year: 1996
 KESALS per year: 492

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Lime Treated Soil	14
3	Soil Agg. Mix.	28
1	Clayey Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: _____
 Type of Asphalt: PG64-22

	HMA	ATB		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
ATB					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1997	0	0	0	0	2002	0	0	1.3	1.0
1998	0	0	0	0	2003	0.2	0	0	1.3
1999	0	0	0	0	2004	0.2	0	0	1.7
2000	0	0	0	0	2005	0.3	0	0	2.3
2001	0	0	0	1.2	2006	0.5	0	0	3.9

LTPP Site Identification Number: 0112 State: Nevada (32)
 Roadway or Route No.: Interstate 80
 Date of Construction: Aug. 1995 Status: In Service

Location:
 Longitude: 117.01 Latitude: 40.69 Elevation: 4550

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
6	HMA	Hot Mixed, Hot Laid AC, Dense Graded	4.5
5	ATB	HMAC, Hot Laid, Central Plant Mix	12.4
4	PATB	Open Graded, Hot Mixed, Hot Laid	4.2
3	GS	Soil Agg. Mix.	15.1
2	TS	Lime Treated Soil	12.0
1	Subgrade Soil	Clayey Sand	---

Traffic Data:

Number of Years with Data: 1
 AADTT (One-way): 926 Year: 1996
 KESALS per year: 492

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
3	Lime Treated Soil	14
2	Soil Agg. Mix.	28
1	Clayey Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: PG64-22

	HMA	ATB		
Asphalt Content, %	4.7	4.6		
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	95	70	54	16	5.0
ATB					

Tensile Strain at Bottom of HMA Layer: 33.35

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1996	0	0	0	0	2002	0	0	0	1.1
1998	0	0	0	0	2003	0	0	0	1.1
1999	0	0	0	0	2004	0	0	0	1.1
2000	0	0	0	0	2005	0.3	0	0	4.8
2001	0	0	0	1.1	2006	0.3	0	0	4.6

LTPP Site Identification Number: 0106 State: New Mexico (35)
 Roadway or Route No.: IH 25
 Date of Construction: Nov. 1995 Status: In Service

Location:
 Longitude: 107.07 Latitude: 32.68 Elevation: 4117

Pavement Cross Section:

Layer	Material Type	Thickness, inches
5	AC	Friction Course
		0.6
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded
		7.0
3	ATB	Hot Mixed, Hot Laid AC, Dense Graded
		8
2	GB	Crushed Stone
		2.9
1	Subgrade Soil	Sandy Fat Clay

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 594 Year: 1997
 KESALS per year: 152

Unbound Layers Resilient Modulus:

Layer No.	Material/Soil Type	Equivalent Resilient Modulus
2	Crushed Stone	25
1	Sandy Fat Clay	5.5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	ATB		
Asphalt Content, %	4.8	4.5		
Air Voids, %	7.0	7.3		

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	95	71	53	17	5.2
ATB	97	78	57	19	4.5

Tensile Strain at Bottom of HMA Layer: 70.15

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1997	0	0	0	0	2003	0	0	3.5	0
1999	0	0	0	0	2004	0	0	3.6	0
2000	0	0	0	0	2005	0	0	3.6	0
2001	0	0	0	0	2006	0.6	0	5.1	0
2002	0	0	3.5	0					

LTPP Site Identification Number: 0103 State: New Mexico (35)
 Roadway or Route No.: IH 25
 Date of Construction: Nov. 1995 Status: In Service

Location:
 Longitude: 107.07 Latitude: 32.68 Elevation: 4117

Pavement Cross Section:

Layer	Material Type	Thickness, inches
5		
4	AC	Friction Course (2)
3	HMA	Hot Mixed, Hot Laid AC, Dense Graded
2	ATB	Hot Mixed, Hot Laid AC, Dense Graded (319)
1	Subgrade Soil	Fat Inorganic Clay (103)

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 594 Year: 1997
 KESALS per year: 152

Unbound Layers Resilient Modulus:

Layer No.	Material/Soil Type	Equivalent Resilient Modulus
1	Fat Inorganic Clay	5.5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	ATB		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
ATB					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1997	0	0	0	0	2003	0.1	0	12.5	0
1999	0	0	0	0	2004	0.2	0	20.4	0
2000	0	0	0	0	2005	0.3	0	26.7	0
2001	0	0	0	0	2006	0.3	0	36.2	0.4
2002	0.1	0	11.0	0					

LTPP Site Identification Number: 0107 State: New Mexico (35)
 Roadway or Route No.: IH 25
 Date of Construction: Nov. 1995 Status: In Service

Location:
 Longitude: 107.07 Latitude: 32.68 Elevation: 4117

Pavement Cross Section:

Layer	Material Type	Thickness, inches
5	AC Friction Course (2)	0.6
4	HMA Hot Mixed, Hot Laid AC, Dense Graded	5.3
3	ATB Open Graded, Hot Mixed, Hot Laid AC (325)	3.7
2	GB Crushed Stone Base (303)	4.0
1	Subgrade Soil Sandy Fat Clay with Sand (109)	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 594 Year: 1997
 KESALS per year: 152

Unbound Layers Resilient Modulus:

Layer No.	Material/Soil Type	Equivalent Resilient Modulus
1	Fat Clay with Sand	5.5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	ATB		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
ATB					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1997	0	0	0	0	2003	0.5	0	33.0	0
1999	0	0	0	0	2004	1.0	0	46.6	1.7
2000	0	0	0	0	2005	1.0	0	48.1	1.8
2001	0	0	0	0	2006	1.2	0	56.4	6.0
2002	0	0	22.6	0					

LTPP Site Identification Number: 0111 State: New Mexico (35)
 Roadway or Route No.: IH 25
 Date of Construction: Nov. 1995 Status: In Service

Location:
 Longitude: 107.07 Latitude: 32.68 Elevation: 4117

Pavement Cross Section:

Layer	Material Type	Thickness, inches
5	AC Friction Course	0.6
4	HMA Hot Mixed, Hot Laid AC, Dense Graded	4.3
3	ATB HMAC, Hot Laid, Central Plant Mix	7.6
2	PATB Open Graded Mix	3.7
1	Subgrade Soil Clayey Sand	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 594 Year: 1997
 KESALS per year: 152

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Clayey Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	ATB		
Asphalt Content, %	4.3	4.2		
Air Voids, %	8.2	7.3		

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	95	73	51	16	4.0
ATB	97	78	57	19	4.5

Tensile Strain at Bottom of HMA Layer: 61.73

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1997	0	0	0	0	2003	0	0	0	0
1999	0	0	0	0	2004	0	0	0	0
2000	0	0	0	0	2005	0	0	0	0
2001	0	0	0	0	2006	0	0	0	0
2002	0	0	0	0					

LTPP Site Identification Number: 0106 State: Ohio (39)
 Roadway or Route No.: US 23
 Date of Construction: Jan. 1994 Status: In Service

Location:
 Longitude: 83.07 Latitude: 40.43 Elevation: 950

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded	6.8
3	ATB	Hot Mixed, Hot Laid AC, Plant Mix	7.9
2	GB	Crushed Stone	3.9
1	Subgrade Soil	Silty Clay	---

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Crushed Stone	10
1	Silty Clay	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 250
 Type of Asphalt: _____

	HMA	HMA	ATB	
Asphalt Content, %	6.5	6.5	5.2	
Air Voids, %	10.4	6.8	14.6	

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	88	52	13	5.9
HMA	89	61	44	10	5.0
ATB	67	54	37	12	7.0

Tensile Strain at Bottom of HMA Layer: 128.23

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1996	0	0	0	0	2002	62.8	0	223.4	0
1997	0	0	0	0	2004	204.1	0	0	0
1999	0	0	9.5	0	2005	274.1	290	0	0
2001	17.7	0	201.6	0					

LTPP Site Identification Number: 0112 State: Ohio (39)
 Roadway or Route No.: US 23
 Date of Construction: Jan. 1994 Status: In Service

Location:
 Longitude: 83.07 Latitude: 40.43 Elevation: 950

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	1.7
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded	2.3
3	ATB	Hot Mixed, Hot Laid AC, Plant Mix	11.8
2	PATB	Open Graded, Plant Mix	4.0
1	Subgrade Soil	Silty Clay	---

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
1	Silty Clay	5

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 250
 Type of Asphalt: _____

	HMA	HMA	ATB	
Asphalt Content, %	6.5	6.5	5.2	
Air Voids, %	11.3	7.6	5.0	

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	89	53	12	5.7
HMA	94	74	54	12	6.1
ATB	62	49	33	12	7.3

Tensile Strain at Bottom of HMA Layer: 128.23

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1996	0	0	0	0	2004	138.3	0	0	0
1999	0	0	3.5	0	2005	244.0	320	0	0
2001	0	0	107.5	0					
2002	20.5	0	37.8	0					

LTPP Site Identification Number: 0902 State: Ohio (39)
 Roadway or Route No.: US 23
 Date of Construction: Jan. 1994 Status: In Service

Location:
 Longitude: 83.07 Latitude: 40.43 Elevation: 950

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
6	HMA	Hot Mixed, Hot Laid AC, Dense Graded	1.8
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	2.3
4	ATB	Asphalt Treated Mixture, Plant Mix	12.0
3	PATB	Open Graded, Hot Laid, Central Plant Mix	3.7
2	GS	Crushed Stone	6
1	Subgrade Soil	Silty Clay	---

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
3	Open Graded, Hot Laid, Central Plant Mix	25
2	Crushed Stone	80
1	Silty Clay	8

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	ATB		
Asphalt Content, %	6.4	5.4		
Air Voids, %	7.1	9.1		

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	88	61		4.6
ATB	100	78	58		4.8

Tensile Strain at Bottom of HMA Layer: 49.22

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1996	0	0	0	0	2004	1.3	0	0	0
1999	0	0	0	0					
2001	0	0	4.9	0					

LTPP Site Identification Number: 0903 State: Ohio (39)
 Roadway or Route No.: US 23
 Date of Construction: Jan. 1994 Status: In Service

Location:
 Longitude: 83.07 Latitude: 40.43 Elevation: 950

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
6	HMA	Hot Mixed, Hot Laid AC, Dense Graded	1.8
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	2.2
4	ATB	Asphalt Treated Mixture, Plant Mix	12.0
3	PATB	Open Graded, Hot Laid, Plant Mix	3.7
2	GS	Crushed Stone	6.0
1	Subgrade Soil	Silty Clay	---

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer No.	Material/Soil Type	Equivalent Resilient Modulus
3	Open Graded, Hot Laid, Central Plant Mix	25
2	Crushed Stone	80
1	Silty Clay	8

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	ATB		
Asphalt Content, %	5.4	5.4		
Air Voids, %	12.8	11.4		

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	86	51		4.7
ATB	100	67	49		7.0

Tensile Strain at Bottom of HMA Layer: 49.07

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1996	0	0	0	0	2004	154.1	0	0	0
1999	0	0	0	0					
2001	0	0	123.8	0					

LTPP Site Identification Number: 0115 State: Oklahoma (40)
 Roadway or Route No.: US 62
 Date of Construction: July 1997 Status: In Service

Location:
 Longitude: 98.66 Latitude: 34.64 Elevation: _____

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded	7.5
3	ATB	Asphalt Treated Base, Plant Mix	9.0
2	TS	Lime Treated Soil	8.0
1	Subgrade Soil	Clayey Sand	144

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 775 Year: 1997
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Lime Treated Soil	28
1	Clayey Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: PG-6422

	HMA	HMA	ATB	
Asphalt Content, %	4.8	4.7	4.6	
Air Voids, %	4.5	3.0	4.5	

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	86	63	46		5.3
HMA	82	55	41		7.6
ATB	79	52	38		8.9

Tensile Strain at Bottom of HMA Layer: 53.19

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1997	0	0	0	0	2001	0	0	0	3.8
1997	0	0	0	0	2002	0	0	0	3.8
1999	0	0	0	0	2003	0	0	0	3.8
2000	0	0	0	2.2					

LTPP Site Identification Number: 0114 State: Oklahoma (40)
 Roadway or Route No.: US 62
 Date of Construction: July 1997 Status: In Service

Location:
 Longitude: 98.66 Latitude: 34.64 Elevation: _____

Pavement Cross Section:

Layer	Material Type	Thickness, inches
6		
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded
3	GB	Granular, Crushed Stone (303)
2	TS	Lime Treated Soil (338)
1	Subgrade Soil	Clayey Sand (216)

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 775 Year: 1997
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
3	Crushed Gravel	25
2	Lime Treated Soil	28
1	Clayey Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: PG64-22

	HMA	HMA		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
HMA					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1997	0	0	0	0	2002	3.9	0	0	0
1999	0	0	0	0	2003	12.6	0	0	0
2000	0	0	0	0	2004	22.5	0	0	0.6
2001	0	0	0	0	2006	32.3	0	0	5.0

LTPP Site Identification Number: 0117 State: Oklahoma (40)
 Roadway or Route No.: US 62
 Date of Construction: July 1997 Status: In Service

Location:
 Longitude: 98.66 Latitude: 34.64 Elevation: _____

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
6	HMA	Hot Mixed, Hot Laid AC, Dense Graded	1.9
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	2.7
4	ATB	Asphalt Treated Base, Plant Mix	8.3
3	GB	Granular, Crushed Gravel	3.6
2	TS	Lime Treated Soil	8.0
1	Subgrade Soil	Clayey Sand	72

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 775 Year: 1997
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
3	Crushed Gravel	25
2	Lime Treated Soil	28
1	Clayey Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: PG64-22

	HMA	HMA	ATB	
Asphalt Content, %	4.4	4.2	4.5	
Air Voids, %	8.0	5.0	3.0	

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	82	63		4.1
HMA	85	50	47		4.8
ATB	82	55	41		8.3

Tensile Strain at Bottom of HMA Layer: 53.19

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1997	0	0	0	0	2002	0	0	0	0
1999	0	0	0	0	2003	0.5	0	0	0
2000	0	0	0	0					
2001	0	0	0	0					

LTPP Site Identification Number: 0160 State: Oklahoma (40)
 Roadway or Route No.: US 62
 Date of Construction: July 1997 Status: In Service

Location:
 Longitude: 98.66 Latitude: 34.64 Elevation: _____

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
6	HMA	Hot Mixed, Hot Laid AC, Dense Graded	1.5
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	6.5
4	ATB	Asphalt Treated Base, Plant Mix (319)	4.0
3	GB	Granular, Crushed Stone (303)	5.4
2	TS	Lime Treated Soil (338)	8.0
1	Subgrade Soil	Clayey Sand (216)	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 775 Year: 1997
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
3	Crushed Gravel	25
2	Lime Treated Soil	28
1	Clayey Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: PG64-22

	HMA	HMA	ATB	
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
HMA					
ATB					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1997	0	0	0	0	2002	0	0	0	0
1999	0	0	0	0	2003	0	0	0	0
2000	0	0	0	0	2004	0	0	0	0
2001	0	0	0	0	2006	0	0	0	0

LTPP Site Identification Number: 0116 State: Texas (48)
 Roadway or Route No.: US 281
 Date of Construction: April 1997 Status: Out of Service; 4-2002

Location:
 Longitude: 98.11 Latitude: 26.74 Elevation: 84

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	2.4
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded	3.5
3	ATB	Asphalt Treated Base, Plant Mix	10.9
2	TS	Lime Treated Soil	24.0
1	Subgrade Soil	Poorly Graded Sand With Silt	---

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Lime Treated Soil	28
1	Poorly Graded Sand With Silt	12

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	ATB		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
ATB					

Tensile Strain at Bottom of HMA Layer: 46.00

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1997	0	0	0	0	2002	0	0	0	0
1998	0	0	0	0	2002	0	0	0	0
1999	0	0	0	0	2003	0	0	0	0
2000	0	0	0	0	2004	0	0	0	0
2001	0	0	0	0	2005	0.4	0	0	0

LTPP Site Identification Number: 0124 State: Texas (48)
 Roadway or Route No.: US 281
 Date of Construction: April 1997 Status: Out of Service; 4-2002

Location:
 Longitude: 98.11 Latitude: 26.74 Elevation: 84

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
6	HMA	Hot Mixed, Hot Laid AC, Dense Graded	2.2
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	4.2
4	ATB	HMAC, Hot Laid, Central Plant Mix	10.8
3	PATB	Open Graded, Plant Mix	4.2
2	TS	Lime Treated Soil	24.0
1	Subgrade Soil	Poorly Graded Sand with Silt	---

Traffic Data:

Number of Years with Data: _____
 AADTT (One-way): _____ Year: _____
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Lime Treated Soil	28
1	Poorly Graded Sand with Silt	12

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	ATB		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
ATB					

Tensile Strain at Bottom of HMA Layer: 30.69

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1997	0	0	0	0	2002	0	0	0	0
1998	0	0	0	0	2003	0	0	0	0
1999	0	0	0	0	2004	0	0	0	0
2000	0	0	0	0	2005	0	0	0	0
2001	0	0	0	0					

LTPP Site Identification Number: 1070 State: Texas (48)
 Roadway or Route No.: SH 175
 Date of Construction: 7-1-1977 Status: Out of Service: 7-2003

Location:
 Longitude: 96.38 Latitude: 32.59 Elevation: 429

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	1.2
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded	9.3
3	ATB	Other; Treated Layer	13.5
2	TS	Lime Treated Soil	10.0
1	Subgrade Soil	Fat Inorganic Clay	---

Traffic Data:

Number of Years with Data: 8
 AADTT (One-way): 532 Year: 1997
 KESALS per year: 153

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Lime Treated Soil	28
1	Fat Inorganic Clay	6

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: _____

	HMA	ATB		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
ATB					

Tensile Strain at Bottom of HMA Layer: 32.30

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1991	0	0	46	82	2000	1.8	216.7	25.6	215.2
1993	0	0	53.2	85.7	2002	1.5	220.8	23.6	215.0
1995	0	0	77.9	147.6	2003	1.7	211.6	16.1	245.9
1998	3.2	320.3	3	30.9					

LTPP Site Identification Number: 1048 State: Texas (48)
 Roadway or Route No.: US 385
 Date of Construction: 11-1-1974 Status: Out of Service: 8-1996

Location:
 Longitude: 102.38 Latitude: 31.88 Elevation: 2942

Pavement Cross Section:

Layer	Material Type	Thickness, inches
3	HMA	Hot Mixed, Hot Laid, Dense Graded Mix (1)
2	ATB	Open Graded, Plant Mix (319)
1	Subgrade Soil	Coarse Grained Soil (215)

Traffic Data:

Number of Years with Data: 6
 AADTT (One-way): 103 Year: 1996
 KESALS per year: 20

Unbound Layers Resilient Modulus:

Layer No.	Material/Soil Type	Equivalent Resilient Modulus
1	215	---

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: ---
 Type of Asphalt:

	HMA	ATB		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
ATB					

Tensile Strain at Bottom of HMA Layer:

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1991	0	0	0	56.4					
1993	0	0	35.1	61.1					
1995	0.7	0	46.2	63.5					
1996	7	7.5	7	51.9					

LTPP Site Identification Number: 0124 State: Wisconsin (55)
 Roadway or Route No.: US 29
 Date of Construction: Nov. 1997 Status: Out of Service in 2008

Location:

Longitude: 89.29 Latitude: 44.87 Elevation: 1239

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
6	HMA	Hot Mixed, Hot Laid AC, Dense Graded	1.9
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	5.2
4	ATB	HMAC, Hot Laid, Central Plant Mix	11.7
3	PATB	Open Graded, Plant Mix	3.3
2	GS	Soil Agg. Mix.; A-1-b	8.0
1	Subgrade Soil	Silty Sand; A-1-b	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 260 Year: 1997
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Soil Agg. Mix.	14
1	Silty Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: AC-20

	HMA	HMA	ATB	
Asphalt Content, %	4.9	5.0	3.3	
Air Voids, %	7.5	6.2	5.9	

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	99	86	66		3.5
HMA	99	86	66		3.5
ATB	92	53	37		3.0

Tensile Strain at Bottom of HMA Layer: 34.73

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1998	0	0	0	0	2005	0	0	0	0
2000	0	0	0	0					
2002	0	0	0	0					
2004	0	0	0	0					

LTPP Site Identification Number: 0116 State: Wisconsin (55)
 Roadway or Route No.: US 29
 Date of Construction: Nov. 1997 Status: Out of Service in 2008

Location:

Longitude: 89.29 Latitude: 44.87 Elevation: 1239

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	2.1
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded	2.0
3	ATB	HMAC, Hot Laid, Central Plant Mix	12.0
2	GB	Granular Base; A-1-a	10.8
1	Subgrade Soil	Silty Sand; A-1-b	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 260 Year: 1997
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Granular Base, Soil Agg. Mix.	14
1	Silty Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: AC-20

	HMA	HMA	ATB	
Asphalt Content, %	5.2	4.9	3.8	
Air Voids, %	5.1	7.3	6.6	

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	88	69		6.5
HMA	99	80	57		3.9
ATB	92	53	37		3.0

Tensile Strain at Bottom of HMA Layer: 34.73

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1998	0	0	0	0	2005	0	0	0	0
2000	0	0	0	0					
2002	0	0	0	0					
2004	1.61	0	0	0					

LTPP Site Identification Number: 0118 State: Wisconsin (55)
 Roadway or Route No.: US 29
 Date of Construction: Nov. 1997 Status: Out of Service in 2008

Location:

Longitude: 89.29 Latitude: 44.87 Elevation: 1239

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	1.9
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded	2.1
3	ATB	HMAC, Hot Laid, Central Plant Mix	8.9
2	GB	Granular Base; A-1-b	14.2
1	Subgrade Soil	Silty Sand; A-1-a	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 260 Year: 1997
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Granular Base, Soil Agg. Mix.	14
1	Silty Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: AC-20

	HMA	HMA	ATB	
Asphalt Content, %	5.0	4.9	3.8	
Air Voids, %	6.6	7.2	6.1	

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	99	86	66		3.5
HMA	99	86	66		3.5
ATB	88	68	58		4.1

Tensile Strain at Bottom of HMA Layer: 34.73

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1998	0	0	0	0	2005	0	0	0	0
2000	0	0	0	0					
2002	0	0	0	0					
2004	0	0	0	0					

LTPP Site Identification Number: 0114 State: Wisconsin (55)
 Roadway or Route No.: US 29
 Date of Construction: Nov. 1997 Status: Out of Service in 2008

Location:

Longitude: 89.29 Latitude: 44.87 Elevation: 1239

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	1.7
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded	6.4
3	GB	Crushed Stone Base (303)	11.0
2	GS	Soil Agg. Mix.; A-1-b (308)	10.0
1	Subgrade Soil	Poorly Graded Sand with Gravel & Silt (205)	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 260 Year: 1997
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Soil Agg. Mix.	14
1	Poorly Graded Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: AC-20

	HMA	HMA		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
HMA					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1998	0	0	0	0	2005	0	0	0	0
2000	0	0	0	0					
2002	0	0	0	0					
2005									

LTPP Site Identification Number: C903 State: Wisconsin (55)
 Roadway or Route No.: US 29
 Date of Construction: Nov. 1996 Status: In Service

Location:

Longitude: 89.29 Latitude: 44.87 Elevation: 1239

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	2.0
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded	7.2
3	GB	Crushed Stone Base; A-1-a	13.0
2	GS	Embankment; Coarse-Fine soil; A-3	5.0
1	Subgrade Soil	Silty Sand; A-1-b	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 260 Year: 1997
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Granular Base, Soil Agg. Mix.	14
1	Silty Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: PG58-340

	HMA	HMA		
Asphalt Content, %	5.0	5.0		
Air Voids, %	8.0	8.0		

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA	100	73	42		3.7
HMA	99	69	51		3.4

Tensile Strain at Bottom of HMA Layer: 34.73

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1998	0	0	0	0	2005	5.2	0	0	1.0
2000	0	0	0	0					
2002	0	0	0	0					
2004	2.9	0	0	0					

LTPP Site Identification Number: C901 State: Wisconsin (55)
 Roadway or Route No.: US 29
 Date of Construction: Nov. 1996 Status: In Service

Location:
 Longitude: 89.29 Latitude: 44.87 Elevation: 1239

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	2.0
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded	7.8
3	GB	Crushed Stone Base; A-1-a (303)	13.0
2	GS	Embankment; Coarse-Fine soil; A-3 (210)	24.0
1	Subgrade Soil	Well Graded Sand with Silt & Gravel (211)	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 260 Year: 1997
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Granular Base, Soil Agg. Mix.	14
1	Well Graded Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: PG58-340

	HMA	HMA		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
HMA					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1998	0	0	0	0					
2000	0	0	0	0					
2002	0	0	0	0					
2004	0	0	0	0					

LTPP Site Identification Number: C960 State: Wisconsin (55)
 Roadway or Route No.: US 29
 Date of Construction: Nov. 1996 Status: In Service

Location:
 Longitude: 89.29 Latitude: 44.87 Elevation: 1239

Pavement Cross Section:

Layer	Material Type	Thickness, inches	
5	HMA	Hot Mixed, Hot Laid AC, Dense Graded	1.9
4	HMA	Hot Mixed, Hot Laid AC, Dense Graded	6.4
3	GB	Crushed Stone Base; A-1-a (303)	13.0
2	GS	Embankment; Coarse-Fine soil; A-3 (210)	5.0
1	Subgrade Soil	Silty Sand; A-1-b (214)	---

Traffic Data:

Number of Years with Data: 4
 AADTT (One-way): 260 Year: 1997
 KESALS per year: _____

Unbound Layers Resilient Modulus:

Layer	Material/Soil Type	Equivalent Resilient Modulus, ksi
2	Granular Base, Soil Agg. Mix.	14
1	Silty Sand	10

Hot Mix Asphalt Mixtures:

Equivalent Annual Modulus of HMA: 450
 Type of Asphalt: PG58-340

	HMA	HMA		
Asphalt Content, %				
Air Voids, %				

Gradation; percent passing:

	#3/4	#3/8	#4	#40	#200
HMA					
HMA					

Tensile Strain at Bottom of HMA Layer: _____

Total Amount of Fatigue Cracking:

Year	Alligator	Block	Long.	Transverse	Year	Alligator	Block	Long.	Transverse
1998	0	0	0	0					
2000	52.4	0	0	0					
2004	262.6	0	0	0					